

On the Mineral containing Rare Elements (Part 10) Allanite found in Angaku Mine, Kokaido, Korea

By

Jitsutaro TAKUBO and Mitsue SAITO

Geological and Mineralogical Institute, University of Kyoto

(Received Oct. 2, 1947)

The Angaku Mine lies about 19km to the north of the Shinsen railway station on the Kokai branch of the Keijyo-Shigishu line. Pre-Cambrian granite gneiss and Cretaceous biotite granite and a large number of aplites, pegmatites and quartz veins, probably derived from the late biotite granite intrusion, are distributed in this field. These veins are, however, mostly located in the granite gneiss area and so their crop-

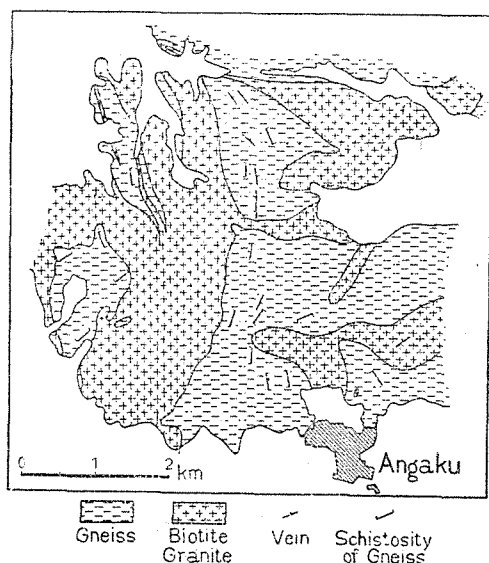


Fig. 1

tings are quite restricted with its schistosity (see Fig.1). Allanite under consideration is contained in some pegmatites or aplites, accompanied with several other minerals, such as garnet, hornblende, tremolite and zircon. On the occurrence of allanite, we are able to present the following general conclusions from our field observations which may make an important basis of genetical consideration. (1) Allanite is contained in the pegmatite or aplite vein, but never in the quartz vein. (2) Generally the aplite or pegmatite veins, located in biotite granite, do not contain allanite. In rare cases, however, we can find its small crystals aggregated with biotite only around the xenolith of the granite gneiss. (3) Associated with both biotite and garnet, it is usually shown in small crystal form, while in the case of allanite associated with biotite only, it is shown in

ings are quite restricted with its schistosity (see Fig.1). Allanite under consideration is contained in some pegmatites or aplites, accompanied with several other minerals, such as garnet, hornblende, tremolite and zircon. On the occurrence of allanite, we are able to present the following general conclusions from our field observations which may make an important basis of genetical consideration. (1) Allanite is contained in the pegmatite or aplite vein, but never in the quartz vein. (2) Generally the aplite or pegmatite veins, located in biotite granite, do not contain allanite. In rare cases, however, we can find its small crystals aggregated with biotite only around the xenolith of the granite gneiss. (3) Associated with both biotite and garnet, it is usually shown in small crystal form, while in the case of allanite associated with biotite only, it is shown in

large crystal form. There is no case in which it is associated with garnet only. (4) Allanite is contained not only in the aplite or pegmatite veins, but also in granite gneiss, in contact with the vein. In this case, it appears generally in large masses, accompanied with biotite in large crystal form.

Physical Properties : $H = 5-6$ The color is black; The streak is brown, and each fresh fracture has a somewhat resinous luster. Specific gravity was determined by the pycnometer method with two specimens; one that is associated with both biotite and garnet (1) and the other with hornblende, tremolite, quartz, zircon and titanite (2). Under the microscope, the latter is seen to have some enclosure of minute crystals. On account of this fact, special caution was taken to select the sample used in this determination. The results thus obtained are as follows :

$$(1) G \left(\begin{matrix} 2^\circ \\ 4^\circ \end{matrix} \right) = 4.076 \qquad (2) G \left(\begin{matrix} 2^\circ \\ 4^\circ \end{matrix} \right) = 3.915$$

From a large number of specimens collected from Naihyori veins, we could find only one having the distinct crystal faces such as a (100), c (001) and σ (103) shown in Fig. 2. The facial angles of those are as follows :

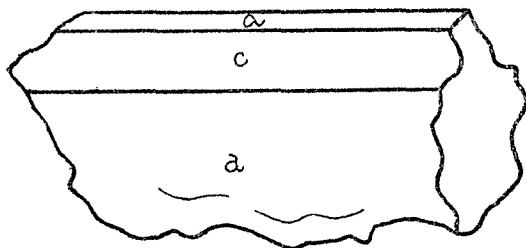


Fig. 2

	Dana
$a \wedge c (= \beta)$	$65^\circ 00' \ 64^\circ 59'$
$c \wedge \sigma$	$22^\circ 06' \ 22^\circ 19'$
$a \wedge \sigma$	$87^\circ 24' \ 87^\circ 18'$

The optical properties of a thin section parallel to (001) made up from this

specimen were determined by using the universal stage microscope. Biaxial negative. Optic plane is in (010). $2V = 51.4^\circ \sim 55^\circ$ $c \wedge x = 57^\circ 01'$. Pleochroism $X =$ nearly colorless to pale brown, $Y =$ brown, $Z =$ pale brown, partly both Y and $Z =$ dark brown. In several other specimens, the central part of crystal shows dark reddish brown, while the outer part, pale brown pleochroism to the direction Z . Moreover, the former shows usually greater index of refraction and smaller index of double refraction than those of the latter. These differences are generally shown in gradual change, but very rarely there exists a distinct boundary between them. We consider that the difference probably comes from the original difference of chemical compositions,

According to the observed intensity of La_1 spectre lines, the content of each element, in the following order, approximately agrees with Harkin's law, 58Ce, 57La, 60Nd, 59Pr, 62Sm, 64Gd, 63Eu.

Chemical composition: In order to determine the chemical composition of this mineral, the molecular ratio of each component was respectively calculated from the analytical results just mentioned above. In this calculation, we have adopted the number 144.68, especially obtained from the weight ratio of oxide to sulphate as the average atomic weight of Ce-group rare earths. Because of the small contents of the Y-group rare earths, their average atomic weight, however, was not determined and we used the mean value 156.8 of the known atomic weights of those elements. The results calculated, concerning the two specimens, are as follows:

1. Bivalent elements: $R^{II}O$ (CaO, MgO, MnO, FeO)

(1) 0.3840	(2) 0.3786
------------	------------
2. Trivalent elements: $R_2^{III}O_3$ (Fe₂O₃, Al₂O₃, Ce₂O₃,
Ce-group and Y-group rare earths.)

(1) 0.2285	(2) 0.2509
------------	------------
3. Tetravalent elements: ThO₂

(1) 0.0022	(2) 0.0019
------------	------------
4. Acidic elements: SiO₂, TiO₂

(1) 0.5662	(2) 0.5586
------------	------------
5. H₂O

(1) 0.0506	(2) 0.0683
------------	------------

Assuming that the component ThO₂ is contained in the form ThSiO₄ (Thorite), we have deducted the value of SiO₂ corresponding to that of ThO₂, from its total values. Thus, the remainder is in the following ratio:



$$\begin{aligned}
 (1) \quad R^{II}O : R_2^{III}O_3 : (Si, Ti)O_2 : H_2O &= 0.3840 : 0.2285 : 0.5640 : 0.0506 \\
 &= 4.07 : 2.42 : 6 : 0.57 \\
 (2) \quad R^{II}O : R_2^{III}O_3 : (Si, Ti)O_2 : H_2O &= 0.3786 : 0.2509 : 0.5567 : 0.0683 \\
 &= 4.08 : 2.70 : 6 : 0.73
 \end{aligned}$$

Experimental formulas of the composition are expressed as follows:

$$\begin{aligned}
 (1) \quad &4.07RO \cdot 2.42R_2O_3 \cdot 6.00(Si, Ti)O_2 \cdot 0.54H_2O \\
 (2) \quad &4.08RO \cdot 2.70R_2O_3 \cdot 6.00(Si, Ti)O_2 \cdot 0.73H_2O
 \end{aligned}$$

In regard to the chemical composition of allanite, several discussions had been hitherto made by chemists and mineralogists, such as A. Michel-Levy, R. Hermann, N. Kockskaroff. N. Engstrom proposed the following two kinds of chemical formulas from the several analytical results: for

fresh allanite as (1) and for somewhat weathered allanite as (2)



P. Groth proposed another form considering it as the basic orthosilicate. $Ca_2(AlOH)(Al, Ca, Fe)(SiO_4)_3$.

In these two formulas, the molecular ratios of respective constituents $R''O$, R_2O_3 , SiO_2 and H_2O are in 4 : 3 : 6 : 1 in the fresh mineral, which is somewhat apart from our results. Calculating the valency values of basic elements, we obtain the following number from our experimental formulas :

$$(1) 2 \times 4.07 + 3 \times 2 \times 2.42 = 22.66$$

$$(2) 2 \times 4.08 + 3 \times 2 \times 2.70 = 24.36$$

These numbers approximately agree with the valency value 24 of acidic radical SiO_4''' as the orthosilicate mineral within the experimental error.

This fact means that there is perfect valency equilibrium between the basic elements and the acidic radicals forming an orthosilicate structure.

We wish to express our hearty thanks to Prof. Tazaki, Mr. S. Kuwabara, and Mr. S. Kobayashi, Hiroshima University, for their help and advice, and also to Mr. S. Oyama, chief manager of the Angaku Mine at the time when we visited there. In this study, we are much obligated to the 66th subcommittee of the Society for Advancement of National Arts and Sciences for valuable financial assistance.