

Swelling and deswelling kinetics of poly(*N*-isopropylacrylamide) gels

Katsunori Takahashi, Toshikazu Takigawa,^{a)} and Toshiro Masuda

Department of Material Chemistry, Kyoto University, Nishikyo-ku, Kyoto 615-8510, Japan

(Received 1 August 2003; accepted 3 November 2003)

Swelling and deswelling kinetics was investigated for three types of cylindrical poly(*N*-isopropylacrylamide) (PNIPA) gels differing in crosslink density. The temperature dependence curves of the volume of the gel specimens were different from one another. One of the gel specimens was considered as a critical gel showing the continuous volume phase transition. The volume change process of the specimens after a temperature jump was examined. In the deswelling processes with temperature jumps to temperatures higher than 35 °C, a phase separation was observed in the gel specimens and the volume change slowed down due to the homogenization after the phase separation. The value of the diffusion constant obtained without the phase separation decreased rapidly as temperature approaches the transition temperature. The rapid decrease for the critical gel indicates the emergence of the critical slowing-down. The value of the critical exponent for the correlation length suggests that the universality class for the volume phase transition of the critical PNIPA gel belongs to the class for the classical theory. © 2004 American Institute of Physics. [DOI: 10.1063/1.1636695]

I. INTRODUCTION

A polymer gel is a three-dimensional polymer network swollen with solvent. The volume of the gel in solvent changes according to the change of an external field, such as temperature and pH. This is because the change of the external field moves the thermodynamic equilibrium state of the gels. The gel in solvent changes the volume by swelling (or deswelling) until a new equilibrium state is achieved. Swelling and deswelling kinetics for polymer gels has been widely studied, and some theoretical approaches to the swelling kinetics has been made.^{1–5} These approaches are based on a kind of linear diffusion equation proposed by Tanaka *et al.*⁶ and are not applicable to large volume change processes. Matsuo *et al.* have studied swelling and deswelling kinetics in large volume change processes using a spherical gel, and proposed that the diffusion constant should be modified by introducing the concentration dependence into the diffusion constant.⁷ However, how to modify the diffusion constant is still unclear.

Poly(*N*-isopropylacrylamide) (PNIPA) gels are well known as typical of thermo-sensitive polymer gels, and show a steep volume change in a narrow temperature range of ~35 °C. When crosslink density of the network is low enough, the PNIPA gel changes the volume discontinuously at a certain temperature around 35 °C. This is called the discontinuous volume phase transition of polymer gels. The degree of discontinuity at the transition temperature decreases with increasing crosslink density, and discontinuity is vanished when the crosslink density becomes high enough. The PNIPA gel at a certain crosslink density shows the continuous volume phase transition, where the slope of volume against temperature diverges at a certain temperature (critical

temperature). This continuous volume phase transition is regarded as the second-order phase transition and the gel showing the continuous transition is called a critical gel. The PNIPA gels having higher crosslink density than the critical gel change the volume continuously against temperature but remains finite over the whole temperature range. This means that no “volume phase transition” occurs for the gels in a thermodynamical sense. For the critical gels, physical quantities such as the correlation length and the specific heat show the critical behavior near the critical temperature.^{8–10} Tanaka *et al.* examined the critical kinetics of the PNIPA (critical) gel to show that the characteristic time of volume change diverges at the critical point.¹¹ On the basis of these studies,^{8–11} the universality class of the volume phase transition was concluded to be identical to that for the three-dimensional (3D) Ising model, but there appears to be no consensus for the universality class.

Recently, it has been shown that the volume phase transition in the course of deswelling (or shrinking) for the PNIPA gels becomes very slow,^{12–17} and the kinetics cannot be described by the conventional theory.^{1–7} This slow kinetics appears to be due to phase separation in the gels. We have also reported⁸ that the characteristic time for the deswelling is of the order of time needed for homogenization of the two phases. To explain the effects of phase separation on the kinetics, Shibayama *et al.* have proposed a mechanism for deswelling process by considering the inherent spatial inhomogeneity of the polymer gels.^{13,14} Suzuki *et al.* have investigated various phenomena observed in the deswelling process such as phase separation, bubble formation and phase coexistence, and they accounted for these phenomena on the basis of the classical phase separation models of nucleation and spinodal decomposition.^{15,16} For further understanding of the origin of the slow kinetics, detailed studies on how the phase separation affects the deswelling kinetics must be still needed.

^{a)}Author to whom correspondence should be addressed. Fax: +81-75-383-2458. Electronic mail: takigawa@rheogate.polym.kyoto-u.ac.jp

In this study, swelling as well as deswelling kinetics was examined for three types of PNIPA gels differing in crosslink density: One specimen shows the discontinuous phase transition and the second one shows a continuous volume change without phase transition, the final one being the critical gel. The effects of phase separation on the kinetics were investigated for various volume change processes induced by temperature jumps, and the kinetics for the three types of gels was compared with one another.

II. EXPERIMENT

Three types of cylindrical PNIPA gels with different crosslink density (coded hereafter as GEL1, GEL2, and GEL3) were prepared in distilled water by radical copolymerization of *N*-isopropylacrylamide (NIPA) as a main constituent and *N*, *N*'-methylene-bis(acrylamide) (BIS) as a crosslink agent. Ammonium peroxodisulfate (AP) and *N*, *N*, *N*', *N*'-tetramethylethylenediamine (TEMED) were used as an initiator and an accelerator, respectively. The monomer concentration (namely, the sum of the concentration of NIPA and BIS) was set to be 10.4 wt%. The molar concentration ratio, [NIPA]/[BIS], was 20, 60, and 80 for GEL1, GEL2, and GEL3, respectively. The pregel solution was poured into glass tubes, in which the gelation was performed at 20 °C for 24 h. Then, the cylindrical PNIPA gels were removed from the glass tubes and immersed into the sufficient amount of distilled water to wash out the unreacted agent. The gels were cut into 15 mm long and used as specimens in measurements. The diameter of the specimens was ~ 500 μm in the equilibrium state at 20.0 °C.

Two types of measurements were employed in this study. One is the measurement in equilibrium (static measurement). The other is the measurement under the volume change (swelling and deswelling) process after a T -jump (dynamic measurement). In both measurements, size and appearances of the gel specimens were observed using a specially designed double-jacket water bath and a microscope equipped with a CCD camera. Temperature of the specimens (T) was controlled by circulating the temperature controlled water in the outer jacket of the water bath. The accuracy in temperature was ± 0.1 °C for the measurements.

First, the static measurement was performed. The T -dependence curve of the diameter of the specimens (d) in the equilibrium state (the state where the diameter does not change with time at a fixed temperature in this experiment) was examined at various T in a T -range of 20 to 80 °C. The measurement was performed on heating (20 °C \rightarrow 80 °C) as well as on cooling (80 °C \rightarrow 20 °C). The T -dependence curve of volume of the specimen (V) was calculated by assuming that the swelling of the gel occurs isotropically; namely, by assuming

$$V \propto d^3. \quad (1)$$

After finishing the static measurement, the dynamic measurement was performed. The T -jump from the initial temperature (T_i) to the final temperature (T_f) was applied to the gel specimens, and the time (t) dependence of d was examined at a constant temperature of T_f until the volume approaches a constant value. In this study, the T -jump was

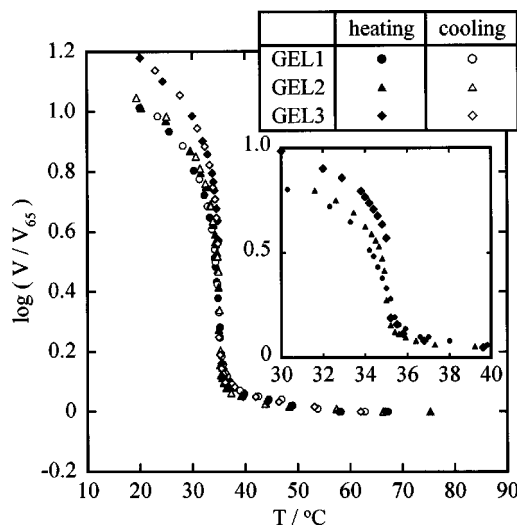


FIG. 1. Temperature (T) dependence of normalized volume V/V_{65} of three types of the PNIPA gels. Here, V_{65} represents V of each gel at 65 °C. The inset shows the enlargement around 35 °C.

applied by transferring the gel specimens kept in water at T_i into the water controlled at T_f , meaning that equilibrium of temperature in the gel specimens occurs very shortly compared with the time scale of this experiment because the volume of water in the bath was ~ 3 cm³ which is large enough compared with that of the specimens.

III. RESULTS AND DISCUSSION

As stated previously in the experimental section, the volume of the gel specimens in thermodynamic equilibrium state at each temperature T was first examined. The volume-temperature (V - T) curves measured on heating as well as on cooling for the three types of gels are shown in Fig. 1. In the equilibrium state, the gels were transparent regardless of temperature for the three gels. The volume used here is a normalized quantity calculated by using the volume of each specimen in the thermodynamic equilibrium state at 65.0 °C (V_{65}). The volume decreases with increasing T , and shows a very steep change around 35 °C for all kinds of specimens. The gels are in the swollen state in the T -range lower than 35 °C, and in the collapsed state at T higher than 35 °C. The inset in Fig. 1 shows the magnified V - T curves on heating around 35 °C. As can be seen from the figure, the gel with the lowest crosslink density (GEL3) changes V discontinuously at 35 °C, evidencing the discontinuous volume phase transition. The gel with the highest crosslink density (GEL1) changes V continuously with T , showing no volume phase transition (of course, the volume change occurs for the gel). The gel with the intermediate crosslink density (GEL2) shows a very steep but continuous volume change around 35 °C, so that we regard hereafter the gel (GEL2) as a critical gel which shows the continuous volume phase transition. The V - T curve for GEL3 shows a hysteresis, which corresponds to 0.2 °C in the transition temperature; namely, the transition occurs at 35.1 °C on heating, while at 34.9 °C on cooling. The transition temperature (T_w) for GEL3 was determined to be 35.0 °C by averaging the two temperatures.

For GEL1 and GEL2, no hysteresis was observed on the V - T curves and even for these gels T_{tr} was determined to be 35.0 °C where the absolute value of slope for the curve holds a maximum.

The dynamic measurement was performed by the T -jump method for the three types of specimens. The values of T_i and T_f are summarized in Table I. The appearance of the gel specimens during the volume change process was different depending on the condition of the T -jump. In the deswelling (shrinking) processes at T_f higher than 35.0 °C, however, the opaqueness was observed for the three gels. The opaqueness must originate from the inhomogeneity of polymer concentration in the whole gel induced by the phase separation¹² and the phase separation temperature lay around 35.0 °C regardless of the gel type. In other cases than the deswelling processes at $T_f > 35$ °C (namely, in the deswelling processes at $T_f < 35.0$ °C or the swelling processes), however, the gels changed V without the phase separation (i.e., with keeping transparency).

For example, the t -dependence curve of d for GEL2 after the T -jump from $T_i = 20.0$ °C to $T_f = 50.0$ °C is shown in Fig. 2. Since this is the deswelling process at $T_f > 35.0$ °C, the gel specimen became opaque after the T -jump. As can be seen from the figure, d decreases steeply just after the T -jump. In this time period, a bamboolike pattern was observed on the surface of the gel specimen. The gel with this large-scale surface pattern was composed of the transparent and opaque regions, the latter corresponding to the node of the bamboo. The node extended in the axial direction with increasing time, and finally the gel became fully opaque at about 30 min after the T -jump. This means that the second filled circle from the left in the figure corresponds to d for fully opaque gel. This large-scale surface pattern was observed only in the deswelling processes at $T_f > 35.0$ °C with relatively large volume change.

The diameter of the opaque region (d_{in}) is also plotted against t in Fig. 2. The value of d_{in} also decreases with t , and the decrease of d_{in} corresponds to the extension of the transparent region from the surface to the center of the gel. As is seen from the figure, at $t = 9.7 \times 10^4$ s d reaches an equilibrium value (d_f) and the opaque region disappears. The opaque gel specimen in a two-phase state, polymer rich and solvent rich phases, shrank with the progress of homogenization and the gel finally recovered the transparency at long time limit.

In order to determine the characteristic time (τ) for the change of d , it is convenient to use two parameters (Δd and Δd_0) defined by the following equations:

$$\Delta d = d - d_f, \quad (2a)$$

$$\Delta d_0 = d_i - d_f. \quad (2b)$$

Here, d_i represents the diameter at T_i . Figure 3 shows a semilogarithmic plot of $\Delta d/\Delta d_0$ against t of the deswelling process after the T -jump from $T_i = 20.0$ °C to $T_f = 50.0$ °C for GEL2. The data here correspond to those in Fig. 2. The slope of the line gives the value of τ of 2.7×10^4 s. As easily understood, τ estimated in this method corresponds to a longest relaxation time for the diameter, or volume, change. In the

short time region of the deswelling, a large-scale surface pattern occurred for this specimen, but the longest relaxation time τ is not affected by the pattern formation because the time domains are quite different. When τ and d_f are determined, we can estimate the diffusion constant (D) by using the following relation for cylindrical gels:¹⁸

$$D = \frac{d_f^2}{24\tau}. \quad (3)$$

The values of D obtained for GEL2, is plotted against T_f in Fig. 4. Figure 4(a) shows the data for $T_f < T_{tr} (= 35.0$ °C), and Fig. 4(b) for $T_f > T_{tr}$. Open and filled symbols represent the data on swelling and deswelling, respectively. The details are summarized in Table I, together with the data for GEL1 and GEL3. It is clear from the figure that D in Fig. 4(b) depends on the total amount of volume change, or a swelling strain (γ_v) defined by

$$\gamma_v = \frac{V_i - V_f}{V_f}. \quad (4)$$

Here, V_i and V_f are the volumes at T_i and T_f , respectively. The diffusion constant D in Fig. 4(a) is independent of γ_v and the T_f -dependence of D on swelling and deswelling appears identical. On the other hand, D on deswelling in Fig. 4(b) appears to decrease with increasing γ_v if comparison is made at a fixed temperature. The data points in Fig. 4(b) can be classified into several categories (four for deswelling and two for swelling) depending on the value of γ_v . Of course, the grouping is an expedient and no clear border between neighboring groups exists. The values of D for the deswelling process where the phase separation was observed are plotted against γ_v in Fig. 5. The values are very small and are almost independent of γ_v at $\gamma_v > 3$ where the large-scale surface pattern was observed. The homogenization after the phase separation requires long time and also moves the time needed for thermodynamic equilibration in dimension to the longer time side compared with that of the volume change process without the phase separation. As a result, the value of D became small. On the other hand, D increases rapidly with decreasing γ_v in the range of $\gamma_v < 2$. The phase separation was also observed in this γ_v -range but the degree of opaqueness was relatively small compared with the case of $\gamma_v > 3$. This may give a shorter time for homogenization of the phase separation, resulting in a larger value of D . As can be seen in Fig. 4, it is clear that the effects of the homogenization after phase separation on the deswelling kinetics become negligible in the small γ_v limit, where D in the deswelling process approaches to that in the swelling process.

The data points for $T_f < T_{tr}$ in Fig. 4(a) appear to fall on a single curve, and the curve shows a steep decrease as T_f approaches T_{tr} , corresponding to the critical slowingdown. Although all data points for $T_f > T_{tr}$ in Fig. 4(b) cannot be approximated by a single curve due to the strong γ_v -dependence of D , the data points marked by open symbols, which correspond to the data on swelling and are therefore free from the effects of the phase separation, might fall on a single curve, just as a mirror image of the curve expected for the data points in Fig. 4(a). In addition, seeing the

TABLE I. Sample code, the final temperature (T_f), the initial temperature (T_i), the diffusion constant (D), and the swelling strain (γ_v) of the dynamic (T -jump) measurements.

| | T_f (°C) | T_i (°C) | D (cm ² s ⁻¹) | γ_v | Symbols in Fig. 7 | Symbols in Fig. 9 | |
|------|------------|------------|--|--------------------|-------------------------|-------------------------|----------------------|
| GEL1 | 8.7 | 20.0 | 7.50×10^{-7} | -0.185 | ○ | | |
| | 15.4 | 26.0 | 4.69×10^{-7} | -0.246 | ○ | | |
| | 19.2 | 27.6 | 5.02×10^{-7} | -0.276 | ○ | | |
| | 27.6 | 33.4 | 2.99×10^{-7} | -0.441 | ○ | ○ | |
| | 33.4 | 34.2 | 1.29×10^{-7} | -0.237 | ○ | ○ | |
| | 33.6 | 34.6 | 1.84×10^{-7} | -0.349 | ○ | ○ | |
| | 34.2 | 34.8 | 6.90×10^{-8} | -0.412 | ○ | ○ | |
| | 35.0 | 37.0 | 3.22×10^{-8} | -0.442 | □ | | |
| | 35.2 | 39.8 | 2.20×10^{-8} | -0.334 | □ | □ | |
| | 35.4 | 39.8 | 1.84×10^{-8} | -0.255 | □ | □ | |
| | 35.6 | 45.0 | 3.19×10^{-8} | -0.192 | □ | □ | |
| | 35.9 | 45.0 | 5.87×10^{-8} | -0.223 | □ | □ | |
| | 37.0 | 45.0 | 3.34×10^{-8} | -0.194 | □ | □ | |
| | 37.0 | 60.0 | 6.83×10^{-8} | -0.096 | □ | □ | |
| | 38.0 | 60.0 | 1.27×10^{-7} | -0.095 | □ | □ | |
| | 39.0 | 60.0 | 8.29×10^{-8} | -0.079 | □ | □ | |
| | 21.4 | 8.0 | 7.09×10^{-7} | 0.346 | ● | ● | |
| | 28.2 | 20.0 | 7.08×10^{-7} | 0.398 | ● | ● | |
| | 28.2 | 20.3 | 4.94×10^{-7} | 0.339 | ● | ● | |
| | 32.0 | 28.2 | 1.96×10^{-7} | 0.553 | ● | ● | |
| | 32.2 | 28.2 | 1.94×10^{-7} | 0.504 | ● | ● | |
| | 33.6 | 32.0 | 1.69×10^{-7} | 0.239 | ● | ● | |
| | 33.6 | 32.2 | 1.47×10^{-7} | 0.215 | ● | ● | |
| | 34.3 | 33.6 | 7.73×10^{-8} | 0.196 | ● | ● | |
| | 34.6 | 33.6 | 5.62×10^{-8} | 0.505 | ● | ● | |
| | 34.8 | 34.3 | 5.10×10^{-8} | 0.268 | ● | ● | |
| | T_f (°C) | T_i (°C) | D (cm ² s ⁻¹) | γ_v | Symbols in Fig. 4(a) | Symbols in Fig. 4(b) | Symbols in Fig. 6 |
| GEL2 | 5.6 | 20.0 | 6.32×10^{-7} | -0.199 | ○ | | |
| | 10.0 | 20.0 | 4.59×10^{-7} | -0.213 | ○ | | |
| | 15.0 | 25.0 | 5.78×10^{-7} | -0.270 | ○ | | |
| | 20.0 | 28.7 | 4.08×10^{-7} | -0.290 | ○ | | ○ |
| | 28.7 | 32.0 | 3.09×10^{-7} | -0.334 | ○ | | ○ |
| | 30.0 | 34.0 | 2.12×10^{-7} | -0.394 | ○ | | ○ |
| | 32.0 | 34.0 | 1.83×10^{-7} | -0.257 | ○ | | ○ |
| | 34.0 | 34.6 | 1.22×10^{-7} | -0.320 | ○ | | ○ |
| | 20.0 | 60.0 | 4.21×10^{-7} | -0.931 | ◇ | | |
| | 34.0 | 37.2 | 7.85×10^{-8} | -0.709 | ◇ | | |
| | 36.1 | 45.0 | 4.17×10^{-8} | -0.088 | | ○ | □ |
| | 38.0 | 60.0 | 5.67×10^{-8} | -0.088 | | ○ | □ |
| | 40.0 | 60.0 | 3.38×10^{-8} | -0.067 | | ○ | □ |
| | 45.0 | 70.0 | 1.39×10^{-7} | -0.036 | | ○ | □ |
| | 35.4 | 40.0 | 1.37×10^{-8} | -0.192 | | △ | □ |
| | 36.4 | 45.0 | 5.56×10^{-8} | -0.103 | | △ | □ |
| | 35.5 | 45.0 | 2.11×10^{-8} | -0.175 | | △ | □ |
| | 35.6 | 45.0 | 2.55×10^{-8} | -0.175 | | △ | □ |
| | 35.9 | 45.0 | 3.24×10^{-8} | -0.119 | | △ | □ |
| | 25.0 | 10.0 | 3.76×10^{-7} | 0.481 | ● | | ● |
| | 28.7 | 20.0 | 3.34×10^{-7} | 0.500 | ● | | ● |
| | 32.2 | 28.7 | 1.65×10^{-7} | 0.403 | ● | | ● |
| | 33.9 | 32.2 | 9.86×10^{-8} | 0.467 | ● | | ● |
| | 34.2 | 33.0 | 9.75×10^{-8} | 0.339 | ● | | ● |
| | 34.4 | 33.0 | 5.36×10^{-8} | 0.548 | ● | | ● |
| | 34.6 | 33.9 | 2.29×10^{-8} | 0.467 | ● | | ● |
| | 45.0 | 43.0 | 1.07×10^{-7} | 0.028 | | ● | |
| | 60.2 | 55.0 | 1.19×10^{-7} | 0.000 ^a | | ● | |
| | 37.0 | 35.9 | 6.55×10^{-8} | 0.037 | | ▲ | |
| | 45.0 | 38.8 | 2.46×10^{-8} | 0.097 | | ▲ | |
| | 45.6 | 41.7 | 1.94×10^{-8} | 0.037 | | ▲ | |
| | 35.9 | 35.1 | 1.40×10^{-8} | 0.210 | | ▼ | |
| | 36.5 | 35.3 | 2.42×10^{-8} | 0.132 | | ▼ | |
| | 38.0 | 35.3 | 7.41×10^{-9} | 0.260 | | ▼ | |
| | 40.0 | 35.3 | 5.28×10^{-9} | 0.456 | | ▼ | |
| | 45.0 | 35.3 | 3.42×10^{-9} | 0.424 | | ▼ | |
| | 45.0 | 35.3 | 3.98×10^{-9} | 0.397 | | ▼ | |
| | 50.0 | 35.5 | 5.52×10^{-9} | 0.700 | | ▼ | |
| | 50.4 | 35.5 | 1.06×10^{-8} | 0.422 | | ▼ | |
| | 60.0 | 35.0 | 4.21×10^{-9} | 0.424 | | ▼ | |
| | 60.2 | 36.0 | 7.38×10^{-9} | 0.256 | | ▼ | |
| | 70.4 | 36.0 | 9.23×10^{-9} | 0.202 | | ▼ | |
| | 40.0 | 20.0 | 7.52×10^{-10} | 10.305 | ◆ | | |
| | 50.0 | 20.0 | 7.36×10^{-10} | 10.665 | ◆ | | |
| | 60.0 | 20.0 | 1.11×10^{-9} | 13.414 | ◆ | | |
| | 60.0 | 30.0 | 1.02×10^{-9} | 6.547 | ◆ | | |
| | 60.0 | 33.0 | 1.14×10^{-9} | 5.985 | ◆ | | |
| | 60.0 | 34.0 | 1.40×10^{-9} | 3.294 | | ◆ | |

TABLE I. (Continued.)

| | T_f (°C) | T_i (°C) | D (cm ² s ⁻¹) | γ_v | Symbols in Fig. 8 | Symbols in Fig. 10 |
|------|------------|------------|--|------------|----------------------|-----------------------|
| GEL3 | 25.4 | 12.0 | 4.27×10^{-7} | 0.310 | ● | ● |
| | 28.8 | 20.2 | 8.57×10^{-7} | 0.456 | ● | ● |
| | 30.0 | 25.4 | 3.10×10^{-7} | 0.434 | ● | ● |
| | 31.9 | 28.8 | 5.21×10^{-7} | 0.816 | ● | ● |
| | 32.9 | 30.0 | 2.10×10^{-7} | 0.352 | ● | ● |
| | 33.4 | 31.9 | 2.85×10^{-7} | 0.377 | ● | ● |
| | 34.3 | 33.4 | 1.19×10^{-7} | 0.344 | ● | ● |
| | 34.6 | 32.9 | 6.15×10^{-8} | 0.953 | ● | ● |
| | 34.8 | 33.4 | 8.24×10^{-8} | 0.559 | ● | ● |
| | 34.8 | 33.4 | 5.18×10^{-8} | 0.953 | ● | ● |
| | 12.0 | 20.2 | 7.43×10^{-7} | -0.170 | ○ | ○ |
| | 20.2 | 28.3 | 3.73×10^{-7} | -0.272 | ○ | ○ |
| | 28.3 | 31.6 | 4.70×10^{-7} | -0.237 | ○ | ○ |
| | 31.6 | 33.0 | 2.36×10^{-7} | -0.173 | ○ | ○ |
| | 33.0 | 34.2 | 2.25×10^{-7} | -0.301 | ○ | ○ |
| | 35.4 | 50.0 | 3.77×10^{-8} | -0.226 | □ | □ |
| | 35.5 | 50.0 | 4.90×10^{-8} | -0.226 | □ | □ |
| | 35.7 | 50.0 | 3.98×10^{-8} | -0.215 | □ | □ |
| | 36.0 | 50.0 | 3.57×10^{-8} | -0.202 | □ | □ |
| | 37.0 | 50.0 | 5.84×10^{-8} | -0.150 | □ | □ |
| | 38.0 | 50.0 | 5.38×10^{-8} | -0.079 | □ | □ |

^aIn this deswelling process, the volume change was too small to detect, but tD was able to be estimated using the relation between τ and the time (t_d) needed for the homogenization after the phase separation ($t_d=3.4\tau$) for the gel.

data on deswelling in $0 < \gamma_v < 0.03$, the data points appear to fall on the same curve as that for the data points for swelling. This means that even for the data on deswelling, D for very small volume changes is little affected by the phase separation. These values of D also seem to converge to zero at T_{tr} , as in the case of Fig. 4(a); namely, the steep decrease of D around T_{tr} originates from the critical slowing-down.

By employing mode-coupling approximation, Onuki¹⁸ has shown that D scales with the correlation length (ξ) as

$$D \sim \frac{1}{\xi^2}, \tag{5a}$$

whereas Tanaka¹⁹ has applied the Kawasaki formula to D : namely

$$D \sim \frac{1}{\xi}. \tag{5b}$$

Introducing a reduced temperature (ϵ) that represents the relative distance from the critical temperature (T_c) by²⁰

$$\epsilon = \frac{|T - T_c|}{T_c}, \tag{6}$$

near T_c , D is related to ϵ by

$$D \sim \epsilon^{2\nu} \tag{7a}$$

or

$$D \sim \epsilon^\nu, \tag{7b}$$

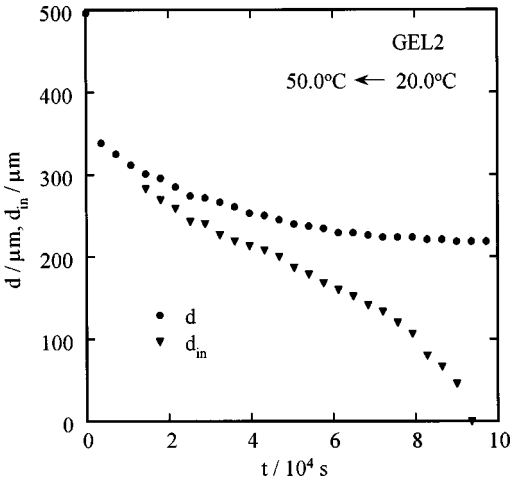


FIG. 2. Time (t) dependence of the diameter of the gel (d) and the diameter of the opaque region (d_{in}) for GEL2. The T jump (from 20.0 °C to 50.0 °C) is applied at $t=0$. At the short times, d was identical to d_{in} , so that the three triangle symbols at $t < 4$ h are eliminated from the figure.

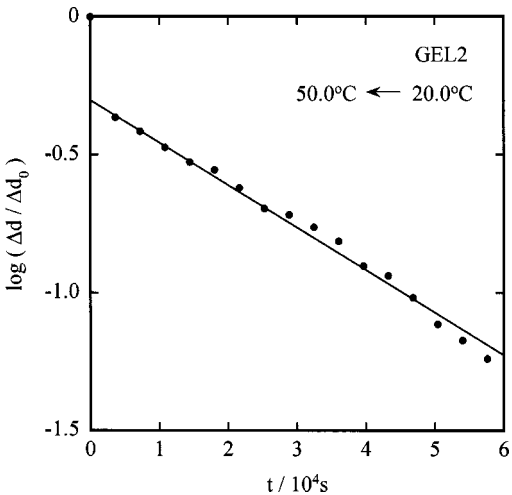


FIG. 3. Normalized volume change $\Delta d/\Delta d_0$ is semilogarithmically plotted against t . The T jump (from 20.0 °C to 50.0 °C) is applied to the GEL2 at $t=0$.

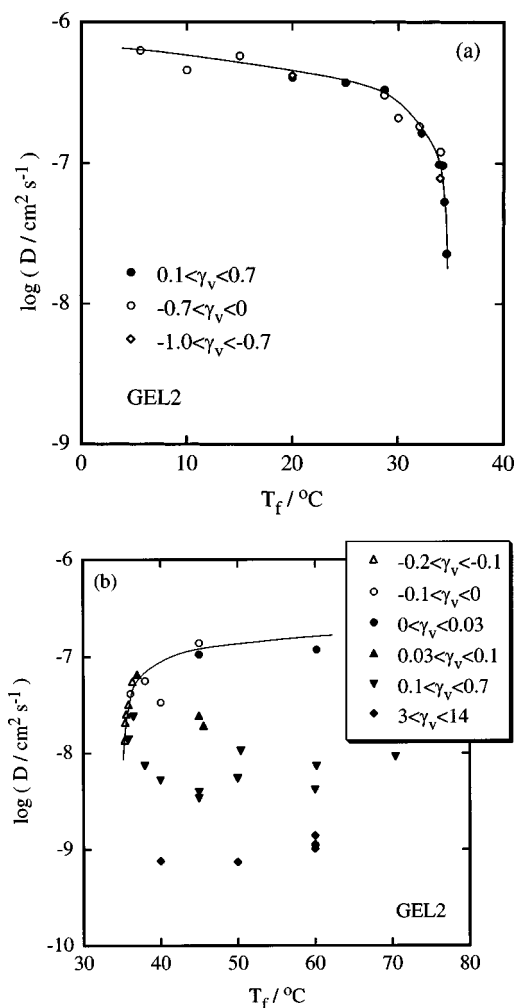


FIG. 4. Diffusion constant (D) for GEL2 is plotted against the final temperature (T_f) for (a) $T_f < 35.0^\circ\text{C}$ and (b) $T_f > 35.0^\circ\text{C}$. The data are classified into several categories depending on the value of swelling strain (γ_v). Open and filled symbols represent data on swelling and deswelling, respectively.

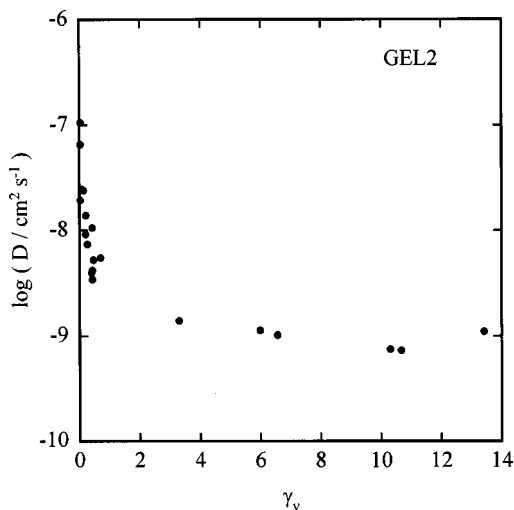


FIG. 5. The γ_v dependence of D for GEL2 for the deswelling process where the phase separation occurs.

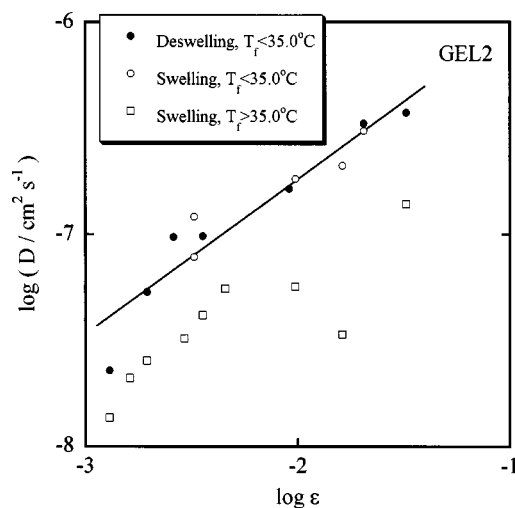


FIG. 6. The diffusion constant D is double-logarithmically plotted against reduced temperature (ϵ) for GEL2. The data plotted are limited to those with $20^\circ\text{C} < T_f < 50^\circ\text{C}$. The solid line is the best fit to the data for $T_f < T_{tr}$.

because $\xi \sim \epsilon^{-\nu}$. Here, ν is the critical exponent for ξ .²⁰ The former scaling law corresponds to the scaling relation proposed by Onuki, the latter corresponding to the Tanaka relation. The critical temperature, T_c , is 35.0°C , T_{tr} for GEL2. Figure 6 shows the semilogarithmic plots of D against ϵ for GEL2. The data shown in Fig. 6 are limited to those in $20^\circ\text{C} < T_f < 50^\circ\text{C}$, and also the data on deswelling with $T_f > T_{tr}$ are eliminated, because D depends strongly on γ_v as shown in Fig. 5. The solid line is the best fit to the data on both swelling and deswelling for $T_f < T_{tr}$.

On the basis of the Onuki relation, the value of ν was determined from the slope to be 0.37 ± 0.03 . This value is smaller than the value either for the 3D Ising model ($\nu \sim 0.63$) or for the mean field value ($\nu = 0.5$),²⁰ but is, if anything, closer to the mean-field value. On the other hand, $\nu = 0.73 \pm 0.05$ for the PNIPA gel based on the Tanaka relation. In this case, the value is closer to the value for the 3D Ising than the mean field prediction. It has been reported that the universality class for the volume phase transition of the critical PNIPA gel belongs to the 3D Ising model.²⁰ Actually, according to the Tanaka relation the universality class of the transition can be considered to belong to the 3D Ising model. When the Onuki relation is valid, however, the universality class may be identical to that of the mean field or classical theory. We think that the critical behavior for the polymer gel should obey the classical theory, because the existence of the polymer network in the gel must suppress the concentration fluctuation as Onuki has stated in Ref. 18; hence, the Onuki relation may be more appropriate for the description of the critical behavior of D . The exponent ν could not be determined for $T_f > T_{tr}$, because the data points are scattered due to the difficulty in measuring small change in d . The value of the slope for the best fit line to the scattered data points for $T_f > T_{tr}$, however, appears to agree with that for $T_f < T_{tr}$.

Figures 7 and 8 show the T_f -dependence of D for GEL1 and GEL3, respectively. Table I contains the detailed data for the gels. The diffusion constant D plotted in these figures are limited for the relatively small volume change processes.

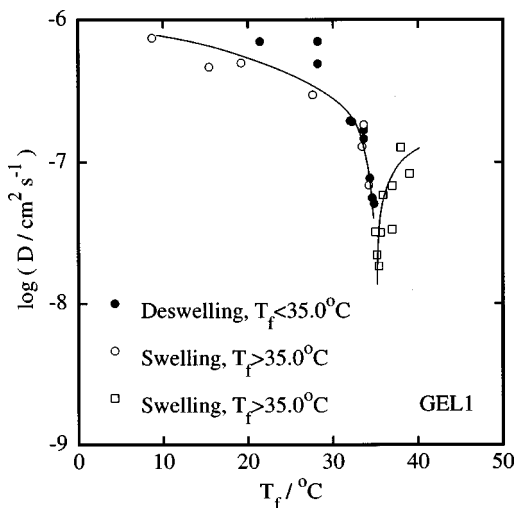


FIG. 7. The diffusion constant D for GEL1 is plotted against T_f . Open and filled symbols represent data on swelling and deswelling, respectively.

The data obtained from the deswelling processes for $T_f > T_{tr}$ was also eliminated, because the effects of homogenization after phase separation exist on the deswelling kinetics. The values of D for both GEL1 and GEL3 decrease rapidly as T_f approaches 35.0 °C, just as observed for GEL2. The T_f -dependence curves of D for the three gels seem to be identical to one another both in shape and magnitude. Theoretically speaking, the values of D for GEL1 and GEL3 do not converge to zero even at the transition temperature T_{tr} ($=35.0$ °C), because the gels are off-critical. GEL1 shows no phase transition, so that the characteristic time τ for volume change does not diverge even at T_{tr} , giving a finite value of D even at the transition temperature. In the case of GEL3 showing the first-order phase transition, τ diverges at the spinodal temperature (T_s), which is slightly different from the transition temperature, and D converges to zero at T_s . This means that the T_f -dependence curve of D for GEL3 must have a cusp at T_{tr} , and D for GEL3 must also have a nonzero value at T_c . In Figs. 9 and 10, D for GEL1 and

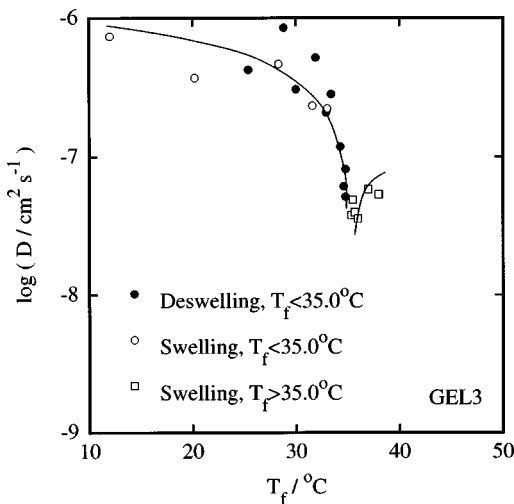


FIG. 8. The diffusion constant D for GEL3 is plotted against T_f . Open and filled symbols represent data on swelling and deswelling, respectively.

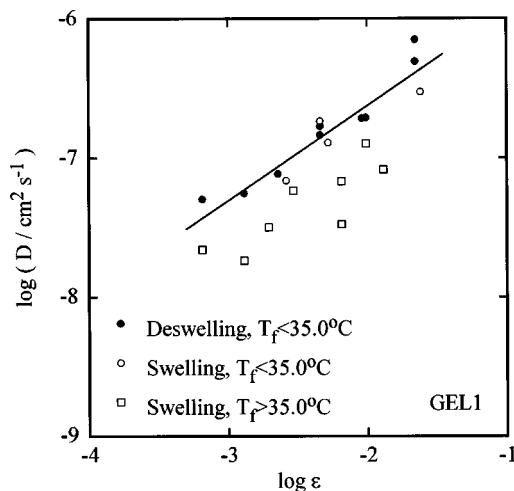


FIG. 9. The diffusion constant D is double-logarithmically plotted against ϵ for GEL1. The data plotted are limited to those with 20.0 °C $< T_f < 50.0$ °C. The solid line is the best fit to the data for $T_f < T_{tr}$.

GEL3 is, respectively, plotted against ϵ . Here, $T_{tr} = T_c$ was assumed. The data plotted are limited to those in 20.0 °C $< T_f < 50.0$ °C. The value of ν obtained from the slope of the best fit line to the data points is 0.34 ± 0.03 both for GEL1 and GEL3 when the Onuki relation is used. This value is almost identical to that for GEL2, resulting from very small values of D at T_c for GEL1 and GEL3, although the theory of the critical phenomena predicts $\nu=0$ for the gels.

IV. CONCLUSION

Swelling and deswelling kinetics was investigated for the three types of the cylindrical PNIPa gels by the T -jump method. In the deswelling processes at $T_f > 35.0$ °C, the phase separation was observed in the gels. The homogenization after the phase separation slowed down the deswelling process, resulting in the small value of D . The value of D obtained without the phase separation decreased rapidly as T_f approached the transition temperature T_{tr} . For the critical gel

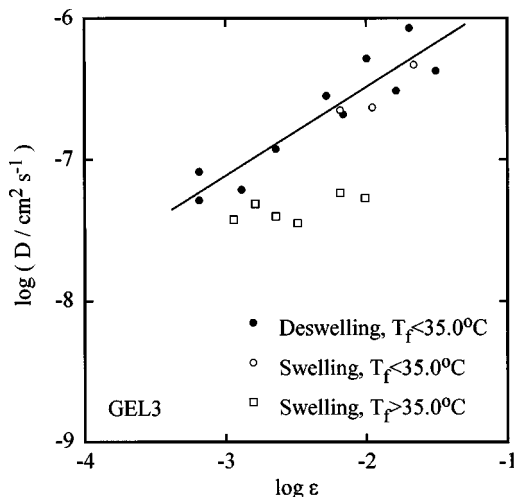


FIG. 10. The diffusion constant D is double-logarithmically plotted against ϵ for GEL3. The data plotted are limited to those with 20.0 °C $< T_f < 50.0$ °C. The solid line is the best fit to the data for $T_f < T_{tr}$.

(GEL2 in this study), this rapid decrease of D near T_{tr} suggests the emergence of the critical slowing-down. The value of the critical exponent ν for GEL2 was determined to be 0.37 ± 0.03 , when a mode-coupling approximation by Onuki was employed. This indicates that the universality class for the volume phase transition of the critical PNIPA gel belongs to the class for the classical theory. According to the theory of the critical phenomena, it can be expected that D for the off-critical gels (GEL1 and GEL3) does not converge to zero at T_c . The T_f -dependence curves of D for off-critical gels were similar in shape with that for the critical gel; namely, the off-critical gels showed pseudo-critical behavior on the D - T_f curves. This means that the bottom of the D - T_f curves for the off-critical gels is very deep.

¹T. Tanaka and D. Fillmore, J. Chem. Phys. **70**, 1214 (1979).

²A. Peters and S. J. Candau, Macromolecules **19**, 1952 (1986).

³A. Peters and S. J. Candau, Macromolecules **21**, 2278 (1988).

⁴Y. Li and T. Tanaka, J. Chem. Phys. **92**, 1365 (1990).

⁵C. Wang, Y. Li, and Z. Hu, Macromolecules **30**, 4727 (1997).

⁶T. Tanaka, L. O. Hocker, and G. B. Benedek, J. Chem. Phys. **59**, 5151 (1973).

⁷E. S. Matsuo and T. Tanaka, J. Chem. Phys. **89**, 1695 (1988).

⁸Y. Li and T. Tanaka, J. Chem. Phys. **90**, 5161 (1989).

⁹M. Tokita and T. Tanaka, Science **253**, 1121 (1991).

¹⁰M. Shibayama, T. Tanaka, and C. C. Han, J. Chem. Phys. **97**, 6829 (1992).

¹¹T. Tanaka, E. Sato, Y. Hirokawa, S. Hirotsu, and J. Peetermans, Phys. Rev. Lett. **55**, 2455 (1985).

¹²T. Takigawa, T. Yamawaki, K. Takahashi, and T. Masuda, Polym. J. (Tokyo, Jpn.) **31**, 595 (1999).

¹³H. Hirose and M. Shibayama, Macromolecules **31**, 5336 (1998).

¹⁴M. Shibayama and K. Nagai, Macromolecules **32**, 7461 (1999).

¹⁵A. Suzuki, S. Yoshikawa, and G. Bai, J. Chem. Phys. **111**, 360 (1999).

¹⁶G. Bai and A. Suzuki, J. Chem. Phys. **111**, 10338 (1999).

¹⁷T. Okajima, I. Harada, K. Nishio, and S. Hirotsu, J. Chem. Phys. **116**, 9068 (2002).

¹⁸A. Onuki, Adv. Polym. Sci. **109**, 63 (1993).

¹⁹T. Tanaka, Phys. Rev. A **17**, 763 (1978).

²⁰H. E. Stanley, *Introduction to phase transitions and critical phenomena* (Clarendon, Oxford, 1971).