

Title	<Preliminary>Structure and Microbial Decolorization of Xylanase-resistant Chromophoric Xylans Isolated from Unbleached Kraft Pulp
Author(s)	MIKAME, Keigo; WATANABE, Takashi; HONDA, Yoichi; KUWAHARA, Masaaki
Citation	Wood research : bulletin of the Wood Research Institute Kyoto University (1995), 82: 28-30
Issue Date	1995-09-30
URL	http://hdl.handle.net/2433/53227
Right	
Type	Departmental Bulletin Paper
Textversion	publisher

Preliminary

Structure and Microbial Decolorization of Xylanase-resistant Chromophoric Xylans Isolated from Unbleached Kraft Pulp*¹

Keigo MIKAME*², Takashi WATANABE*²,
Yoichi HONDA*² and Masaaki KUWAHARA*²

(Received May 31, 1995)

Keywords: kraft pulp, biobleaching, xylan, LCC, lignin peroxidase

One of the most characteristic features of kraft pulp is that uronic acid and arabinose side chains of xylans are cleaved during the cooking process, and the xylans are redeposited on the cellulose fibrils as the alkaline concentration of the cooking liquor decreases^{1,2)}. The redeposited xylans are known to be categorized into two types, (1) xylans extractable with solvents which are associated weakly with cellulose fibrils and resistant to a xylanase-digestion, and (2) alkali-resistant xylans co-crystallizing with cellulose³⁻⁷⁾. In this study, a water-soluble xylanase-resistant chromophoric xylan fraction (LF-D) and a residual lignin fraction (HF-P) were separated from a hard wood unbleached kraft pulp (UKP) by a cellulase/xylanase-membrane bioreactor (Fig. 1). Chemical and spectroscopic analyses revealed that this chromophoric xylanase-resistant fraction (LF-D) contained a large amount of unremovable inorganic atoms including Si, Na and S, together with non-branched β -1, 4-linked xylan chain. Although strong UV absorption was observed in LF-D, a signal originating from methoxyl group of lignin nuclei was below the background noise level in its ¹³C-NMR spectrum. A nucleus exchange reaction of LF-D also revealed that a part of lignin nuclei in LF-D had been demethylated during the course of kraft pulping because LF-D produced a large amount of catechol and pyrogallol in a nucleus exchange reaction at 110°C. A nitrobenzene oxidation of LF-D gave vanillic acid but yields of vanillin and syringaldehyde were very low, suggesting that quinoid structures are involved in LF-D. On the other hand, a higher molecular weight residual lignin fraction (HF-P), which was obtained from an impermeable part of the enzymatic digests, was found to contain much diphenylmethane structure based on the nitrobenzene oxidation and nucleus exchange reaction.

*¹ A part of this work was presented at the 39th Lignin Symposium at Fukuoka, October, 1994, and at the 6th ICBPPI at Vienna, June, 1995.

*² Laboratory of Biomass Conversion.


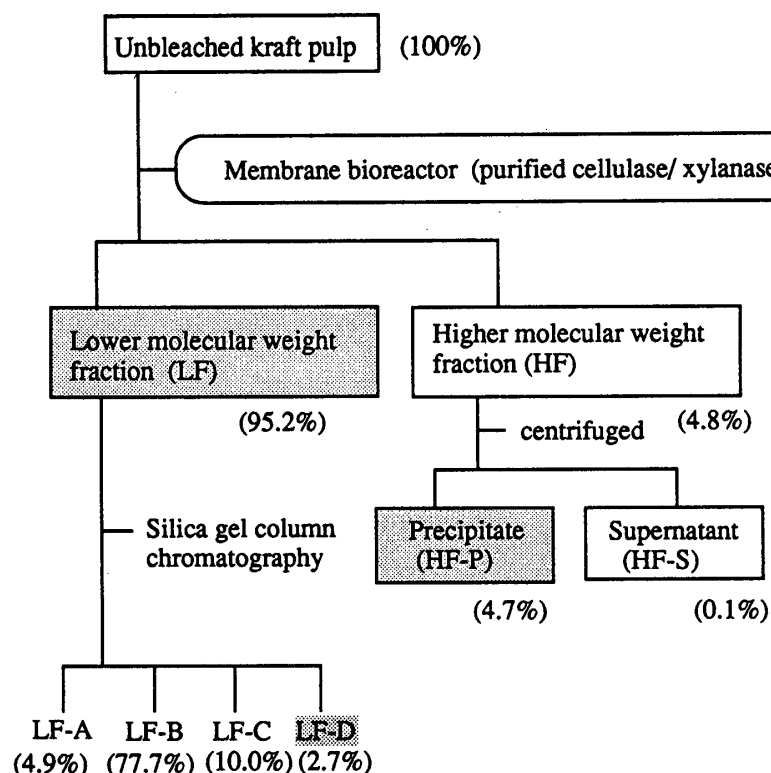


Fig. 1. Enzymatic degradation and fractionation of unbleached kraft pulp.

LF-D was more effectively decolorized by bacterial microflora from soil rather than selected white rot fungi including *Phanerochaete chrysosporium* and *Bjerkandera adusta* which can partly decolorize the original unbleached kraft pulp (UKP). However, *Coriolus versicolor* was found to decolorize not only the UKP but also the isolated xylanase-resistant chromophoric xylan fraction. However, activities of extracellular lignin peroxidase, Mn-peroxidase, laccase and xylanase in the culture filtrates of *C. versicolor* and the bacterial microflora were very low during the cultivation with the chromophoric xylans. In contrast with the oxidizing enzymes, reducing activity of sodium 2, 6-dichlorophenol-indophenol was detected in the cultures of the bacterial microflora. Thus, chromophores of the xylanase-resistant xylans are different from typical residual lignin in UKP, and their biochemical decolorization needs enzymes different from the extracellular ligninolytic enzymes. Although the xylanase-resistant xylans can be removed by D-E-D process from UKP⁴⁾, their microbial decolorization is important for environmentally-safe high yield bleaching⁸⁾.

Because *p*-etherified benzyl ether bonds between lignin and carbohydrates have been considered to be one of the major cause for bleaching resistance of UKP, screening of microorganisms which effectively cleave the benzyl ethers was studied. When a purified lignin peroxidase (H8) from *P. chrysosporium* was reacted with a *p*-ethylated β -O-4 LCC model bearing methyl β -glucoside at its α -position under the condition that veratryl alcohol

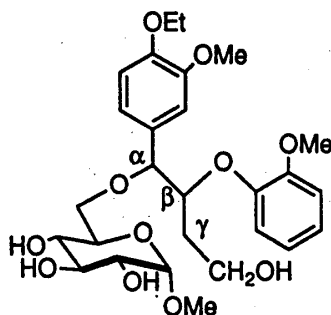

Scheme 1

was oxidized to veratraldehyde, methyl β -glucoside was not detected in the reaction products by HPLC⁹⁾. Therefore, screening of microorganisms which effectively split off the benzyl ether model compound was carried out⁹⁾. As a result, several bacterial single colonies which emit fluorescence during the cultivation were isolated. Extensive studies on the screening and characterization of those benzyl ether-cleaving microorganisms would also contribute to an environmentally safe biobleaching system of UKP.

Acknowledgement

The authors are indebted to Dr. Masamitsu Funaoka, Mie University for the technical advice and discussion on the nucleus exchange reaction. This study was supported by a Grant-in Aid No. 05660189 for Scientific Research from the Ministry of Education, Science and Culture of Japan.

References

- 1) J.K. HAMILTON, E.V. PARTLOW and N.S. THOMPSON: *Tappi*, **41**, 803-811 (1958).
- 2) S. YLLNER and B. ENSTROM: *Svensk Papperstidn.*, **59**, 229-232 (1956).
- 3) F. MORA, K. RUEL, J. COMTAT and J.P. JOSELEAU: *Holzforschung*, **40**, 85-91 (1986).
- 4) S. SKJOLD-JØRGENSEN, N. MUNK and L.S. PEDERSON: "Biotechnology in Pulp and Paper Industry" ed by Kuwahara, M. and Shimada, M., Uni Publishers, Tokyo, 93-99 (1992).
- 5) A. ISHIZU: *Mokuzai Gakkaishi*, **39**, 1335-1340 (1993).
- 6) A. KANTELINEN, B. HORTLING, M. RANUA and L. VIKARI: *Holzforschung*, **47**, 29-35 (1993).
- 7) A. KANTELINEN, B. HORTLING, J. SUNDQUIST, M. LINKO and L. VIKARI: *Holzforschung*, **47**, 318-324 (1993).
- 8) T. WATANABE: *Trends in Glycosci. Glycotechol.*, **7**, 57-68 (1995).
- 9) K. MIKAME, T. WATANABE, Y. HONDA and M. KUWAHARA: *Proc. of 39th Lignin Symp.*, 79-82 (1994).