

理
186 函

学位申請論文

岡部俊夫

本論文

Characteristic Energy Loss Spectra and Optical Constants of
Some Solid Hydrocarbons

Toshio Okabe: J. Phys. Soc. Japan **35**, in press.

参考論文 1

Diffuse Scattering of Electrons by Defect in Crystal.

I. General Formulation and Application to Guinier-Preston
Zone

Toshio Okabe, Katsuhiko Hasebe and Michi-hiko Mannami:
J. Phys. Soc. Japan **27** (1969) 1245.

参考論文 2.

Diffuse Scattering of Electrons by Defect in Crystal.

II. Structure Analysis of the Guinier-Preston Zone in
Cu-Be alloy

Katsuhiko Hasebe, Toshio Okabe and Michi-hiko Mannami:
J. Phys. Soc. Japan **30** (1971) 417.

Characteristic Energy Loss Spectra and Optical Constants
of Some Solid Hydrocarbons

Toshio OKABE

Department of Physics, Faculty of Science,
Kyoto University

Characteristic electron energy loss measurements on some solid hydrocarbons, β -carotene, diphenyl-polyenes and paraffins applying 40 keV electrons are reported. From the energy loss function $-\text{Im}[1/\epsilon(\Delta E)]$ the dielectric constant $\epsilon(\Delta E)$ is calculated by means of a Kramers-Kronig transformation. It is possible to divide the optical properties of these compounds into three spectral regions. The low-lying losses below 8 eV observed in β -carotene and diphenyl-polyenes are interpreted by the single excitation of π -electrons. In the range 8 to 16 eV the excitations of σ -electrons are observed. The electron loss at 21 eV is due to the plasma oscillations of π - and σ -electrons.

§1. Introduction

The electronic structures of organic compounds have been studied by the optical absorption methods in the VUV region up to about 7 eV¹⁾ and recently their excited electronic states in higher energy region have been made clear with the optical reflectivity measurements and also with the characteristic electron energy loss experiments.

The electron energy loss experiments have been widely adopted to investigate the aromatic hydrocarbons and some polymers. Jäger²⁾ interpreted the loss peak at about 6 eV in the energy loss spectra of the aromatic hydrocarbons as a hybrid resonance effected both by single π -electron excitations and collective interactions, while Otto and coworkers^{3~5)} identified the loss as a π - π^* single-electron transition in comparison with optical absorption measurements. In polystyrene the existence of the collective effect at about 7 eV was confirmed in terms of the energy dependent dielectric constant derived from the energy loss spectra,⁶⁾ which was supported later in the optical reflectivity measurements.⁷⁾

In the case of long chain compounds, the investigations have been carried optically only in the low energy region. Much attentions have been paid on the convergence of the wavelength of optical absorption maxima observed in this region for polyenes and asymmetric cyanines as the number of carbon atoms increased and this has been interpreted in terms of the single excitation of π -electrons.⁸⁾

This paper reports the characteristic electron energy loss

spectra of some long chain hydrocarbons having carbon conjugated double bonds; β -carotene, diphenyl-polyenes and those of normal paraffins. Then the loss spectra are transformed into the optical constants by applying the Kramers-Kronig dispersion relation. From both the electron loss spectra and the optical constants the excitations of π - and σ -electrons are discussed.

§2. Experimental

Specimen films were prepared from β -carotene $C_{40}H_{56}$, diphenyl-polyenes $C_6H_5(-CH=CH-)_n C_6H_5$ for $n=2, 3, 4$ and 26-, 36-normal-paraffins. Diphenyl-polyenes and paraffins were vacuum evaporated onto mica, then the thin films were floated on the water and scooped with copper mesh. Another technique was used for β -carotene; the benzene solution of about one per cent by weight was dropped on the water by glass squirt to form thin film and the film was scooped with the mesh for specimen holder. This procedure was done in argon atmosphere in the dark box to prevent the oxidization of β -carotene. To examine the change of specimens during the preparation of thin films, the optical absorptions of thin films dissolved in organic solutions were measured. It was found that the specimen chemical structures were unchanged during the preparations of thin films.

The energy loss spectra were obtained by the Möllenstedt type energy analyzer attached to an electron microscope. The incident electron energy was 40 keV and the energy resolution of the analyzer was about 1 eV. The energy analysis was made by forming the electron microscope image with the objective aperture which accepted

the electrons scattered in the angle less than 3 mrad. The energy spectra were recorded on the photographic plates and the intensity was measured by the microphotometry. Energy calibration was made by employing the plasma loss of aluminum for 15.0 eV, and the linearity check of the energy scale was made following the procedure by Swanson and Powell.⁹⁾

Also the optical absorption spectra of the solid films of the materials evaporated onto mica or quartz were measured in the low energy region below 6 eV in order to compare with the optical constants derived from the energy loss spectra.

§3. Results

Some of the observed electron energy loss spectra are shown in Fig. 1 and the loss values are tabulated in Table I. Also the errors of the loss values are estimated in Table I. The accuracy of the profiles of the loss spectra are observed better than 10 % for each energy values. The electron loss spectra of the compounds studied show a similar profile in the energy region higher than about 8 eV; a very broad peak at about 21 eV and a shoulder or a peak at about 10 eV. Carotene and diphenyl-polyenes, which have carbon conjugated double bonds, show peaks at lower energy region; a peak at 3 eV for β -carotene and two peaks at 4 eV and 7 eV for diphenyl-polyenes. However, paraffins which have only carbon linear single chains indicate no remarkable peak in this energy region.

The observed loss spectra can be correlated with the optical properties. The differential cross section of the incoming electrons for the transfer of momentum $\hbar k$ (scattering angle θ) and

energy $\hbar\omega = \Delta E$ into the solid angle $d\Omega$ is proportional to the imaginary part of the inverse dielectric constant (the loss function) as¹⁰⁾

$$\frac{d^2\sigma}{d(\hbar\omega)d\Omega} = \frac{1}{2\pi^2 a_0 n E_0} \frac{1}{\theta^2 + (\hbar\omega/2E_0)^2} \text{Im} \frac{-1}{\epsilon(\mathbf{k}, \omega)} \quad (1)$$

where E_0 is the energy of the incident electrons, a_0 is Bohr radius and n is the number of electrons per volume participating in the process. In the present experimental conditions the observed loss spectra were correlated to be proportional to the cross section integrated over the scattering angle as

$$\begin{aligned} \frac{d\sigma}{d(\hbar\omega)} &= \frac{1}{2\pi^2 a_0 n E_0} \int_0^{\theta_L} \frac{1}{\theta^2 + (\hbar\omega/2E_0)^2} d\Omega \text{Im} \frac{-1}{\epsilon(\omega)} \\ &= \frac{1}{2\pi a_0 n E_0} \log\left\{1 + \left(\frac{2E_0 \theta_L}{\hbar\omega}\right)^2\right\} \text{Im} \frac{-1}{\epsilon(\omega)} \end{aligned} \quad (2)$$

where θ_L (the maximum angle of the scattered electrons captured by the objective aperture into the loss spectrum) is 3 mrad. Moreover, for the loss function there exists the f-sum rule;

$$\int_0^\infty \omega \text{Im} \frac{-1}{\epsilon(\omega)} d\omega = \frac{2\pi^2 e^2 N}{m} n_0 \quad (3)$$

where N is the density of atoms (or molecules) in the material, n_0 is the number of electrons per atom (molecule); $Nn_0 = n$, and m is the free electron mass. Then the observed loss spectra give the loss function $-\text{Im}[1/\epsilon(\omega)]$ according to eqs. (2) and (3). The real part of $1/\epsilon(\omega)$ are derived by employing the Kramers-Kronig dispersion integration as¹¹⁾

$$\text{Re} \frac{1}{\epsilon(\omega)} = 1 + \frac{2}{\pi} P \int_0^\infty \frac{\omega' \text{Im}[1/\epsilon(\omega')]}{\omega'^2 - \omega^2} d\omega' \quad (4)$$

where P indicates the principal-part integral. The integration was computed numerically over the energy range 0~45 eV dividing 0.1 eV width. For the integration the energy loss spectra were corrected as shown by dashed lines in Fig. 1 to avoid the effects on no-loss electrons and those of multiple scattering above 30 eV. Also in the present work to normalize the loss function the value n_0 was chosen so that the one of the resultant dielectric constants ϵ_2 agree qualitatively with the optical absorption measurements in the range below 6 eV (Fig. 3). It was found that the agreement between the calculated values and the optical measurements is good in the case when only carbon atoms should participate in the interaction. Some of these optical constants ϵ_1 , ϵ_2 and $-\text{Im}(1/\epsilon)$ are shown in Fig. 2. The behaviors of the imaginary parts of the dielectric constants correspond well with their energy loss spectra or their loss functions in the region below 8 eV and the peaks of ϵ_2 at approximately 10 eV correspond to the shoulders in the electron loss spectra. The imaginary parts of the dielectric constants show peaks in the low energy region for β -carotene and diphenyl-polyenes. On the other hand there is no peak for paraffins in this region.

§4. Discussion

The low-lying electron energy loss peaks of β -carotene at 3.0 eV and diphenyl-polyenes at 4 eV can be corresponded to the optical absorption peaks arising from the single excitation of π -electrons.⁸ The dielectric constants ϵ_2 derived here have peaks at 2.7 eV for β -carotene and 3.6 eV for diphenyl-hexatriene, whose values are in good agreement with the optical absorption measurements of these solid films as 2.77 eV and 3.83 eV respectively (Fig. 3). The

interpretation of these losses from the standpoint of the collective excitations of π -electrons¹³⁾ cannot be accepted since the dielectric constants ϵ_1 and ϵ_2 are too large to satisfy the condition for the excitation of plasma oscillations; $\epsilon \neq 0$. It seems that the only example in which the plasma oscillation of π -electrons has been established is the 7 eV loss of graphite.^{14,15)}

Two peaks observed between 8 to 16 eV on the curves of ϵ_2 in Fig. 2 may be ascribed to the excitations σ -electrons; (CH)-(CH)* excitations and σ - σ^* excitations involving the C-C bonds. The lower peaks in this energy region give approximately the same energy values through the series. The location of the higher peaks, however, moves upwards in energy as the distance of C-C bonds decreases. Therefore we expect the σ - σ^* excitations to lie at higher energy than (CH)-(CH)* excitations. Honig¹⁶⁾ showed that the ionization potentials (the highest occupied levels) of σ -electrons were observed from propane to decane as 11.21 eV to 10.19 eV, which are consistent with the present experiment.

In the region above 16 eV the dielectric constants ϵ_1 and ϵ_2 are monotonously increasing and decreasing respectively similar to the Drude's formula for the free electron gas. Therefore we may expect the free electron like behavior of the systems in this region. So the broad peaks at 21 eV in the loss functions can be interpreted as those due to the excitations of plasmon as in the case of metals. In fact the behaviors of the dielectric constants in this region confirm this mode of excitations where ϵ_1 and ϵ_2 are small. In graphite the loss at 25 eV are assigned as plasma loss of the π + σ -electrons (4 per atoms).¹⁴⁾ However, the loss values in the present work do not coincide well with the values calculated from

the free-electron model according to $\hbar\omega_p = \hbar\sqrt{4\pi Nn_0 e^2/m}$. These values are shown in Table II. The observed loss values are in the second column. The values in the third and the fourth columns are calculated ones which count all the valence electrons and do only the valence electrons of carbons as n_0 respectively. The observed energies of plasma oscillations are higher than the calculated ones. It is known that the displacement of the plasma frequency to higher values is caused by a low-lying interband transitions.¹⁷⁾ Therefore the shift is ascribed to the interband transitions of σ -electrons in the range 8 to 16 eV and also this has been observed in the aromatic hydrocarbons.²⁾

The losses at 7 eV in the electron energy loss spectra which correspond to 6.1 eV peaks in ϵ_2 are observed only in diphenylpolyenes. The UV absorption spectra of benzene and its derivatives have been extensively measured and an intense absorption peak observed in the vicinity of 6 eV has been ascribed to π - π^* single electron excitation of the benzene ring π -electrons.^{18,19)} Therefore these losses can be interpreted as the excitation of π -electrons on the benzene rings at both ends of the carbon chains.

In the present electron loss experiments we only utilized the relative cross sections. Therefore to get the loss function $-\text{Im}(1/\epsilon)$ it was necessary to normalize the observed energy spectrum according to eq. (3). The profile of the dielectric constants obtained by employing the Kramers-Kronig relation is very sensitive to the choice of the value n_0 . Only in the case that we used the number of electrons of carbon atoms without hydrogen atoms the derived ϵ_2 were in good agreement with the one from the optical absorption measurements. The same situation has been recognized

for polystyrene in the works of Lavilla and Mendlowitz.⁶⁾ The reason why only carbon atoms should participate in the excitations, however, has not been yet understood. Another method for the normalization of the loss function employed by Creuzburg,²⁰⁾ where the measurements of the thickness of the specimen films are used for this purpose, will be useful for the comparison with the present work. Furthermore it is necessary to compare the calculated dielectric constants from the electron energy loss spectrum with the optical measurements over the wide energy region.

Acknowledgements

The author wishes to express his sincere thanks to Prof. Mannami for his encouragement and useful discussions during the course of this study. Thanks are also due to Dr. Yamashita for the Guidance to write the computer program for the K-K dispersion integration and to Dr. Taniguchi for the optical measurements.

References

- 1) UV-Atlas Organischer Verbindungen (Butterworth, Verlag Chemie, 1966).
- 2) J. Jäger: Ann. Phys. (Germany) **22** (1969) 147.
- 3) S. Kunstreich and A. Otto: Optics Commun. **1** (1969) 45.
- 4) E. E. Koch and A. Otto: Optics Commun. **1** (1969) 47.
- 5) E. E. Koch, S. Kunstreich and A. Otto: Optics Commun. **2** (1971) 365.
- 6) R. E. Lavilla and H. Mendlowitz: J. Phys. Radium **25** (1964) 114.
- 7) J. G. Carter, T. M. Jelinek, R. N. Hamm and R. D. Birkhoff: J. chem. Phys. **44** (1966) 2266.
- 8) O. W. Adams and R. L. Miller: Theoret. chim. Acta **12** (1968) 151.
- 9) N. Swanson and C. J. Powell: J. chem. Phys. **39** (1963) 630.
- 10) P. Nozières and D. Pines: Phys. Rev. **113** (1959) 1254.
- 11) D. Pines: Elementary Excitations in Solids (Benjamin, New York, 1964) Chap. 3, p. 134.
- 12) H. H. Jaffe and M. Orchin: Theory and Application of Ultraviolet Spectroscopy (John Wiley, New York, 1962) Chap. 11, p. 220
- 13) G. Araki and T. Murai: Prog. theor. Phys. **8** (1952) 639;
T. Murai: Prog. theor. Phys. **27** (1962) 899.
- 14) E. A. Taft and H. R. Philipp: Phys. Rev. **138** (1965) A197.
- 15) K. Zeppenfeld: Z. Phys. **211** (1968) 391.
- 16) R. E. Honig: J. chem. Phys. **16** (1948) 105.
- 17) H. Raether: Springer Tracts in Modern Physics ed. G. Hohler (Springer, Berlin, 1965) Vol. 38. p. 94.
- 18) V. J. Hammond et al.: Discussions Faraday Soc. **9** (1950) 53.
- 19) S. Onari: J. Phys. Soc. Japan **26** (1969) 500.
- 20) M. Kreuzburg: Z. Phys. **196** (1966) 423

Figure Captions

- Fig. 1. Characteristic energy loss spectra. a) β -carotene; b) diphenyl-hexatriene; c) 26-n-paraffin. The dotted curves indicate the profiles of the major energy loss.
- Fig. 2. Dielectric constants ϵ_1 , ϵ_2 and the energy loss functions $-\text{Im}(1/\epsilon)$ of a) β -carotene, b) diphenyl-hexatriene and c) 26-n-paraffin obtained by Kramers-Kronig analysis of the corrected curves (dashed lines) in Fig. 1.
- Fig. 3. Optical absorption spectra of solid hydrocarbons. a) β -carotene, dried on LiF from the chloroform solution (solid line); b) diphenyl-hexatriene, vacuum evaporated on quartz (solid line). The dashed lines are the spectra of the chloroform solutions of the materials.

Table I. Characteristic energy loss values (in eV).

substance	loss values (in eV)			
β -carotene	3.0 \pm 0.2		10.5 \pm 0.2	20.6 \pm 0.4
Diphenyl-butadiene	4.1 \pm 0.1	7.0 \pm 0.1	11.1 \pm 0.2	21.0 \pm 0.5
Diphenyl-hexatriene	3.9 \pm 0.1	7.0 \pm 0.1	11.0 \pm 0.2	21.4 \pm 0.2
Diphenyl-octatetraene	3.7 \pm 0.1	6.5 \pm 0.1	10.4 \pm 0.1	20.5 \pm 0.2
26-n-paraffin			9.8 \pm 0.2	20.2 \pm 0.4
36-n-paraffin			9.6 \pm 0.2	20.4 \pm 0.5

Table II. Free electron plasmon energy $\hbar\omega_{p \text{ cal}}$ compared with the observed $\hbar\omega_{p \text{ obs}}$ (in eV).

substance	$\hbar\omega_{p \text{ obs}}$	$\hbar\omega_{p \text{ cal}}^*$	$\hbar\omega_{p \text{ cal}}^{**}$
β -carotene	20.6 \pm 0.4	18.2	15.7
Diphenyl-butadiene	21.0 \pm 0.5	17.4	15.8
Diphenyl-hexatriene	21.4 \pm 0.2	17.6	16.0
Diphenyl-octatetraene	20.5 \pm 0.2	17.7	16.0
26-n-paraffin	20.2 \pm 0.4	18.8	15.2
36-n-paraffin	20.4 \pm 0.5	18.8	15.3

* All valence electrons are taken into account to participate the excitation of plasmon.

** Only the valence electrons of carbon atoms are taken into account on this excitation.

FIG. 1 a)

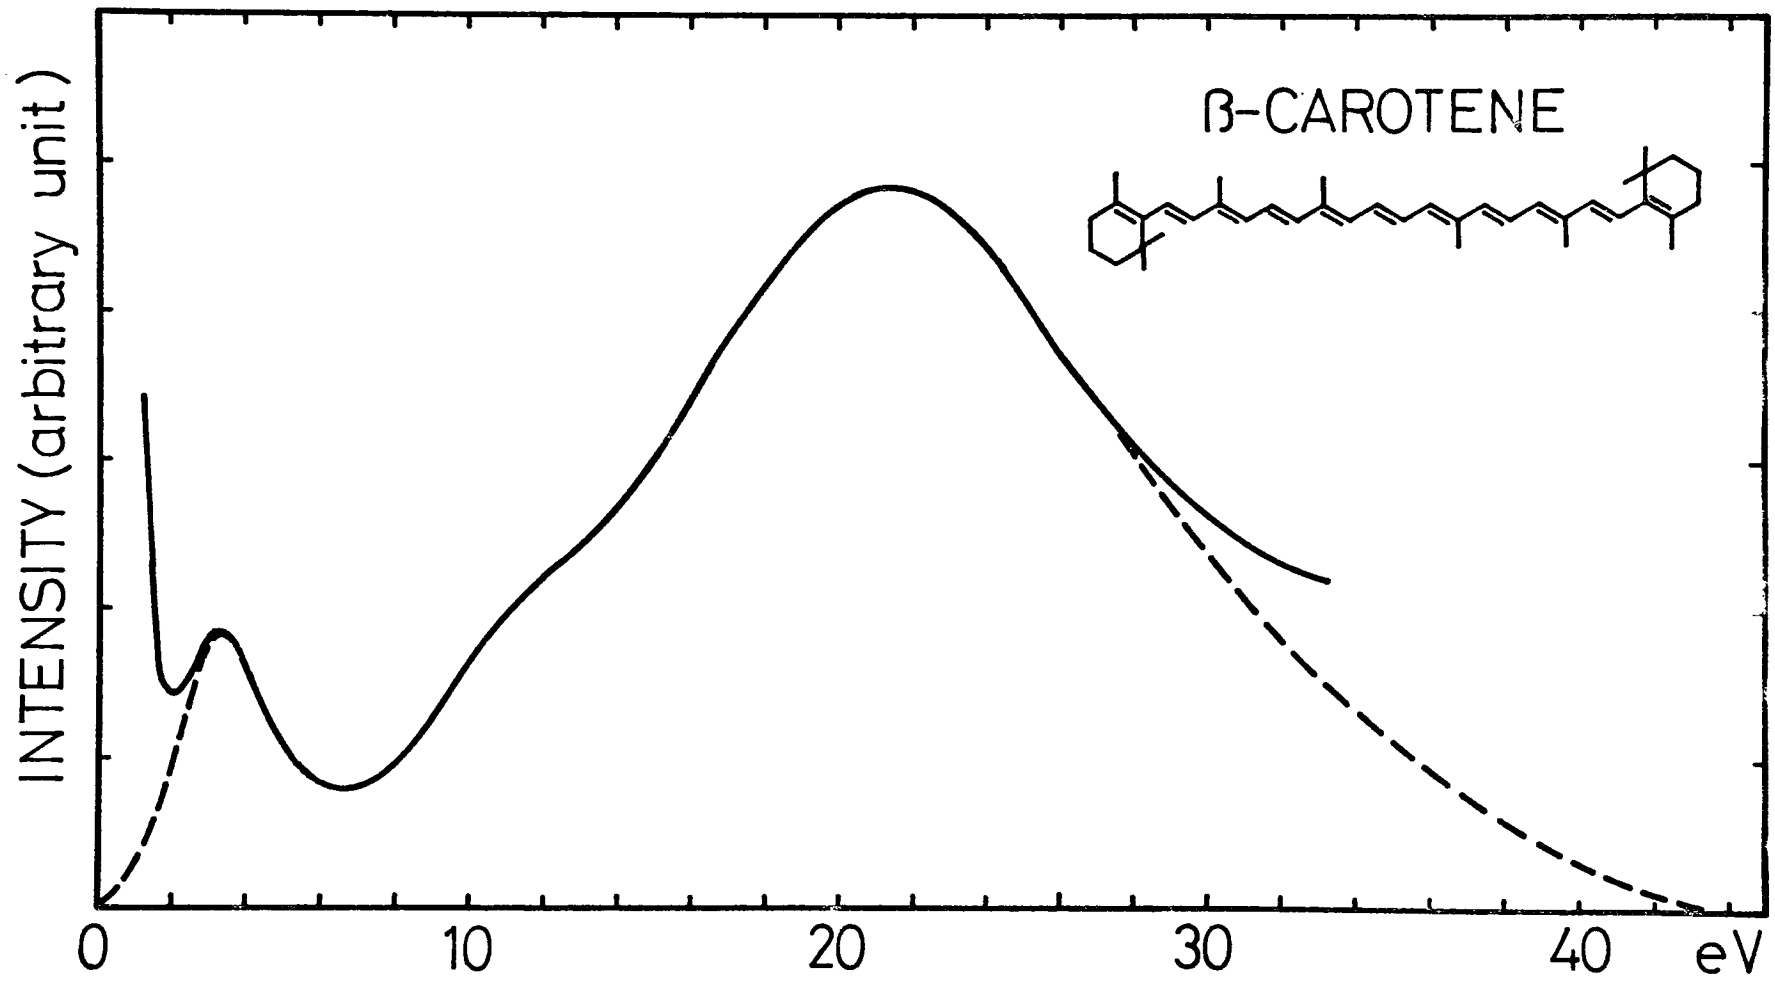


FIG. 1 b)

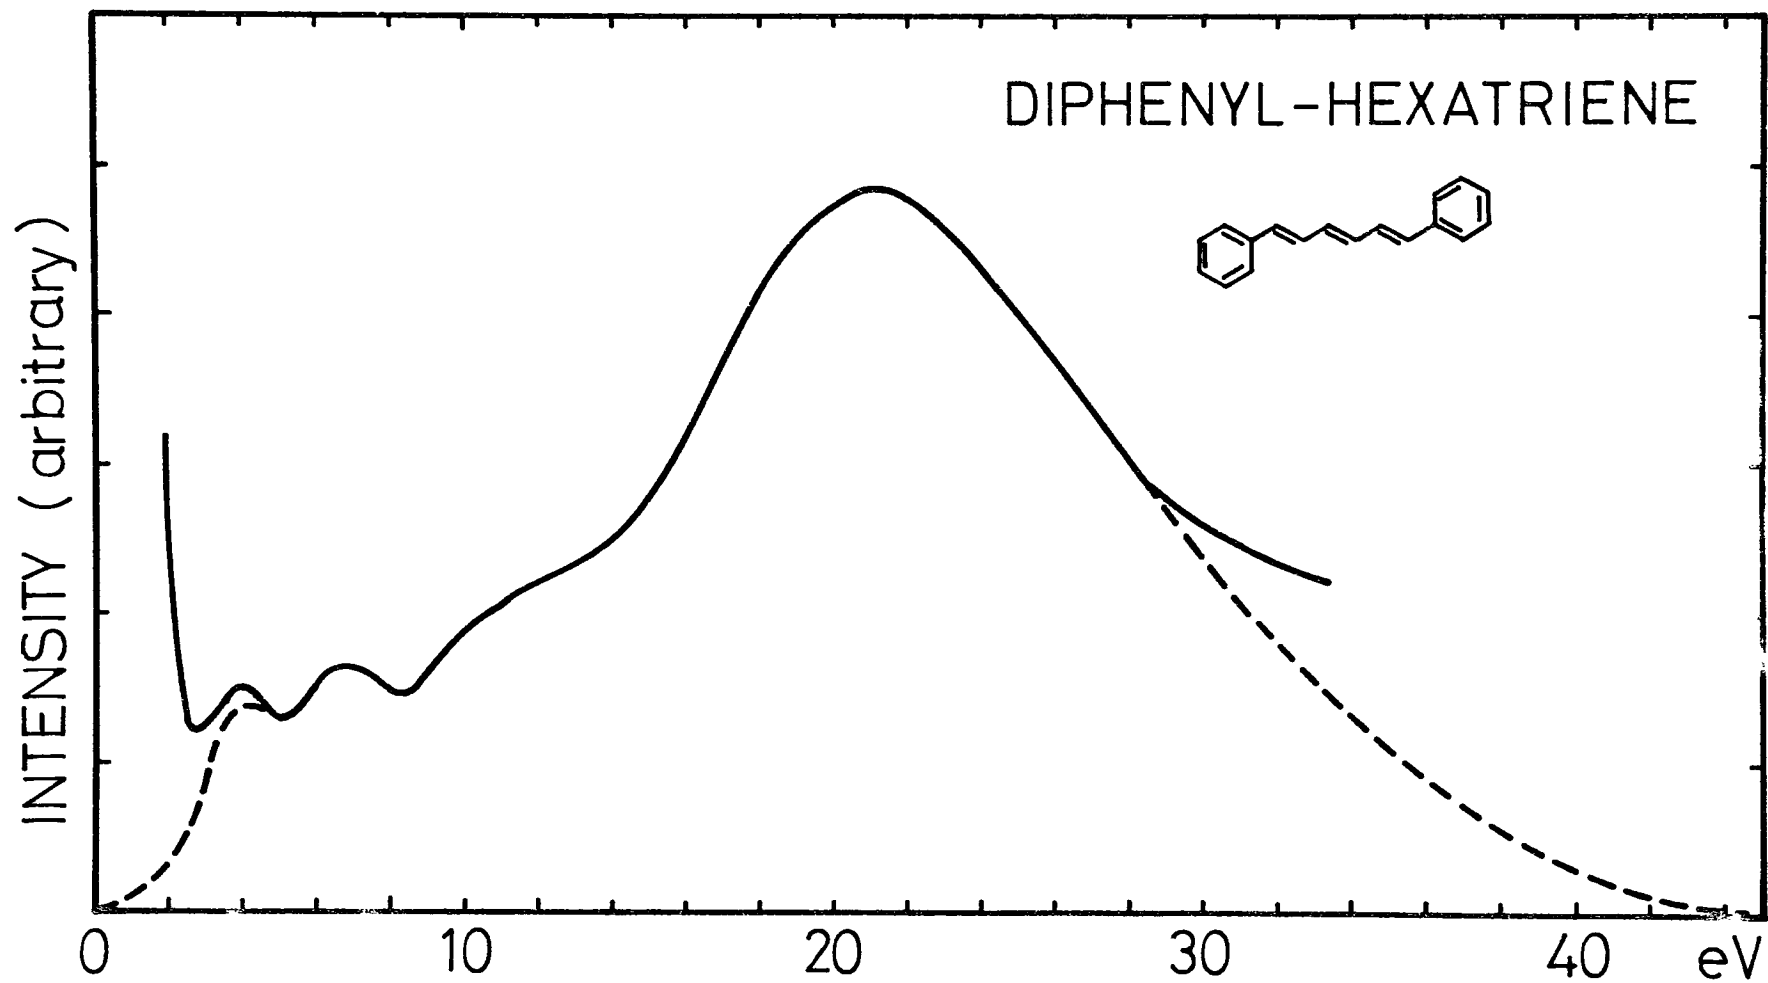


FIG. 1 c)

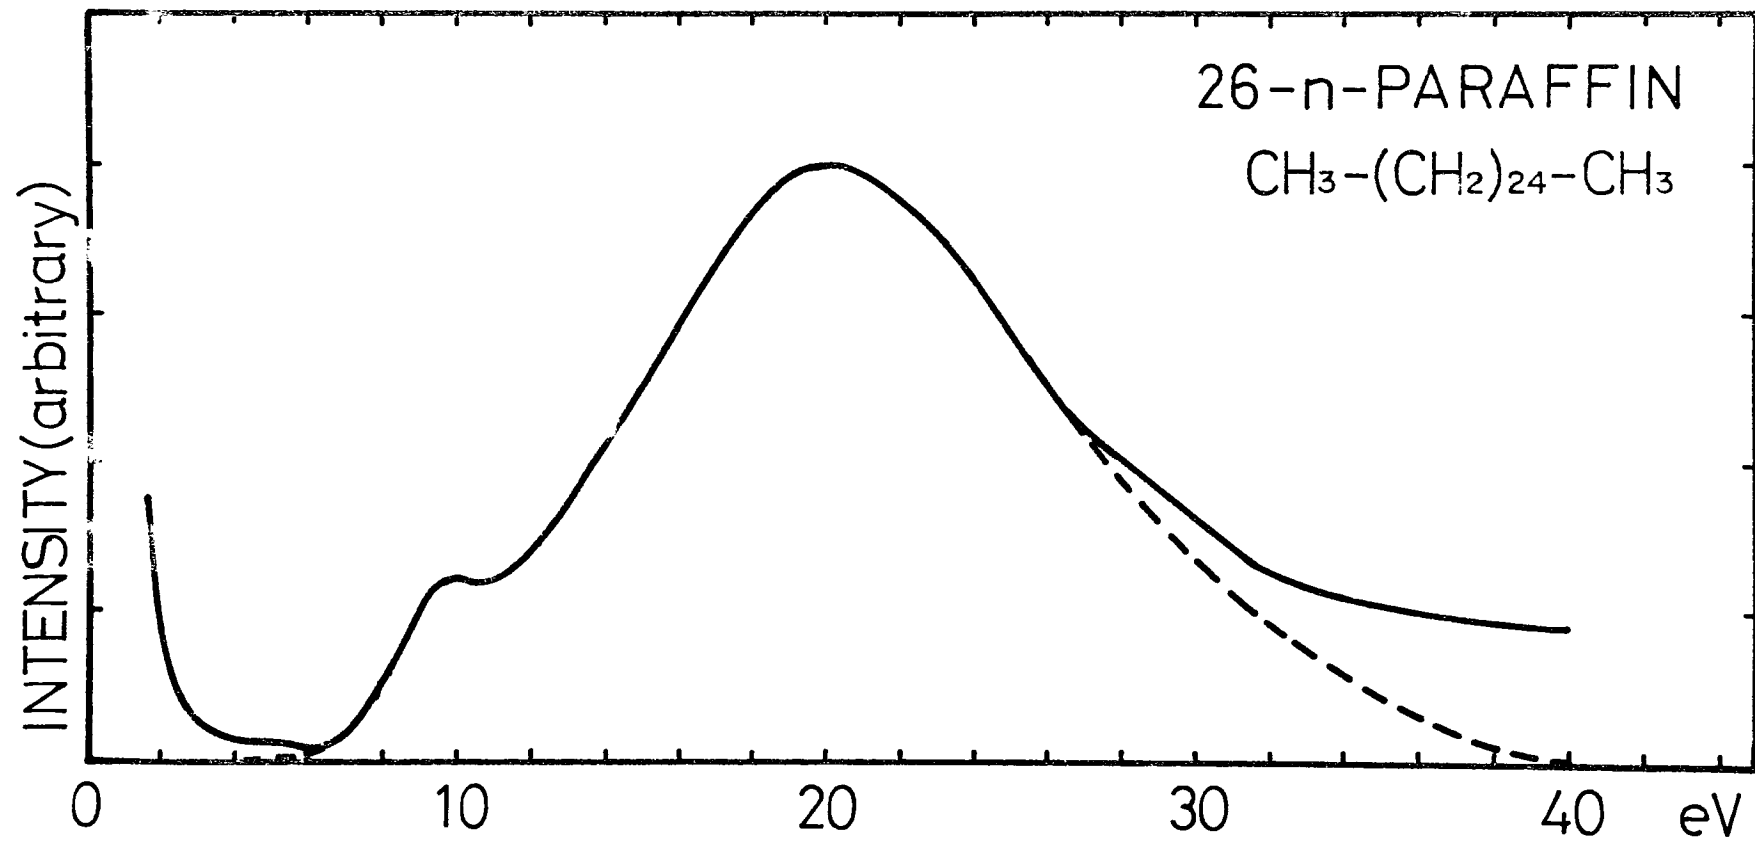


FIG. 2 a)

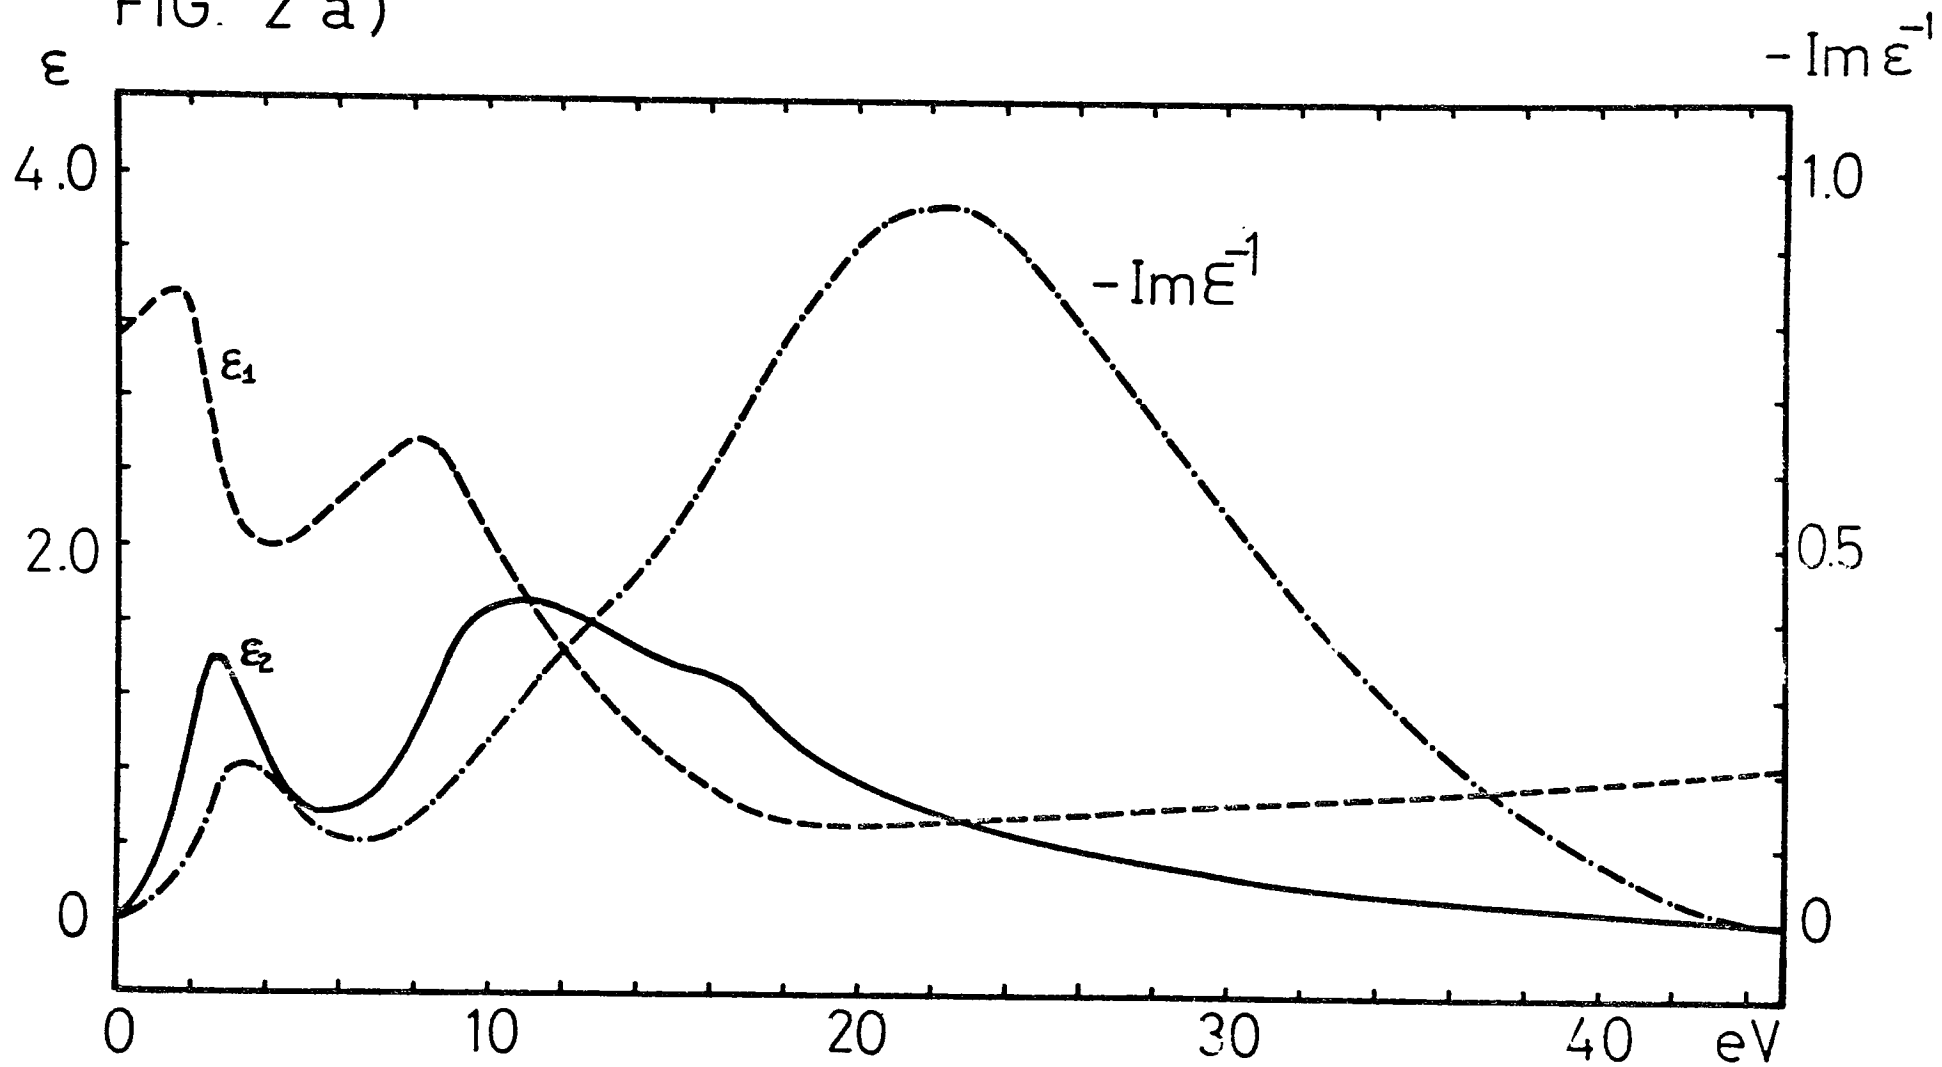


FIG. 2 b)

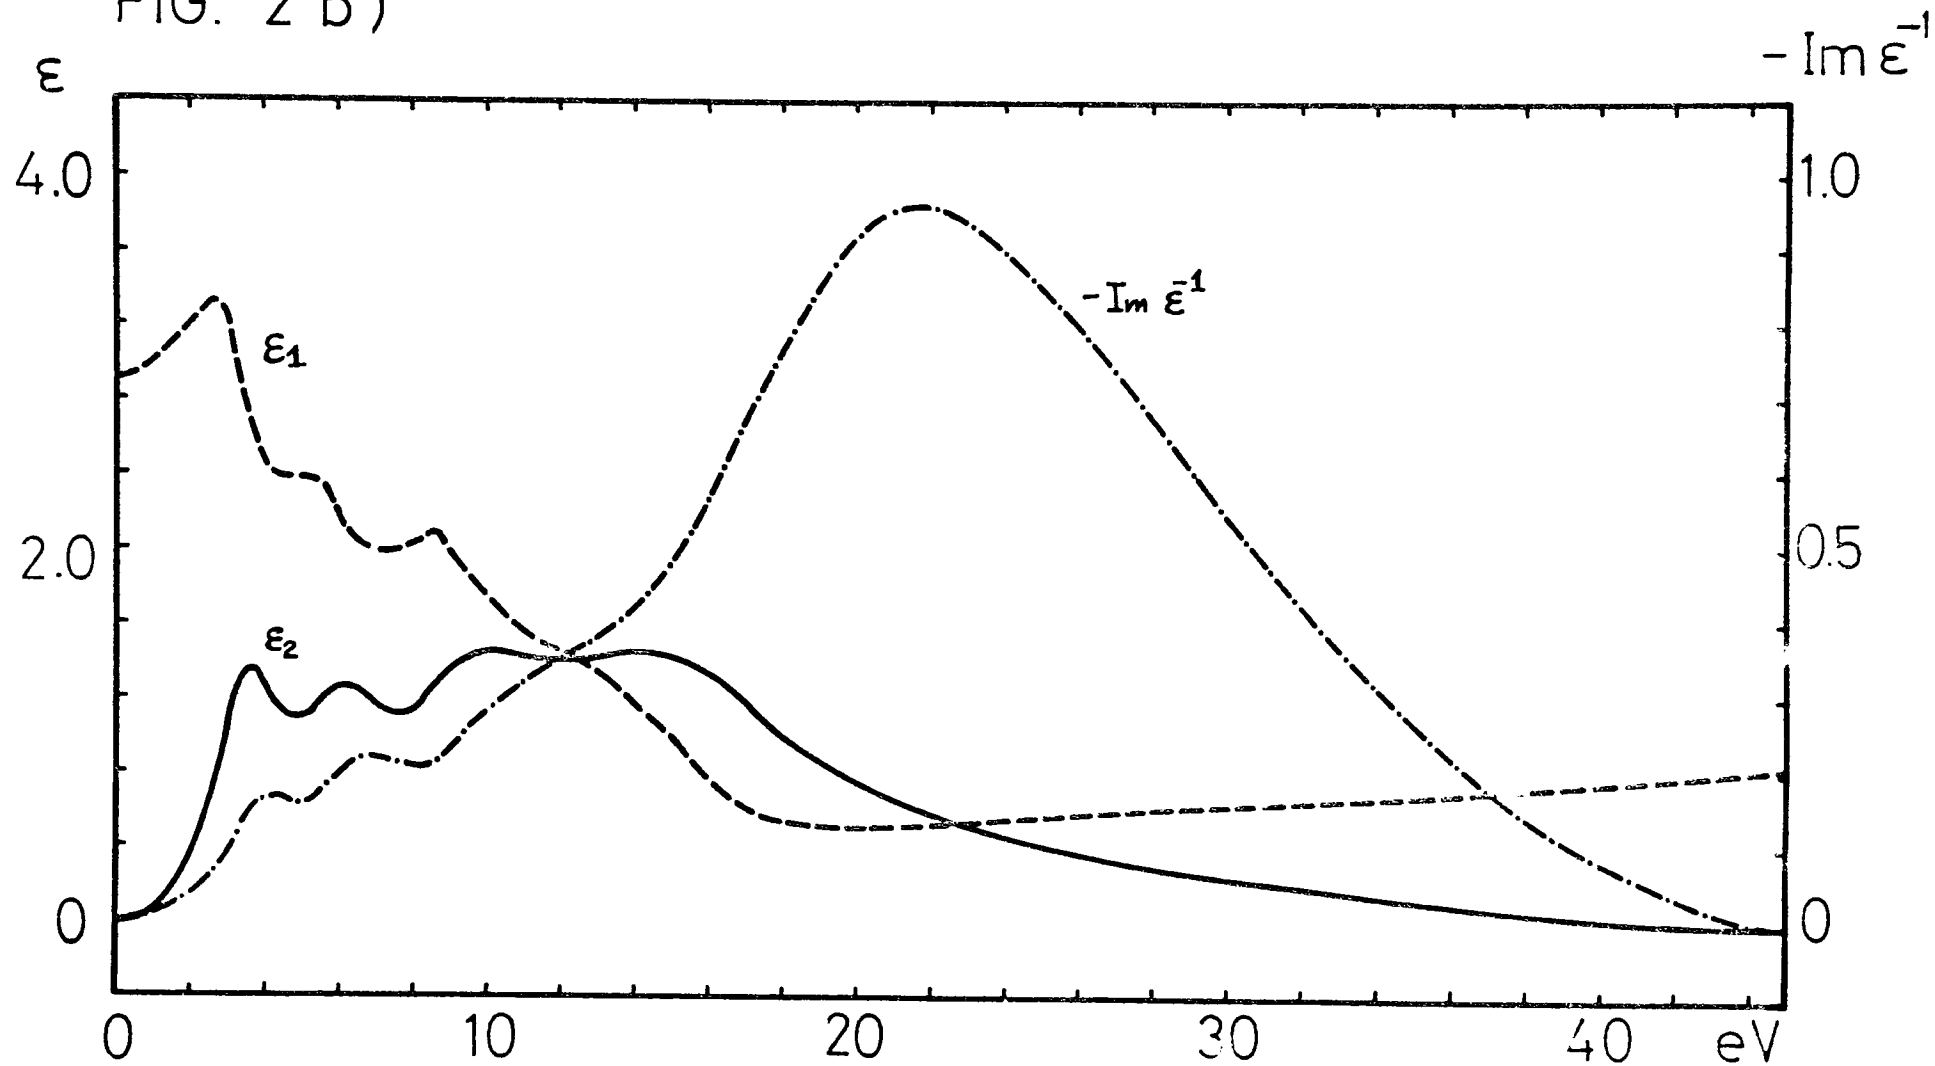


FIG. 2 c)

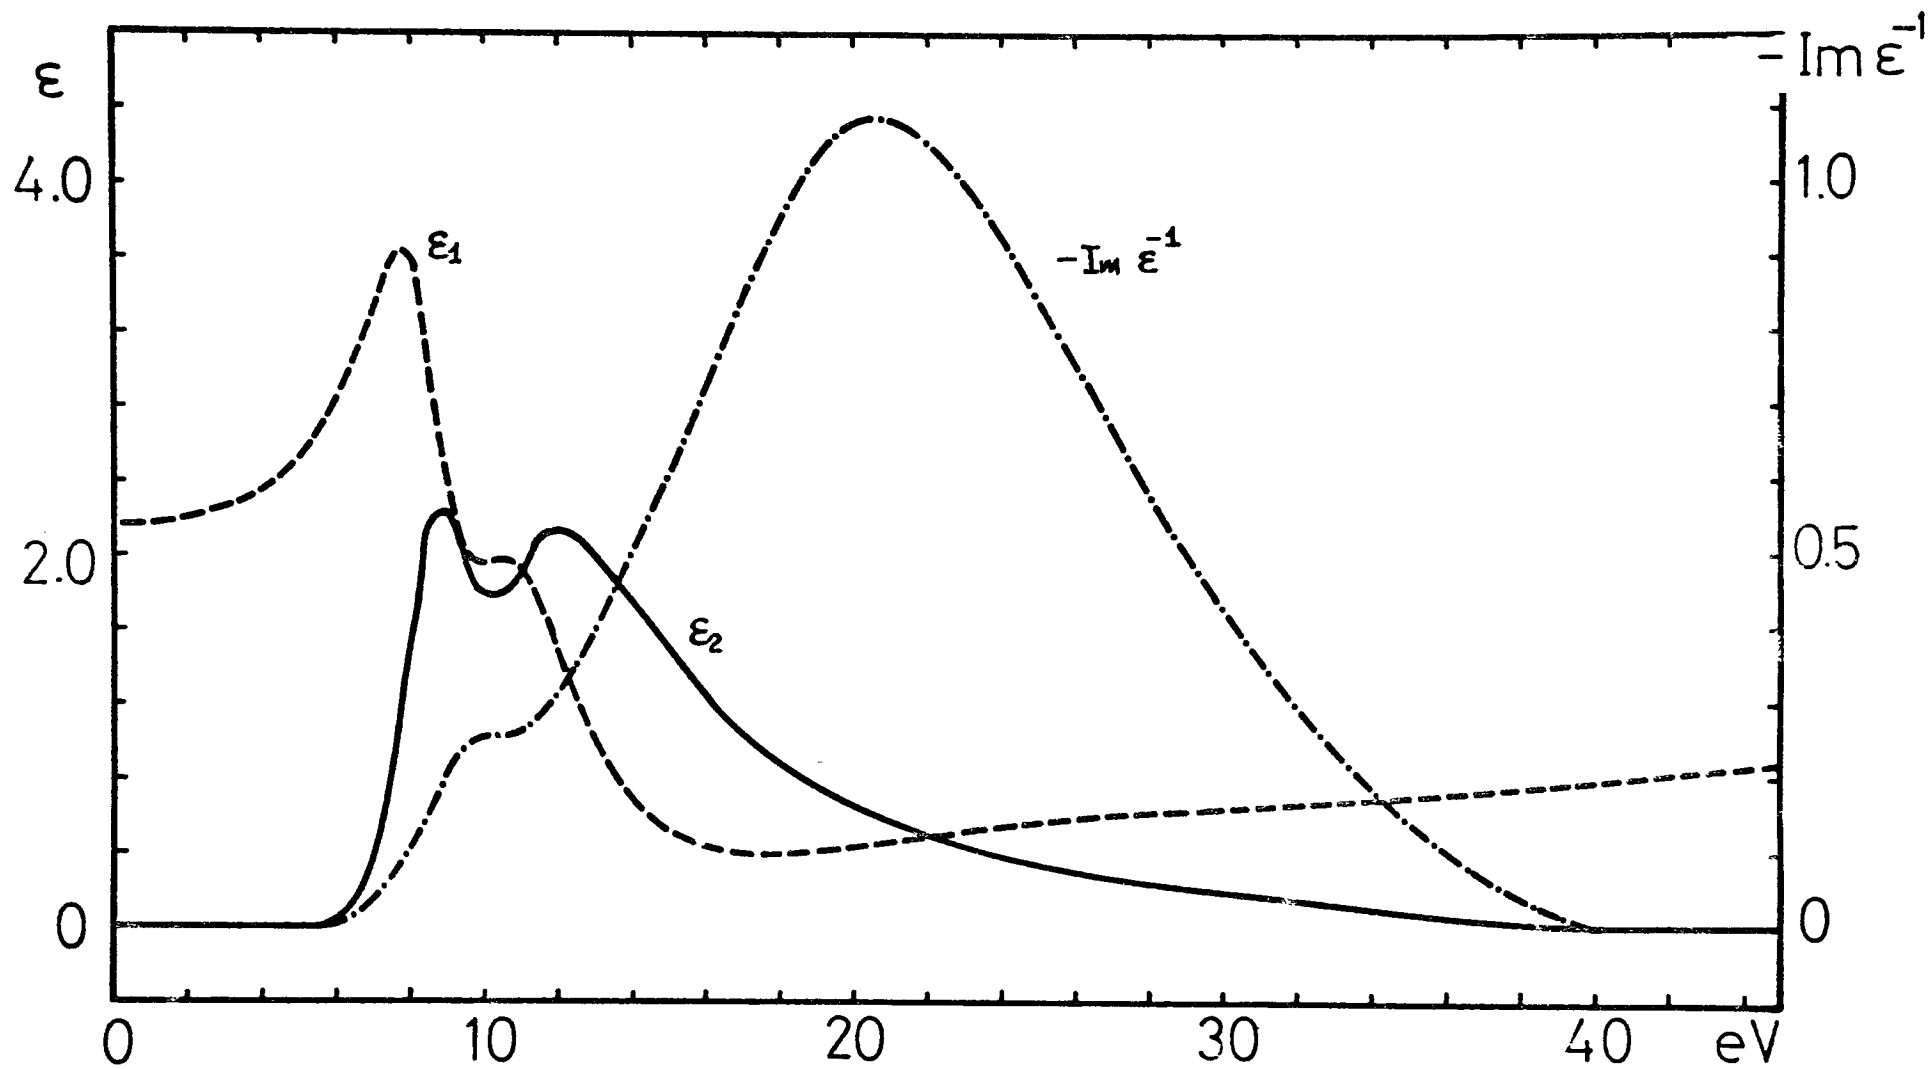


FIG. 3 a)

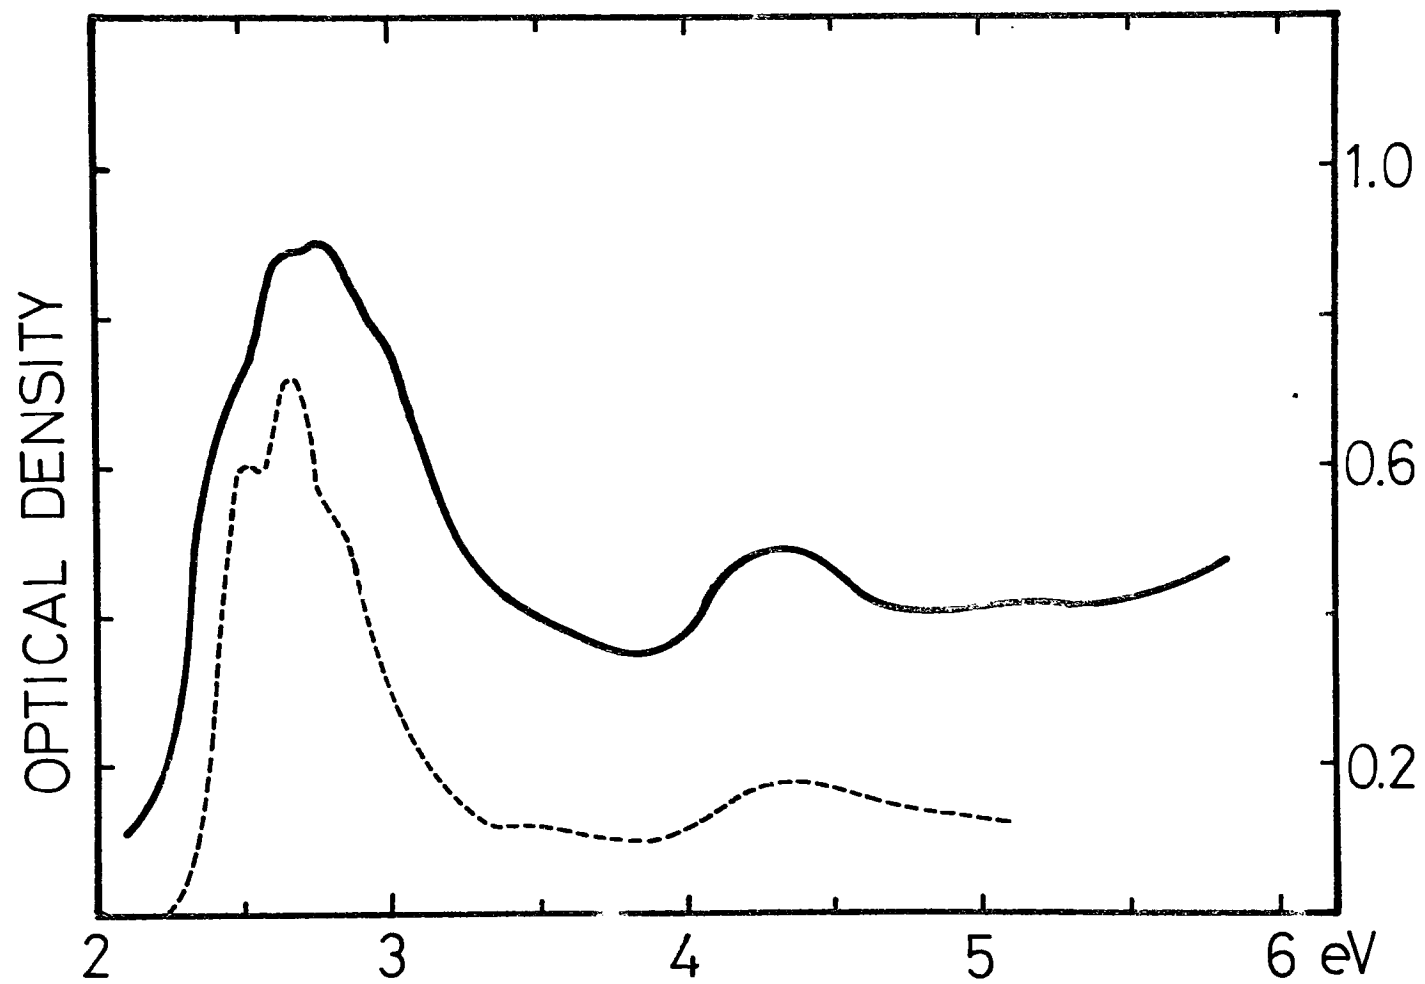


FIG. 3 b)

