

Integrated Research Center for Carbon Negative Energy Science

T. Nohira, Professor

K. Kondo, Program-Specific Associate Professor

1. Introduction

To achieve carbon neutrality in 2050, it is necessary to create a new energy system which includes an active carbon dioxide fixation process in addition to "zero emission" technology. In this research center, we are investigating such carbon negative technologies. Specifically, we are engaged in research to convert carbon dioxide into useful materials using renewable energy, biomass, etc.

In this fiscal year, we have investigated the conversion of CO₂ into diamond by molten salt electrochemical process. We have also studied the activity of fungal glucuronoyl esterase to cleave ester linkages in lignin-carbohydrate complex.

2. Conversion of CO₂ into diamond by molten salt electrochemical process

As a carbon negative technology, not only the CO₂ capture and storage (CCS) but also the CO₂ capture and utilization (CCU) will play an important role in the future. Here, electrochemical CO₂ conversion technology in molten salt is considered to be one of the promising candidates for CCU [1,2]. In this study, we aimed to convert CO₂ into diamond, which is one of the most valuable carbon materials. As a first step, we investigated the electrochemical synthesis of diamond in molten LiCl–KCl systems containing K₂CO₃ and KOH, based on the premise that CO₂ dissolves as CO₃²⁻ in molten salts containing O²⁻. We used micro-Raman spectroscopy and scanning electron microscopy (SEM) to confirm that the deposits obtained by electrolysis were diamond. As a second step, we attempted the electrochemical synthesis of diamond using CO₂ as the actual raw material. Here, we also bubbled H₂O into the molten salt to produce KOH.

Cyclic voltammetry and potentiostatic electrolysis were performed after adding K₂CO₃ and KOH to LiCl–KCl eutectic melts under an Ar atmosphere at 973 K. The working electrode was a Ni flag (Φ 3 × 0.1 mm) or Ni plate (5 mm × 10 mm × 0.1 mm), the counter electrode was a glass-like carbon rod, and the reference electrode was an Ag⁺/Ag electrode. The potential was calibrated with Li⁺/Li potential. After electrochemical measurements were performed, samples were prepared by potentiostatic electrolysis using the Ni plate electrodes. In the case where CO₂ was used as a raw material, LiCl–KCl eutectic molten salt containing Li₂O was prepared, and CO₂ and H₂O were bubbled into it in predetermined

amounts, respectively. After electrochemical measurements, potentiostatic electrolysis was performed to prepare samples. The obtained samples were analyzed by SEM, EDX, and micro-Raman spectroscopy.

First, electrochemical measurements in baths containing only K₂CO₃, only KOH, or both indicated that carbon deposition and hydrogen evolution proceed simultaneously in the potential range more negative than 1.2 V. Then, samples were prepared by potentiostatic electrolysis using Ni plate electrodes at 1.0 to 1.2 V (vs. Li⁺/Li). As an example, the surface SEM image of a deposit obtained at 1.1 V is shown in Fig. 1a. The EDX analysis of this area showed that only C and Ni from the substrate were detected. The result of micro-Raman spectroscopy of the sample is shown in Fig. 1b, which shows a spectrum characteristic of diamond with a sharp peak at 1332 cm⁻¹. Based on the results of these three analyses, the electrochemically synthesized angular particles were identified as diamond.

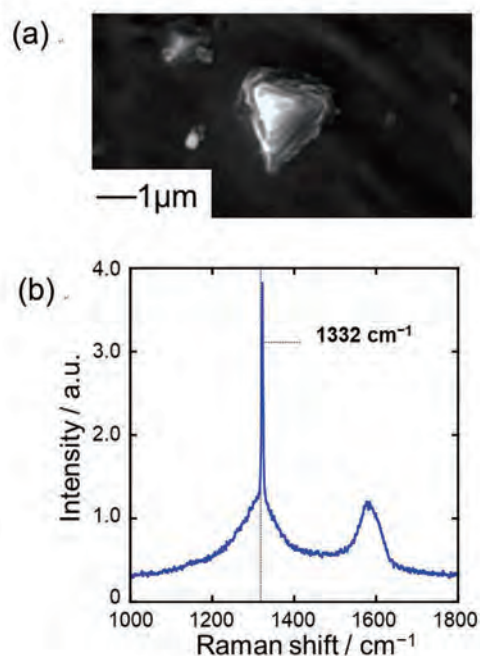


Fig. 1 (a) An SEM image and (b) a Raman spectrum of the sample obtained by potentiostatic electrolysis of a Ni plate electrode in molten LiCl–KCl–K₂CO₃–KOH at 973 K.

Second, CO₂ gas and H₂O gas were introduced in molten LiCl–KCl containing O²⁻ ions. After that, potentiostatic electrolysis was performed at 1.0 to 1.2 V (vs. Li⁺/Li). In samples prepared at 1.2 V, we observed a peak at 1332 cm⁻¹ attributed to diamond, as well as broad peaks attributed to the D-band and G-band of amorphous carbon. The obtained deposits are considered to be a mixture of diamond and amorphous carbon.

3. Activity of fungal glucuronoyl esterase to cleave ester linkages in lignin-carbohydrate complex

A major component of woody biomass is a lignin-carbohydrate complex which is formed by associations of lignin, hemicellulose, and cellulose. Lignin is an attractive aromatic resource for the production of various materials. Hemicellulose and cellulose can also be utilized to produce biofuels and multiple materials. However, the recalcitrant structure of the lignin-carbohydrate complex is an obstacle to the efficient utilization of woody biomass. In the lignin-carbohydrate complex, the association of lignin and hemicellulose is strengthened by covalent cross-linkages such as ether, ester, and phenyl glycoside linkages. Among these linkages, ester linkages formed between lignin and glucuronoxylan are often found in hardwood biomass, where glucuronoxylan is a main hemicellulose component. Glucuronoyl esterase (GE) is an enzyme that catalyzes the hydrolysis of the ester linkage, thereby weakening the association of lignin and glucuronoxylan (Fig. 2).

We previously identified a fungal GE which exerts high catalytic efficiency toward a model substrate, benzyl glucuronate. Although the GE can be prepared by yeast expression system, its yield (0.16 mg/L-culture) was insufficient for the investigation of GE activity toward natural substrates. This year, we improved the purification procedure for the GE. As a result, the yield of the GE reached 3.65 mg/L-culture. Therefore, a 28-fold increase in the yield was achieved.

We then investigated the activity of the GE toward ester linkage in the natural woody biomass. Firstly, a biomass fraction rich in the ester linkage was extracted from beech wood powder. From the extracted fraction, multiple signals of ester linkage were observed by NMR spectroscopy, which suggested the existence of various structures of lignin or hemicellulose proximal to the ester linkage (Fig. 3a). Next, enzymatic reaction by the GE toward the extracted fraction was performed. Intensities of some ester linkage signals were reduced by the reaction (Fig. 3-2b, labeled with asterisks), which indicated successful cleavage of ester linkages catalyzed by the GE. Exceptionally, the intensity of one ester linkage signal was not changed by the reaction (Fig. 3b, labeled with an arrow head). This result suggested that GE could not cleave the ester linkage giving this signal. The proximal structure of lignin or hemicellulose to this ester linkage may prevent GE activity due to steric hindrance. Our NMR analysis

demonstrated the GE activity to cleave ester linkages in the lignin-carbohydrate complex extracted from natural beech wood. In addition, an insight into the preference of substrate structure for GE activity was obtained.

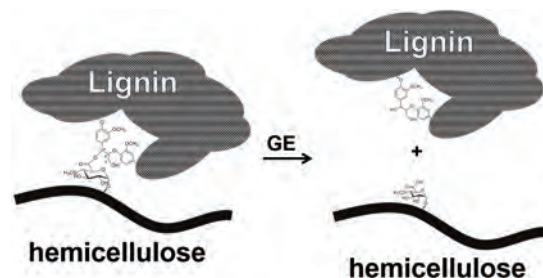


Fig. 2. Cleavage of ester linkage between lignin and hemicellulose.

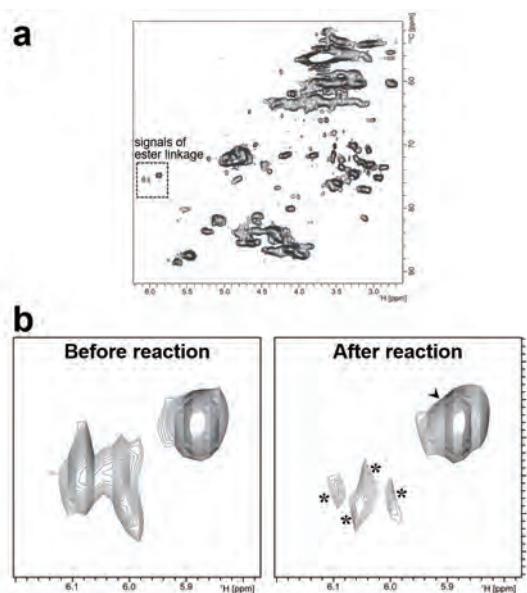


Fig. 3. NMR spectrum of extracted lignin-carbohydrate complex fraction (a) and ester linkage signals before and after the reaction by the GE (b).

Acknowledgement

These researches were partly supported by grant to T. N. from JSPS KAKENHI (21K19024).

References

- [1] H. Yin, X. Mao, D. Tang, W. Xiao, L. Xing, H. Zhu, D. Wang, D. R. Sadoway, *Energy Environ. Sci.*, **6**, 1538 (2013).
- [2] Y. Chen, M. Wang, J. Zhang, J. Tu, J. Ge, and S. Jiao, *J. Mater. Chem. A*, **9**, 14119 (2021).

Collaboration Works

野平俊之, コスモ石油-京都大学, 「溶融塩電解による CO₂ の炭素固定化技術」に関する研究

Financial Support

1. Grant-in-Aid for Scientific Research

野平俊之, 基盤研究(A), 液体亜鉛陰極を利用した太陽電池用シリコンの新製造法

野平俊之, 挑戦的研究(萌芽), 二酸化炭素を原料とした革新的常圧ダイヤモンド電解合成法の開発

近藤敬子, 基盤研究(C), リグニンと多糖を分離する酵素の実バイオマスに対する活性および構造機能相関の解析

2. Others

野平俊之, (株) SOKEN, CO₂ 還元デバイスの原理検証に関する研究

野平俊之, (公財) かずさ DNA 研究所・本田技研工業(株), バイオマスの高エネルギー密度化研究

野平俊之, 新エネルギー・産業技術総合開発機構, 「高効率な資源循環システムを構築するためのリサイクル技術の研究開発事業」

野平俊之, 日本風力開発(株), 洋上風力等再エネにかかる水素関連技術動向とその連携の在り方に関する研究

野平俊之, 国際協力機構, JICA 研修員受入

Publications

T. Yamamoto, A. Yadav, T. Nohira, Charge–Discharge Behavior of Graphite Negative Electrodes in FSA-Based Ionic Liquid Electrolytes: Comparative Study of Li-, Na-, K-Ion Systems, *Journal of the Electrochemical Society*, 169, 5, 050507, 2022

T. Kodaki, T. Kishiro, Y. Sugie, T. Nohira, Isolation of ionic liquid-tolerant *Saccharomyces cerevisiae* using adaptive laboratory evolution, and bioethanol production from cellulose in the presence of ionic liquids, *Journal of the Japan Institute of Energy*, 101, 4, 83-87, 2022

Y. Ma, K. Yasuda, T. Yamamoto, X. Yang, T. Nohira, Electrodeposition of Si from Silicate Ions at Graphite and Liquid Zn Electrodes in Molten CaCl₂, *Journal of*

the Electrochemical Society, 169, 5, 052506, 2022

H. Hua, K. Yasuda, T. Nohira, Highly Efficient and Precise Electrolysis Separation of Dysprosium from Neodymium for Magnet Scrap Recycling in Molten Salt, *ACS Sustainable Chemistry & Engineering*, 10, 28, 9225-9231, 2022

Y. Ma, K. Yasuda, T. Nohira, Electrochemical Reduction of Silicate Ions at Liquid Zn Electrode in Molten NaCl–CaCl₂, *Metallurgical and Materials Transactions B–Process Metallurgy and Materials Processing Science*, 53, 3602-3612, 2022

Y. Norikawa, M. Unoki, K. Yasuda, T. Nohira, Effects of Temperature, Ti(III) Ion Concentration, and Current Density on Electrodeposition of Ti Films in LiF–LiCl Melt, *Journal of the Electrochemical Society*, 169, 9, 092523, 2022

T. Nishida, Y. Fukunaka, T. Homma, T. Nohira, Galvanostatic Li Electrodeposition in LiTFSI-PC Electrolyte: Part II. Coupling Phenomena in Growth Process, *Journal of the Electrochemical Society*, 169, 9, 090529, 2022

T. Nishida, Y. Fukunaka, T. Homma, T. Nohira, Galvanostatic Li Electrodeposition in LiTFSI-PC Electrolyte: Part I. Effects of Current Density in Initial Stage, *Journal of the Electrochemical Society*, 169, 10, 100548, 2022

Y. Norikawa, A. Kondo, K. Yasuda, T. Nohira, Electrodeposition of crystalline Si in molten alkali metal fluoride–chloride mixtures: Comparative study of Li, Na, K, and Cs systems, *Electrochimica Acta*, 434, 1, 141255, 2022

Y. Norikawa, X. Meng, K. Yasuda, T. Nohira, Effect of Temperature on Crystal Structure of W Films Electrodeposited from Molten CsF–CsCl–WO₃, *Journal of the Electrochemical Society*, 169, 10, 102506, 2022

T. P. Moffat, Y. S. Meng, T. Jacob, T. Nohira, Y. Fukunaka, Commentary—JES Focus Issue on Nucleation Growth: Measurements, Processes, and Materials, *Journal of the Electrochemical Society*, 169, 11, 110001, 2022

A. Yadav, H. Kobayashi, T. Yamamoto, T. Nohira, Electrochemical Rubidium Storage Behavior of Graphite in Ionic Liquid Electrolyte, *Electrochemistry*, 91, 1, 017002, 2023

T. Nikaido, A. Yadav, T. Yamamoto, T. Nohira, Comparative Study on Charge–Discharge Behavior of Graphite

Positive Electrode in FSA- and FTA-Based Ionic Liquid Electrolytes with Different Alkali Metal Cations, *Journal of the Electrochemical Society*, 170, 2, 020526, 2023

Y. Norikawa, M. Iizuka, T. Nohira, Electrolytic Separation of Iodine from LiCl-KCl-LiBr-LiI Melt and Recovery of Iodine Gas with Copper, *ECS Transactions*, 109, 14, 165-173, 2022

H. Konishi, T. Takao, T. Oishi, T. Nohira, Y. Koizumi, Electrochemical Formation of Dy-Ni Alloys in a Molten Cesium Chloride System, *ECS Transactions*, 109, 14, 3-9, 2022

W. Moteki, Y. Norikawa, T. Nohira, Electrodeposition of Crystalline Si Using a Liquid Zn Electrode in Molten KF-KCl-K₂SiF₆, *ECS Transactions*, 109, 14, 225-234, 2022

K. Yasuda, T. Nohira, Electrochemical production of silicon, *High Temperature Materials and Processes*, 41, 1, 247-278, 2022

O.S. Eladl, Y. Yamaoki, K. Kondo, T. Nagata, M. Katahira, Detection of interaction between an RNA aptamer and its target compound in living human cells using 2D in-cell NMR., *Chemical Communications*, 59, 102-105, 2022

Y. Yamaoki, T. Nagata, K. Kondo, T. Sakamoto, S. Takami, M. Katahira, Shedding light on the base-pair opening dynamics of nucleic acids in living human cells, *Nature Communications*, 13, 7143, 2022

T. Mori, N. Masuzawa, K. Kondo, Y. Nakanishi, S. Chida, D. Uehara, M. Katahira, M. Takeda, A heterodimeric hyaluronate lyase secreted by the activated sludge bacterium *Halicomonobacter hydrossis*, *Bioscience, Biotechnology, and Biochemistry*, 87, 3, 256-266, 2023

Presentations

Y. Norikawa, X. Meng, K. Yasuda, T. Nohira, Effect of Temperature on the Crystal Structure and Surface Morphology of W Films Electrodeposited from CsF-CsCl Eutectic Melt, 241st ECS Meeting, Vancouver Convention Center / Online, 2022.5. 29-6.2

Y. Norikawa, K. Yasuda, T. Nohira, Effect of Temperature on Grain Growth during Ti Electrodeposition in LiF-LiCl Eutectic Melt, 241st ECS Meeting, Vancouver Convention Center / Online, 2022.5. 29-6.2

石尾吉史, 眞鍋光毅, 山本貴之, 野平俊之, その場ラマン分光を用いたナトリウム二次電池の性能向

上要因の解析, 第 92 回マテリアルズ・テラリング研究会, 財団法人 加藤山崎教育基金 軽井沢研修所, 2022.8.5-7

茂木 渉, 法川 勇太郎, 野平 俊之, 熔融 KF-KCl-K₂SiF₆ 中における液体 Zn 電極を用いた結晶性 Si 電析に与える電気量の影響, 第 92 回マテリアルズ・テラリング研究会, 財団法人 加藤山崎教育基金 軽井沢研修所, 2022.8.5-7

王昊琛, 孟憲鐸, 法川勇太郎, 野平俊之, Electrodeposition of Smooth Tungsten Films in Molten CsF-CsCl-WO₃, 第 92 回マテリアルズ・テラリング研究会, 財団法人 加藤山崎教育基金 軽井沢研修所, 2022.8.5-7

Y. Itoda, H. Usui, Y. Domi, T. Yamamoto, T. Nohira, K. Matsumoto, R. Hagiwara, H. Sakaguchi, The Effects of Solid Solution Strengthening of Bi-Sb Alloy on Anode Properties of Sodium Ion Batteries, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

N. Wada, Y. Domi, H. Usui, T. Yamamoto, T. Nohira, H. Sakaguchi, Anode Properties of LaSb/Sb Composite Electrodes for Potassium-Ion Battery, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

Y. Itoda, H. Usui, Y. Domi, T. Yamamoto, T. Nohira, K. Matsumoto, R. Hagiwara, H. Sakaguchi, Development of Anode/Electrolyte Interface for Advanced Na-Ion Battery, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

N. Wada, Y. Domi, H. Usui, T. Yamamoto, T. Nohira, H. Sakaguchi, Study on Development of Compound-Based Anode for K-Ion Battery and on Compatibility with Ionic Liquid Electrolyte, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

K. Jiao, T. Yamamoto, T. Nohira, KFeO₂ positive electrode for K-ion battery using an FSA-based ionic liquid electrolyte, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

A. Yadav, H. Kobayashi, T. Nikaido, T. Yamamoto, T. Nohira, Potassium-based Dual-Carbon Battery Using FTA-based Ionic Liquid Electrolytes, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

W. Moteki, Y. Norikawa, T. Nohira, Electrodeposition of Crystalline Si at a Liquid Zn Electrode in KF-KCl Molten Salt: Effect of the Charge Passed, The 13th International Symposium of Advanced Energy Science, Online,

2022.9.5-7

Y. Katasho, Y. Norikawa, T. Oishi, T. Nohira, Spectroscopic measurement of boron species in molten salt, The 13th International Symposium of Advanced Energy Science, Online, 2022.9.5-7

堀場由梨奈, 法川勇太郎, 野平俊之, 熔融 LiCl-KCl-K₂CO₃-KOH 系におけるダイヤモンド電解合成に向けた炭素電析の最適化, 第 54 回熔融塩化学討論会, ハイブリッド開催, 2022.9.29-30

王昊琛, 孟憲鐸, 法川勇太郎, 野平俊之, 熔融 CsF-CsCl-WO₃ 中で得られる電析W膜の結晶構造に与える酸素の影響, 第 54 回熔融塩化学討論会, ハイブリッド開催, 2022.9.29-30

茂木 渉, 法川勇太郎, 野平俊之, 熔融 KF-KCl-K₂SiF₆ 中における液体 Zn 電極を用いた, 第 54 回熔融塩化学討論会, ハイブリッド開催, 2022.9.29-30

W. Moteki, Y. Norikawa, T. Nohira, Electrodeposition of Crystalline Si Using a Liquid Zn Electrode in Molten KF-KCl-K₂SiF₆, The 242nd ECS Meeting, Hilton Atlanta, 2022.10.9-13

Y. Norikawa, M. Iizuka, T. Nohira, Electrolytic Separation of Iodine from LiCl-KCl-LiBr-LiI Melt and Recovery of Iodine Gas with Copper, The 242nd ECS Meeting, Hilton Atlanta, 2022.10.9-13

小林大展, Alisha Yadav, 山本貴之, 野平俊之, イオン液体中におけるアルカリ金属-グラファイト層間化合物の電気化学的挙動, 第 63 回電池討論会, 福岡国際会議場/Online, 2022.11.8-10

二階堂貴文, 山本貴之, 野平俊之, 異なるイオン液体中におけるグラファイトへのアミドアニオン挿入脱離挙動の比較検討, 第 63 回電池討論会, 福岡国際会議場/Online, 2022.11.8-10

石尾吉史, 山本貴之, 野平俊之, イオン液体を用いた Na 二次電池の正極/電解液界面のその場ラマン分光分析, 第 63 回電池討論会, 福岡国際会議場/Online, 2022.11.8-10

後藤啓太, 川口健次, 野平俊之, 熔融 KOH-H₂O 系を用いた新規高温アルカリ水電解, 第 46 回電解技術討論会, コンパルホール (大分) /Online, 2022.11.17-18

和田直也, 道見康弘, 薄井洋行, 山本貴之, 野平俊之, 坂口裕樹, LaSb と Sb からなるコンポジット電極のカリウムイオン電池負極特性, 鳥取大学工学部附属 GSC 研究センター創立 10 周年記念シンポジ

ウム, 鳥取大学/Online, 2022.12.5

二階堂貴文, 山本貴之, 野平俊之, 異なるアミド系イオン液体中におけるグラファイト正極挙動の比較検討, 2022 年度第 3 回関西電気化学研究会, Online, 2022.12.10

堀場由梨奈, 法川勇太郎, 野平俊之, 熔融 LiCl-KCl 中における CO₂ と H₂O を原料としたダイヤモンド電解合成, 2022 年度第 3 回関西電気化学研究会, Online, 2022.12.10

川口健次, 野平俊之, 熔融 LiF-CaF₂-NdF₃-DyF₃ 中における Nd-Dy-Fe 合金の電気化学的生成, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

山本貴之, 二階堂貴文, 小林大展, ヤダヴ アリシャ, 野平俊之, アミド系イオン液体電解質を用いたデュアルカーボン電池の開発, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

焦楷, 山本貴之, 木内久雄, 趙昊懂, 野平俊之, Charge-discharge behavior of KFeO₂ positive electrode for K-ion battery using an FSA-based ionic liquid electrolyte, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

茂木 渉, 法川勇太郎, 野平俊之, 熔融 KF-KCl-K₂SiF₆ 中における液体 Zn 電極を用いた結晶性 Si 電析: Si 基板上に電析で準備した Zn 膜電極を用いた検討, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

石尾吉史, 山本貴之, 野平俊之, 高 Na+濃度イオン液体を用いた Na 二次電池における性能向上要因の検討, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

後藤啓太, 川口健次, 野平俊之, 熔融 KOH-H₂O 系における Ni 電極上での高温アルカリ水電解反応の速度論的解析, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

王昊琛, 法川勇太郎, 野平俊之, 熔融 CsF-CsCl-WO₃-Li₂O 中におけるタングステン電析, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

侯正陽, 茂木 渉, 法川勇太郎, 野平俊之, 熔融 KF-KCl-K₂SiF₆ 中での Si 電析による p-n 接合 Si 膜の作製, 電気化学会第 90 回大会, 東北工業大学/Online, 2023.3.27-29

道見康弘, 薄井洋行, 栗谷和希, 西川慶, 山本貴之, 野平俊之, 坂口裕樹, カリウムイオン電池用アンチモン合金負極の創製, 電気化学会第 90 回大会, 東

北工業大学／Online, 2023.3.27-29

名合虎之介, 法川勇太郎, 松島永佳, 野平俊之, 上田幹人, 溶解 LiCl-KCl-LiD-LiH 系での電解を用いた重水素同位体分離, 電気化学会第 90 回大会, 東北工業大学／Online, 2023.3.27-29

Y. Yamaoki, O. Eladl, K. Kondo, T. Sakamoto, T. Nagata, M. Katahira, Investigation of the structural dynamics and interactions of RNAs in living human cells by in-cell NMR, The 23rd Annual Meeting of the RNA Society of Japan, Miyako Messe, 2022.7.20-22

八木勇成, 近藤敬子, Huyen Nguyen, 井関優侑, 奥岡奈宜, 渡辺隆司, 三上文三, 永田崇, 片平正人, 結晶性セルロースの分解におけるセルラーゼと選択的白色腐朽菌由来 LPMO9 のシナジー効果, セルロース学会第 29 回年次大会, 金沢市文化ホール, 2022.7.21-22

小林直子, 橋爪知弘, 近藤敬子, 片平正人, 北山健司, 渡辺隆司, リグノセルロースの有機酸可溶化とバイオマスペーパーの構造特性解析, セルロース学会第 29 回年次大会, 金沢市文化ホール, 2022.7.21-22

T. Saito, Y. Qiao, W. Osugi, K. Kondo, M. Katahira, M. Takeda, Fermentation of cellulase-aminating reagent via carbon fixation, The 13th International Symposium of Advanced Energy Science, Kyoto University, 2022.9.5-7

R. Kurokawa, Y. Yoneda, N. Ueda, Y. Yamaoki, K. Kondo, T. Nagata, M. Katahira, NMR analysis on regulation of the RNA-binding protein TLS-induced phase separation via methylated RNA, The 13th International Symposium of Advanced Energy Science, Kyoto University, 2022.9.5-7

H. Nishimura, K. Saito, N. Kobayashi, M. Sano, Y. Iseki, Y. Mizukoshi, Y. Minami, T. Hashizume, K. Kondo, M. Katahira, T. Watanabe, Structural analysis of lignocellulosic biomass by NMR spectroscopy toward decarbonized society, The 13th International Symposium of Advanced Energy Science, Kyoto University, 2022.9.5-7

S. Waga, K. Kamba, Y. Yamaoki, A. Eladl, S. Hoshina, H. Horinouchi, K. Kondo, T. Nagata, M. Katahira, Structural basis of DNA recognition by the replication initiator ORC, The 13th International Symposium of Advanced Energy Science, Kyoto University, 2022.9.5-7

H. Morita, S. Chida, M. Takato, K. Kondo, M. Katahira, M. Takeda, Enzymatic degradation of a cellulose-aminating polysaccharide, glucosaminoglycan, Ac-

tive Enzyme Molecule 2022, Toyama Prefectural University, 2022.9.30-10.1

千田舜, 森田大貴, 高遠昌樹, 近藤敬子, 片平正人, 武田穰, キトサナーゼによるグルコース-グルコサミン β -1, 4 交互共重合体の分解, 第 74 回日本生物工学会大会, Online, 2022.10.17-20

Y. Yamaoki, E. Eladl, K. Kondo, T. Sakamoto, T. Nagata, M. Katahira, Base-pair opening dynamics of nucleic acids in living human cells studied by in-cell NMR, International Symposium on Nucleic Acids Chemistry 2022 (ISNAC2022), Tokyo University of Science Katsushika Campus, 2022.11.2-4

山置佑大, 永田崇, 近藤敬子, 阪本知樹, Eladl Omar, 片平正人, In-cell NMR 法によるヒト生細胞内における核酸の塩基対開閉ダイナミクスの解析, 第 61 回 NMR 討論会, 高知県立県民文化ホール, 2022.11.8-10

小林直子, 橋爪知弘, 近藤敬子, 片平正人, 北山健司, 渡辺隆司, リグノセルロースの有機酸可溶化とバイオマスフィルムの構造特性解析, 第 67 回リグニン討論会, Online, 2022.11.10-11

山置佑大, 永田崇, 川上愛加, 阪本知樹, Eladl Omar, 近藤敬子, 片平正人, NMR 法による核酸のコンデンセートおよびヒト生細胞内における核酸の塩基対開閉ダイナミクスの解析, 第 45 回日本分子生物学会, 幕張メッセ, 2022.11.30-12.2

川上愛加, 山置佑大, 近藤敬子, 阪本知樹, 永田崇, 片平正人, 核酸から成る液滴の NMR 法を用いた物理化学的解析, 第 45 回日本分子生物学会, 幕張メッセ, 2022.11.30-12.2

P. Apisan, K. Kondo, T. Nagata, M. Katahira, Co-displaying of xylanase and feruloyl esterase on the *Pichia pastoris* cell surface, The 73rd Annual Meeting Japan Wood research Society, Fukuoka University Kyushu University, 2023.3.14-16

Teo Kenneth, 近藤敬子, 渡辺隆司, 永田崇, 片平正人, マンガンペルオキシダーゼ触媒によるフェノールリグニン二量体の変換の分子レベルでの解明, 第 73 回日本木材学会大会, 福岡大学 九州大学, 2023.3.14-16

井関優侑, 奥岡奈宜, 橋爪知弘, 近藤敬子, 永田崇, 片平正人, 渡辺隆司, *Ceriporiopsis subvermispora* 由来溶解性多糖モノオキシゲナーゼのセルロース解重合反応の解析, 第 73 回日本木材学会大会, 福岡大学 九州大学, 2023.3.14-16

小林直子, 橋爪智弘, 近藤敬子, 片平正人, 北山健

司, 渡辺隆司, リグノセルロースの有機酸可溶化とバイオマスフィルムの構造特性解析, 第 73 回日本木材学会大会, 福岡大学 九州大学, 2023.3.14-16

内田貴己, 徳永有希, 永田崇, 近藤敬子, 片平正人, 渡辺隆司, *Trichoderma reesei* Cel7A のセルラーゼ糖質結合モジュールと人工リグニンの相互作用解析, 第 73 回日本木材学会大会, 福岡大学 九州大学, 2023.3.14-16

斉藤朝昌, 大杉航, 近藤敬子, 片平正人, 武田穰, 硫化水素存在下での従属栄養および独立栄養によるセルロースアミノ化剤の発酵生産, 日本農芸化学会 2023 年度広島大会, Online, 2023.3.14-17

小林直子, 橋爪智弘, 近藤敬子, 片平正人, 北山健司, 渡辺隆司, リグノセルロースの有機酸可溶化とバイオマスフィルムの構造特性解析, 日本化学会 第 103 春季年会, 東京理科大学, 2023.3.22-25