

Research Paper

Title:

**Thermodynamic Analysis and Effect of Crystallinity for Silicon Monoxide
Negative Electrode for Lithium Ion Batteries**

Authors:

Kouji Yasuda,^{a,b,*} Yusuke Kashitani,^c Shingo Kizaki,^c Kohki Takeshita,^c
Takehisa Fujita,^c and Shinji Shimosaki^c

Affiliations:

^aEnvironment, Safety and Health Organization, Kyoto University, Yoshida-honmachi,
Sakyo-ku, Kyoto 606-8501, Japan

^bGraduate School of Energy Science, Kyoto University, Yoshida-honmachi, Sakyo-ku,
Kyoto 606-8501, Japan

^cHigh-Performance Materials Manufacturing Department, OSAKA Titanium
technologies Co., Ltd., 1, Higashihama-cho, Amagasaki, Hyogo 660-8533, Japan

Corresponding Author:

*E-mail: yasuda.kouji.3v@kyoto-u.ac.jp (K. Yasuda); Tel: +81-75-753-4817; Fax: +81-
75-753-5906

Abstract

The electrochemical behavior of SiO negative electrodes for lithium ion batteries is thermodynamically and experimentally investigated. The analysis of the reaction pathway and the calculation of the reaction potentials during the Li insertion/extraction reactions are carried out by the construction of the ternary phase diagram for the Li–Si–O system. In the initial reaction of Li insertion, metallic Si and lithium silicates are formed above 0.37 V vs. Li/Li⁺ as a conversion reaction of the SiO negative electrode. Further Li insertion produces Li–Si alloys as reversible reaction phases. The decomposition of the Li₄SiO₄ phase begins before the formation of the Li–Si alloy is completed. The measured electrode behavior of the SiO negative electrode basically agrees with the thermodynamic calculations, especially at a low reaction rate; deviations can be ascribed to kinetic factors and electrode resistance. The values of over 1898 mA h g⁻¹ and 71.0% were obtained for the discharge capacity and the coulombic efficiency, respectively. Furthermore, the overvoltage for an amorphous SiO electrode was smaller than that for a disproportionated SiO electrode into Si and SiO₂ phases.

Highlights

- Thermodynamic analysis of SiO electrodes
- Highest discharge capacity and relatively high coulombic efficiency for SiO anode
- Superior characters of amorphous SiO than disproportionated SiO

Keywords

Silicon monoxide, Thermodynamics, Phase diagram, Lithium ion battery

1. Introduction

Lithium ion batteries (LIBs) are widely utilized as efficient storage devices for mobile systems such as laptop computers and cell phones. The large operational voltage derives from the redox reactions for lithium (Li) species both at the positive and negative electrodes. One major concern surrounding LIBs is the insufficient capacity of the graphite negative electrode in the context of long-distance driving for electric vehicles (EVs) and hybrid electric vehicles (HEVs). The development of alloying-dealloying processes with Li by using alloying materials such as silicon (Si) and tin (Sn) as well as conversion-type materials of metal oxides, nitrides, and phosphides constitutes a crucial task toward achieving large capacities [1–3]. Among the various candidates, silicon monoxide (SiO) is expected to have a high capacity and impressive cyclability by overcoming the drawbacks of a large volume expansion and a large irreversible capacity for alloying materials and conversion-type materials, respectively.

In the Si–oxygen (O) binary system [4], silicon dioxide (SiO₂) is the only stable oxide at ambient pressure and temperature. Silicon oxides with lower oxygen content, SiO_x – where x is the atomic ratio of oxygen with respect to silicon, and falls between 0 (Si) and 2 (SiO₂) – have no stable crystalline structure including SiO [5–11]. Among silicon lower oxides, solid SiO is the only commercially available variety, and is usually manufactured with a vapor deposition technique from the gaseous SiO produced by the reaction of Si and SiO₂ at high temperatures [11–13]. The notable characteristic of solid SiO is its disproportionation into solid nanocrystalline Si particles and solid SiO₂ matrix above ~1123 K [14,15]. The crystallinity of the SiO materials changes with the thermal history during the production processes. Accordingly, both the amorphous and disproportionated varieties of SiO are sometimes referred to as “commercial SiO.”

Nevertheless, it should be emphasized that the characteristics of amorphous SiO and disproportionated SiO are different. For instance, the Si valence states for amorphous SiO are evaluated using X-ray photoelectron spectroscopy (XPS) analysis as Si(0), Si(1+), Si(2+), Si(3+), and Si(4+), depending on the number of bonds coordinated with oxygen; on the other hand, the valence states are evaluated as Si(0) and Si(4+) for disproportionated SiO [16–18].

The characteristics of SiO negative electrodes for LIBs have already been reported by many researchers for the case of both amorphous SiO and disproportionated SiO [19–32]. In addition to SiO negative electrodes, the electrochemical characteristics of (SiO + carbon) composite electrodes [33–44] and SiO₂ electrodes [28, 45–50] have also been reported. Table 1 summarizes the results for the SiO phase (amorphous or disproportionated), the intermediate phase during Li insertion/extraction, the initial charge and discharge capacities, the initial coulombic efficiency, and the analysis methods, where the charge/discharge rates and cut-off voltages are irrelevant.


Table 1 Representative reports on battery and electrode characteristics of the SiO negative electrode.

Author, Ref.	Year	SiO phase	Intermediate phase	Initial charge capacity (mAh g ⁻¹)	Initial discharge capacity (mAh g ⁻¹)	Initial coulombic efficiency (%)	Note
Yang et al. [19]	2002	Amor.	-	ca. 2250	ca. 1300	ca. 57.8	-
Nagao et al. [20]	2004	Amor.	SiO ₂	1594	-	-	Neutron elastic scattering
Miyachi et al. [21]	2005	Amor.	Li-Si-O, Li ₂ O	2404	598	24.9	XPS
Miyachi et al. [22]	2007	-	Li-Si-O, Li ₂ O	2520	1260	50.0	Metal-doped SiO, XPS
Kim et al. [23]	2007	-	Li-Si-O, Li ₂ O	2680	1470	54.9	NMR, HR-TEM, electrochemical dilatometry. Plateau at 0.8 V vs. Li ⁺ /Li in 1st discharge
Yamada et al. [24]	2007	-	-	-	-	-	Kinetics evaluation by AC impedance spectroscopy
Park et al. [25]	2010	Amor./dispro.	SiO ₂	2216/185	1104/94	49.8/50.8	TEM, Disproportionated at 800, 1000, and 1200 °C.
Komaba et al. [26]	2011	-	-	ca. 1800	826	45.9	-
Kim et al. [27]	2011	Amor./dispro.	Li-Si-O, Li ₂ O	2410	1300	53.9	NMR, HR-TEM, Differential capacity peaks at 0.08 and 0.24 V vs. Li ⁺ /Li
Yamamura et al. [28]	2011	Dispro.	Li-Si-O	2548	1791	70.3	Plateau at 0.2 and 0.5 V vs. Li ⁺ /Li in 1st discharge. First principles calculation. SiO ₂ was also reacted.
Miyuki et al. [29]	2011	Amor./dispro.	-	-	-	-	LiFePO ₄ /SiO full cell.
Jeong et al. [30]	2012	Dispro.	-	1757	1265	72.0	TiO ₂ coated SiO
Kim et al. [31]	2013	Dispro.	-	1958	1413	72.2	Carbon coated SiO. Differential capacity peaks at 0.06, 0.21, 0.31 and 0.48 V vs. Li ⁺ /Li after 5th cycle
Takezawa et al. [32]	2013	Amor.	Li-Si-O, Li ₂ O	2418	1306	54.0	SiO ₂ (0.17 < x < 1.34) was used. XPS

-: Not given

1
2
3 In this paper, we use the phrases “charge” and “discharge” for Li insertion and
4
5 extraction reactions, respectively. The Li insertion reaction is reported to proceed with
6
7 the formation of Li–Si alloys, lithium silicates (Li–Si–O), and/or Li₂O [21,33,34];
8
9 moreover, the alloying-dealloying of Si contributes to the reversible capacity. Whereas
10
11 the formed silicates and Li₂O lead to the irreversible capacity, the silicates play the role
12
13 of a matrix of nano Si (2–10 nm diameter) for the fast diffusion of Li atoms and the
14
15 mitigation of structural collapse [24]. The formation of these oxide phases has been
16
17 evaluated by various techniques such as XPS, nuclear magnetic resonance (NMR), high-
18
19 resolution transmission electron microscopy (HR-TEM), and electrochemical dilatometry.
20
21
22

23
24 The theoretical reaction of a SiO negative electrode was reported as follows [28,
25
26 29,51]:
27
28
29
30
31



37 According to Eq. (1), the initial charge and discharge capacities and initial coulombic
38
39 efficiency are theoretically calculated as 2615 mA h g⁻¹, 2007 mA h g⁻¹, and 76.7%,
40
41 respectively. However, as understood from Table 1, the reported values for SiO negative
42
43 electrodes differ among researchers. In addition, the reaction potentials observed as
44
45 potential plateaus in the potential-charge curves and capacity peaks in voltammograms
46
47 also differ between reports [34,52]. Consequently, the nature of the electrochemical
48
49 characteristics of SiO has not yet been sufficiently clarified. Although Yang et al. have
50
51 provided a thermodynamic analysis of the reaction potentials of a SiO electrode [53],
52
53 their calculations are not entirely reliable because they do not take into account the Gibbs
54
55 phase rule that is indispensable for the evaluation of the equilibrium.
56
57
58
59
60
61
62
63
64
65

1
2
3 In this paper, the reactions for a SiO negative electrode are thermodynamically
4
5 evaluated. Firstly, the Li–Si–O system is investigated on the basis of the construction of
6
7 the ternary phase diagram according to the Gibbs phase rule, in which the number of
8
9 degrees of freedom at a fixed temperature can be expressed as:

$$f = C - P + 1, \quad (2)$$

10
11
12
13
14
15
16
17
18
19 where f stands for the number of degrees of freedom, C is the number of components, and
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
66
67
68
69
70
71
72
73
74
75
76
77
78
79
80
81
82
83
84
85
86
87
88
89
90
91
92
93
94
95
96
97
98
99
100
101
102
103
104
105
106
107
108
109
110
111
112
113
114
115
116
117
118
119
120
121
122
123
124
125
126
127
128
129
130
131
132
133
134
135
136
137
138
139
140
141
142
143
144
145
146
147
148
149
150
151
152
153
154
155
156
157
158
159
160
161
162
163
164
165
166
167
168
169
170
171
172
173
174
175
176
177
178
179
180
181
182
183
184
185
186
187
188
189
190
191
192
193
194
195
196
197
198
199
200
201
202
203
204
205
206
207
208
209
210
211
212
213
214
215
216
217
218
219
220
221
222
223
224
225
226
227
228
229
230
231
232
233
234
235
236
237
238
239
240
241
242
243
244
245
246
247
248
249
250
251
252
253
254
255
256
257
258
259
260
261
262
263
264
265
266
267
268
269
270
271
272
273
274
275
276
277
278
279
280
281
282
283
284
285
286
287
288
289
290
291
292
293
294
295
296
297
298
299
300
301
302
303
304
305
306
307
308
309
310
311
312
313
314
315
316
317
318
319
320
321
322
323
324
325
326
327
328
329
330
331
332
333
334
335
336
337
338
339
340
341
342
343
344
345
346
347
348
349
350
351
352
353
354
355
356
357
358
359
360
361
362
363
364
365
366
367
368
369
370
371
372
373
374
375
376
377
378
379
380
381
382
383
384
385
386
387
388
389
390
391
392
393
394
395
396
397
398
399
400
401
402
403
404
405
406
407
408
409
410
411
412
413
414
415
416
417
418
419
420
421
422
423
424
425
426
427
428
429
430
431
432
433
434
435
436
437
438
439
440
441
442
443
444
445
446
447
448
449
450
451
452
453
454
455
456
457
458
459
460
461
462
463
464
465
466
467
468
469
470
471
472
473
474
475
476
477
478
479
480
481
482
483
484
485
486
487
488
489
490
491
492
493
494
495
496
497
498
499
500
501
502
503
504
505
506
507
508
509
510
511
512
513
514
515
516
517
518
519
520
521
522
523
524
525
526
527
528
529
530
531
532
533
534
535
536
537
538
539
540
541
542
543
544
545
546
547
548
549
550
551
552
553
554
555
556
557
558
559
560
561
562
563
564
565
566
567
568
569
570
571
572
573
574
575
576
577
578
579
580
581
582
583
584
585
586
587
588
589
590
591
592
593
594
595
596
597
598
599
600
601
602
603
604
605
606
607
608
609
610
611
612
613
614
615
616
617
618
619
620
621
622
623
624
625
626
627
628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643
644
645
646
647
648
649
650
651
652
653
654
655
656
657
658
659
660
661
662
663
664
665
666
667
668
669
670
671
672
673
674
675
676
677
678
679
680
681
682
683
684
685
686
687
688
689
690
691
692
693
694
695
696
697
698
699
700
701
702
703
704
705
706
707
708
709
710
711
712
713
714
715
716
717
718
719
720
721
722
723
724
725
726
727
728
729
730
731
732
733
734
735
736
737
738
739
740
741
742
743
744
745
746
747
748
749
750
751
752
753
754
755
756
757
758
759
760
761
762
763
764
765
766
767
768
769
770
771
772
773
774
775
776
777
778
779
780
781
782
783
784
785
786
787
788
789
790
791
792
793
794
795
796
797
798
799
800
801
802
803
804
805
806
807
808
809
810
811
812
813
814
815
816
817
818
819
820
821
822
823
824
825
826
827
828
829
830
831
832
833
834
835
836
837
838
839
840
841
842
843
844
845
846
847
848
849
850
851
852
853
854
855
856
857
858
859
860
861
862
863
864
865
866
867
868
869
870
871
872
873
874
875
876
877
878
879
880
881
882
883
884
885
886
887
888
889
890
891
892
893
894
895
896
897
898
899
900
901
902
903
904
905
906
907
908
909
910
911
912
913
914
915
916
917
918
919
920
921
922
923
924
925
926
927
928
929
930
931
932
933
934
935
936
937
938
939
940
941
942
943
944
945
946
947
948
949
950
951
952
953
954
955
956
957
958
959
960
961
962
963
964
965
966
967
968
969
970
971
972
973
974
975
976
977
978
979
980
981
982
983
984
985
986
987
988
989
990
991
992
993
994
995
996
997
998
999
1000
1001
1002
1003
1004
1005
1006
1007
1008
1009
1010
1011
1012
1013
1014
1015
1016
1017
1018
1019
1020
1021
1022
1023
1024
1025
1026
1027
1028
1029
1030
1031
1032
1033
1034
1035
1036
1037
1038
1039
1040
1041
1042
1043
1044
1045
1046
1047
1048
1049
1050
1051
1052
1053
1054
1055
1056
1057
1058
1059
1060
1061
1062
1063
1064
1065
1066
1067
1068
1069
1070
1071
1072
1073
1074
1075
1076
1077
1078
1079
1080
1081
1082
1083
1084
1085
1086
1087
1088
1089
1090
1091
1092
1093
1094
1095
1096
1097
1098
1099
1100
1101
1102
1103
1104
1105
1106
1107
1108
1109
1110
1111
1112
1113
1114
1115
1116
1117
1118
1119
1120
1121
1122
1123
1124
1125
1126
1127
1128
1129
1130
1131
1132
1133
1134
1135
1136
1137
1138
1139
1140
1141
1142
1143
1144
1145
1146
1147
1148
1149
1150
1151
1152
1153
1154
1155
1156
1157
1158
1159
1160
1161
1162
1163
1164
1165
1166
1167
1168
1169
1170
1171
1172
1173
1174
1175
1176
1177
1178
1179
1180
1181
1182
1183
1184
1185
1186
1187
1188
1189
1190
1191
1192
1193
1194
1195
1196
1197
1198
1199
1200
1201
1202
1203
1204
1205
1206
1207
1208
1209
1210
1211
1212
1213
1214
1215
1216
1217
1218
1219
1220
1221
1222
1223
1224
1225
1226
1227
1228
1229
1230
1231
1232
1233
1234
1235
1236
1237
1238
1239
1240
1241
1242
1243
1244
1245
1246
1247
1248
1249
1250
1251
1252
1253
1254
1255
1256
1257
1258
1259
1260
1261
1262
1263
1264
1265
1266
1267
1268
1269
1270
1271
1272
1273
1274
1275
1276
1277
1278
1279
1280
1281
1282
1283
1284
1285
1286
1287
1288
1289
1290
1291
1292
1293
1294
1295
1296
1297
1298
1299
1300
1301
1302
1303
1304
1305
1306
1307
1308
1309
1310
1311
1312
1313
1314
1315
1316
1317
1318
1319
1320
1321
1322
1323
1324
1325
1326
1327
1328
1329
1330
1331
1332
1333
1334
1335
1336
1337
1338
1339
1340
1341
1342
1343
1344
1345
1346
1347
1348
1349
1350
1351
1352
1353
1354
1355
1356
1357
1358
1359
1360
1361
1362
1363
1364
1365
1366
1367
1368
1369
1370
1371
1372
1373
1374
1375
1376
1377
1378
1379
1380
1381
1382
1383
1384
1385
1386
1387
1388
1389
1390
1391
1392
1393
1394
1395
1396
1397
1398
1399
1400
1401
1402
1403
1404
1405
1406
1407
1408
1409
1410
1411
1412
1413
1414
1415
1416
1417
1418
1419
1420
1421
1422
1423
1424
1425
1426
1427
1428
1429
1430
1431
1432
1433
1434
1435
1436
1437
1438
1439
1440
1441
1442
1443
1444
1445
1446
1447
1448
1449
1450
1451
1452
1453
1454
1455
1456
1457
1458
1459
1460
1461
1462
1463
1464
1465
1466
1467
1468
1469
1470
1471
1472
1473
1474
1475
1476
1477
1478
1479
1480
1481
1482
1483
1484
1485
1486
1487
1488
1489
1490
1491
1492
1493
1494
1495
1496
1497
1498
1499
1500
1501
1502
1503
1504
1505
1506
1507
1508
1509
1510
1511
1512
1513
1514
1515
1516
1517
1518
1519
1520
1521
1522
1523
1524
1525
1526
1527
1528
1529
1530
1531
1532
1533
1534
1535
1536
1537
1538
1539
1540
1541
1542
1543
1544
1545
1546
1547
1548
1549
1550
1551
1552
1553
1554
1555
1556
1557
1558
1559
1560
1561
1562
1563
1564
1565
1566
1567
1568
1569
1570
1571
1572
1573
1574
1575
1576
1577
1578
1579
1580
1581
1582
1583
1584
1585
1586
1587
1588
1589
1590
1591
1592
1593
1594
1595
1596
1597
1598
1599
1600
1601
1602
1603
1604
1605
1606
1607
1608
1609
1610
1611
1612
1613
1614
1615
1616
1617
1618
1619
1620
1621
1622
1623
1624
1625
1626
1627
1628
1629
1630
1631
1632
1633
1634
1635
1636
1637
1638
1639
1640
1641
1642
1643
1644
1645
1646
1647
1648
1649
1650
1651
1652
1653
1654
1655
1656
1657
1658
1659
1660
1661
1662
1663
1664
1665
1666
1667
1668
1669
1670
1671
1672
1673
1674
1675
1676
1677
1678
1679
1680
1681
1682
1683
1684
1685
1686
1687
1688
1689
1690
1691
1692
1693
1694
1695
1696
1697
1698
1699
1700
1701
1702
1703
1704
1705
1706
1707
1708
1709
1710
1711
1712
1713
1714
1715
1716
1717
1718
1719
1720
1721
1722
1723
1724
1725
1726
1727
1728
1729
1730
1731
1732
1733
1734
1735
1736
1737
1738
1739
1740
1741
1742
1743
1744
1745
1746
1747
1748
1749
1750
1751
1752
1753
1754
1755
1756
1757
1758
1759
1760
1761
1762
1763
1764
1765
1766
1767
1768
1769
1770
1771
1772
1773
1774
1775
1776
1777
1778
1779
1780
1781
1782
1783
1784
1785
1786
1787
1788
1789
1790
1791
1792
1793
1794
1795
1796
1797
1798
1799
1800
1801
1802
1803
1804
1805
1806
1807
1808
1809
1810
1811
1812
1813
1814
1815
1816
1817
1818
1819
1820
1821
1822
1823
1824
1825
1826
1827
1828
1829
1830
1831
1832
1833
1834
1835
1836
1837
1838
1839
1840
1841
1842
1843
1844
1845
1846
1847
1848
1849
1850
1851
1852
1853
1854
1855
1856
1857
1858
1859
1860
1861
1862
1863
1864
1865
1866
1867
1868
1869
1870
1871
1872
1873
1874
1875
1876
1877
1878
1879
1880
1881
1882
1883
1884
1885
1886
1887
1888
1889
1890
1891
1892
1893
1894
1895
1896
1897
1898
1899
1900
1901
1902
1903
1904
1905
1906
1907
1908
1909
1910
1911
1912
1913
1914
1915
1916
1917
1918
1919
1920
1921
1922
1923
1924
1925
1926
1927
1928
1929
1930
1931
1932
1933
1934
1935
1936
1937
1938
1939
1940
1941
1942
1943
1944
1945
1946
1947
1948
1949
1950
1951
1952
1953
1954
1955
1956
1957
1958
1959
1960
1961
1962
1963
1964
1965
1966
1967
1968
1969
1970
1971
1972
1973
1974
1975
1976
1977
1978
1979
1980
1981
1982
1983
1984
1985
1986
1987
1988
1989
1990
1991
1992
1993
1994
1995
1996
1997
1998
1999
2000
2001
2002
2003
2004
2005
2006
2007
2008
2009
2010
2011
2012
2013
2014
2015
2016
2017
2018
2019
2020
2021
2022
2023
2024
2025
2026
2027
2028
2029
2030
2031
2032
2033
2034
2035
2036
2037
2038
2039
2040
2041
2042
2043
2044
2045
2046
2047
2048
2049
2050
2051
2052
2053
2054
2055
2056
2057
2058
2059
2060
2061
2062
2063
2064
2065
2066
2067
2068
2069
2070
2071
2072
2073
2074
2075
2076
2077
2078
2079
2080
2081
2082
2083
2084
2085
2086
2087
2088
2089
2090
2091
2092
2093
2094
2095
2096
2097
2098
2099
2100
2101
2102
2103
2104
2105
2106
2107
2108
2109
2110
2111
2112
2113
2114
2115
2116
2117
2118
2119
2120
2121
2122
2123
2124
2125
2126
2127
2128
2129
2130
2131
2132
2133
2134
2135
2136
2137
2138
2139
2140
2141
2142
2143
2144
2145
2146
2147
2148
2149
2150
2151
2152
2153
2154
2155
2156
2157
2158
2159
2160
2161
2162
2163
2164
2165
2166
2167
2168
2169
2170
2171
2172
2173
2174
2175
2176
2177
2178
2179
2180
2181
2182
2183
2184
2185
2186
2187
2188
2189
2190
2191
2192
2193
2194
2195
2196
2197
2198
2199
2200
2201
2202
2203
2204
2205
2206
2207
2208
2209
2210
2211
2212
2213
2214
2215

1
2
3 diagram is constructed at 298 K from the reported thermodynamic data of the compounds.
4
5 Furthermore, the phase change and equilibrium potentials in the Li insertion/extraction
6
7 reactions for a SiO negative electrode are analyzed. Against this background, the
8
9 dependence of battery performance on charge/discharge conditions is discussed.
10
11
12
13
14

15 2-1. Construction of the ternary phase diagram for the Li–Si–O system

16
17 In the Li–Si–O system at 298 K, the compounds including solid Li, solid Si, and O₂
18
19 gas (listed in Table 2) exist. Only solid Li₂O and SiO₂ are the stable phases in the binary
20
21 systems for the Li–O [4,56] and Si–O [4,57,58] systems, respectively. According to the
22
23 quasi-binary phase diagrams for the Li₂O–SiO₂ system [59–61], solid Li₂Si₂O₅, Li₂SiO₃,
24
25 and Li₄SiO₄ are stable phases among the lithium silicates. In the Li–Si system, four
26
27 compounds (Li₁₂Si₇, Li₇Si₃, Li₁₃Si₄, and Li₂₂Si₅) are reported [62]. These diagrams
28
29 indicate a negligible composition range for these compounds deriving from the vacancy
30
31 and solubility.
32
33
34
35
36

37 The thermodynamic data for these compounds in the Li–Si–O system (acquired
38
39 from the thermodynamic software HSC Chemistry[®] ver. 5.1 [63]) are also listed in Table
40
41 2 [64–72]. Because SiO has no stable crystalline phase at ambient temperature and
42
43 pressure, its data are not reported. Concerning the thermodynamic data for the Li–Si
44
45 compounds, there were several reports that used electromotive force (emf) measurements
46
47 [73–77]. Their data were recalculated by Demidov et al. [78] and Braga et al. [79] using
48
49 two assessment methods, which were adopted and updated for the construction of the
50
51 current phase diagram for the Li–Si system [62], respectively. In this study, the standard
52
53 Gibbs energies of formation at 298 K in the first assessment method in the report by
54
55 Braga et al. [79] were applied. The phase diagram was constructed by Chesta ver. 2.22,
56
57
58
59
60
61
62
63
64
65

which is a free software supplied by Kyoto University for creating chemical potential diagrams for multi-component systems [80].

Table 2 Thermodynamic data for Li–Si–O system at 298 K used for the calculation.

Formula	Compound			Standard Gibbs energy, $G^\circ / \text{kJ mol}^{-1}$	Standard Gibbs energy of formation, $\Delta G_f^\circ / \text{kJ mol}^{-1}$	Ref
	Li	Si	O			
Li	1	0	0	–8.7	0	[64–66]
Si	0	1	0	–5.6	0	[67]
O ₂	0	0	2	–61.1	0	[66,68]
Li ₁₂ Si ₇	12	7	0	–570.5	–426.9	Calculated from [79].
Li ₇ Si ₃	7	3	0	–312.7	–235.0	
Li ₁₃ Si ₄	13	4	0	–525.6	–390.1	
Li ₂₂ Si ₅	22	5	0	–758.8	–539.4	
Li ₂ O	2	0	1	–609.1	–561.2	[64,69,70]
SiO ₂	0	1	2	–923.2	–856.5	[71]
Li ₂ Si ₂ O ₅	2	2	5	–2598.3	–2416.9	[64]
Li ₅ SiO ₅	2	1	3	–1673.4	–1558.8	[67]
Li ₄ SiO ₄	4	1	4	–2366.2	–2203.6	[72]

Figure 1(a) shows the ternary phase diagram for the Li–Si–O system at 298 K calculated from the reported thermodynamic data in Table 2. As can be seen, the large triangle consists of Li, Si, and 1/2 O₂ vertices; the diagram is divided into small triangles, except for the upper part. According to the Gibbs phase rule at a fixed temperature indicated by Eq. (2) and the value of $C = 3$ (Li, Si, and O) in the system, three condensed phases indicated as the vertices are equilibrated ($f = 0$, $P = 4$ by three phases and gas). On the other hand, at the upper part of the diagram, the triangle of Li₂O–SiO₂–O₂ is not divided into small triangles. In the Li₂O–SiO₂–O₂ system, the value of P is 3 because two condensed phases and the gas phase exist. Thus, the value of $f = 1$ indicates that the system has one variable, such as the partial pressure of oxygen (p_{O_2}).

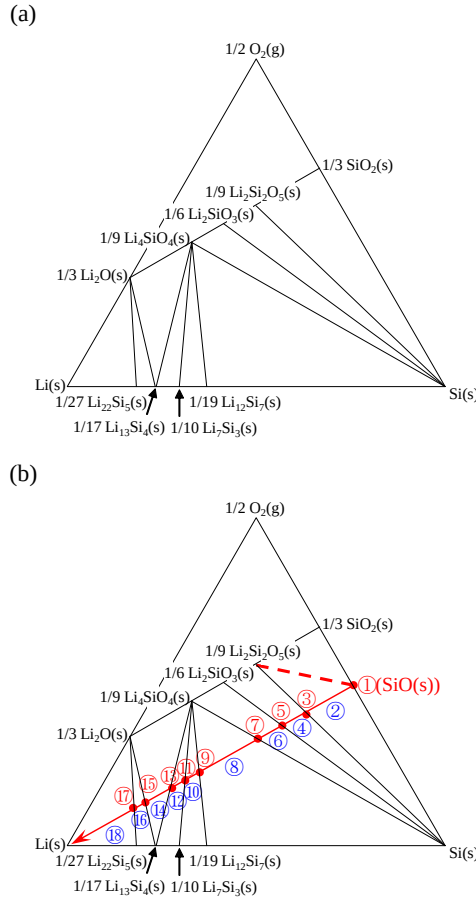


Fig. 1 (a) Calculated ternary phase diagram for the Li-Si-O system at 298 K.
 (b) Transition of formed phases during the Li insertion for a SiO negative electrode at 298 K shown in the ternary phase diagram for Li-Si-O system.

2-2. Phase change and equilibrium potential for a SiO electrode

Because the position in the ternary phase diagram indicates the nominal composition of the system, the phase change during the electrochemical Li insertion/extraction reaction of a SiO electrode can be discussed based on the equilibrium phases. Assuming that there are no ionic species containing Si and O related to the electrode reactions, the electrode potential, E , with respect to the standard potential of Li is a function of the Li activity in the electrode:




$$E = \frac{RT}{F} \ln \frac{a_{\text{Li}}}{a_{\text{Li}^+}} = \frac{2.303RT}{F} \log a_{\text{Li}}, \quad (4)$$

where R is the gas constant, T is the absolute temperature, F is the Faraday constant, and a_{Li} and a_{Li^+} are the activities of Li and Li^+ ions, respectively. Here, the standard states of Li and Li^+ ions are pure solid Li and ion concentration dispersed in the electrolyte, respectively. It should be mentioned that the calculation is based on the following assumptions, which are inherent to the discussion of chemical equilibria: the composition of the electrode is homogeneous; the compounds are electrochemically active with Li; and the electrode potential is determined by the activity of Li in the electrode, as expressed by Eq. (4). Another assumption is that the chemical potentials of Si and O_2 in the SiO phase are the same at the equilibrium of Si and SiO_2 . The three phases at the vertices are equilibrated when a nominal composition is located within the triangle. The electrode potential takes on a fixed value when the system has zero degrees of freedom according to Eq. (2). Another equilibrium is a two-phase equilibrium whose composition is positioned along a line. The two phases at the side ends are equilibrated with one degree of freedom ($f = 1$) – i.e., the electrode potential changes.

When the Li insertion reaction occurs for a SiO electrode, the change of nominal composition is expressed as the red arrow drawn from SiO to Li in Fig. 1(b). The calculation suggests the formation of $\text{Li}_2\text{Si}_2\text{O}_5/\text{Si}/\text{SiO}_2$ in the initial reaction of SiO. In the actual reaction, SiO_2 is not formed and $\text{Li}_2\text{Si}_2\text{O}_5/\text{SiO}/\text{Si}$ are equilibrated as the red broken line becomes a side of the triangle.

The formation of Li–Si–O compounds ($\text{Li}_a\text{Si}_b\text{O}_c$, where a , b , and c are stoichiometric ratios) from metallic Li and Si as well as O_2 gas at atmospheric pressure can be expressed as follows:



The chemical potentials of Li, Si, and O₂ can be expressed as a function of the standard Gibbs energy of formation of Li_aSi_bO_c ($\Delta G_f^\circ(\text{Li}_a\text{Si}_b\text{O}_c)$):

$$\begin{aligned} & a (G^\circ(\text{Li}) + RT \ln a_{\text{Li}}) + b (G^\circ(\text{Si}) + RT \ln a_{\text{Si}}) + c/2 (G^\circ(\text{O}_2) + RT \ln p_{\text{O}_2}) \\ & = G^\circ(\text{Li}_a\text{Si}_b\text{O}_c), \end{aligned} \quad (6)$$

$$\begin{aligned} & 2.303RT (a \log a_{\text{Li}} + b \log a_{\text{Si}} + c/2 \log p_{\text{O}_2}) \\ & = G^\circ(\text{Li}_a\text{Si}_b\text{O}_c) - (a G^\circ(\text{Li}) + b G^\circ(\text{Si}) + c/2 G^\circ(\text{O}_2)) \\ & = \Delta G_f^\circ(\text{Li}_a\text{Si}_b\text{O}_c). \end{aligned} \quad (7)$$

Here, $G^\circ(\text{Li})$, $G^\circ(\text{Si})$, and $G^\circ(\text{O}_2)$ are the standard Gibbs energy of Li, Si, and O₂, respectively, and a_{Si} is the activity of Si with respect to pure solid Si.

As shown in Eq. (7), a_{Li} , a_{Si} , and p_{O_2} are variables under the existence of a single phase only. On the other hand, they take on fixed values at the equilibrium state of three phases where the standard Gibbs energies of these compounds simultaneously satisfy Eq. (7). By combining the two compounds, the chemical potentials at the Li₂Si₂O₅/Si/SiO₂ equilibrium (region ② in Fig. 1(b)) can be calculated in Eq. (8):

$$2.303RT \begin{pmatrix} 2 & 2 & \frac{5}{2} \\ 0 & 1 & 0 \\ 0 & 1 & 1 \end{pmatrix} \begin{pmatrix} \log a_{\text{Li}} \\ \log a_{\text{Si}} \\ \log p_{\text{O}_2} \end{pmatrix} = \begin{pmatrix} \Delta G_f^\circ(\text{Li}_2\text{Si}_2\text{O}_5) \\ \Delta G_f^\circ(\text{Si}) \\ \Delta G_f^\circ(\text{SiO}_2) \end{pmatrix}. \quad (8)$$

Namely, $\log a_{\text{Li}}$, $\log a_{\text{Si}}$, and $\log p_{\text{O}_2}$ are calculated by Eq. (9) as -24.2 , 0 , and -150.1 , respectively, from the values of ΔG_f° for $\text{Li}_2\text{Si}_2\text{O}_5$, Si , and SiO_2 listed in Table 2. The electrode potential at this equilibrium is obtained to be 1.428 V vs. Li/Li^+ by Eq. (4).

With the progress of Li insertion, the nominal composition reaches the $\text{Li}_2\text{Si}_2\text{O}_5/\text{Si}$ two-phase equilibrium (point ③). The potential shifts to a negative value during the two-phase equilibrium. Further Li insertion introduces the reaction state of the $\text{Li}_2\text{Si}_2\text{O}_5/\text{Li}_2\text{SiO}_3/\text{Si}$ equilibrium (region ④). The chemical potentials and electrode potential can be calculated in the same manner as in the previous paragraph using Eqs. (4) and (8). At the end, the system reaches the $\text{Li}/\text{Li}_2\text{O}/\text{Li}_{22}\text{Si}_5$ equilibrium (region ⑧). The equilibrium phases and electrode potentials during the Li insertion of a SiO electrode are summarized in Table 3.


Table 3 Equilibrium phases and electrode potentials during the Li insertion for a SiO negative electrode at 298 K.

	Equilibrium phases			Activity or pressure				Equilibrium potential, E_e / V (vs. Li^+/Li)
				$\log p_{\text{O}_2}$	$\log a_{\text{Si}}$	$\log a_{\text{Li}}$	a_{Li}	
①	Si	SiO_2						
②	Si	SiO_2	$\text{Li}_2\text{Si}_2\text{O}_5$	-150.1	0	-24.2	6.9×10^{-25}	1.428
③	Si	$\text{Li}_2\text{Si}_2\text{O}_5$						↓
④	Si	$\text{Li}_2\text{Si}_2\text{O}_5$	Li_2SiO_3	-150.4	0	-23.8	1.6×10^{-24}	1.406
⑤	Si	Li_2SiO_3						↓
⑥	Si	Li_2SiO_3	Li_4SiO_4	-160.2	0	-16.5	3.4×10^{-17}	0.973
⑦	Si	Li_4SiO_4						↓
⑧	Si	$\text{Li}_{12}\text{Si}_7$	Li_4SiO_4	-180.6	0	-6.24	5.8×10^{-17}	0.368
⑨	$\text{Li}_{12}\text{Si}_7$	Li_4SiO_4						↓
⑩	$\text{Li}_{12}\text{Si}_7$	Li_7Si_3	Li_4SiO_4	-182.1	-2.27	-4.91	1.2×10^{-5}	0.290
⑪	Li_7Si_3	Li_4SiO_4						↓
⑫	Li_7Si_3	$\text{Li}_{13}\text{Si}_4$	Li_4SiO_4	-183.2	-5.17	-3.67	2.1×10^{-4}	0.217
⑬	$\text{Li}_{13}\text{Si}_4$	Li_4SiO_4						↓
⑭	$\text{Li}_{13}\text{Si}_4$	Li_4SiO_4	Li_2O	-183.3	-6.21	-3.35	4.5×10^{-4}	0.198
⑮	$\text{Li}_{13}\text{Si}_4$	Li_2O						↓
⑯	$\text{Li}_{13}\text{Si}_4$	$\text{Li}_{22}\text{Si}_5$	Li_2O	-190.4	-12.0	-1.58	2.7×10^{-2}	0.093
⑰	$\text{Li}_{22}\text{Si}_5$	Li_2O						↓
⑱	$\text{Li}_{22}\text{Si}_5$	Li_2O	Li	-196.7	-18.9	0	1	0


Figure 1(b) provides information on the reaction pathway for a SiO electrode. The reaction can be divided into three stages. (1) At the initial stage of the reaction, lithium silicates ($\text{Li}_2\text{Si}_2\text{O}_5$, Li_2SiO_3 , and Li_4SiO_4) are formed together with metallic Si (from point ① to point ⑦). (2) Secondly, the formed metallic Si reacts with Li to form Li–Si alloys ($\text{Li}_{12}\text{Si}_7$, Li_7Si_3 , and $\text{Li}_{13}\text{Si}_4$) that are in equilibrium with Li_4SiO_4 (from point ⑦ to point ⑬). (3) Thirdly, Li_4SiO_4 is decomposed to form Li_2O and $\text{Li}_{13}\text{Si}_4$. (4) Further Li insertion produces $\text{Li}_{22}\text{Si}_5$ from $\text{Li}_{13}\text{Si}_4$ (from point ⑮ to point ⑰). (5) Finally, metallic Li is deposited (after point ⑱). Steps (1) and (2) proceed in accordance with the various reports on the formation of Li–Si alloys in a lithium silicate matrix [21,33,34].

The calculated phase diagram also explains two other reactions. One is the electrochemical reaction of a SiO_2 electrode with Li. In spite of the strong insulating


characteristics of SiO₂, the Li insertion reaction forms lithium silicates in the initial stage in the same manner as the SiO electrode; from this point the alloying reaction of Si demonstrates a reversible capacity, as shown in Fig. 2(a). The formation of lithium silicates agrees with the previous reports [28,46–48,50]. The other reaction is the electrochemical inactiveness of Li₄SiO₄ as reported in Ref. [28], in which no Li dissolution reaction occurs for Li₄SiO₄, even at the positive potential of 4.0 V vs. Li/Li⁺. As shown in Fig. 2(b), the Li extraction reaction of Li₄SiO₄ leads to the formation of O₂ gas and other silicates with low Li concentration.



Therefore, Li₄SiO₄ is expected to be stable even at very positive potentials and until the reaction of O₂ gas evolution (reaction (9)). The high stability of lithium silicates suggests that their formation takes on an irreversible capacity, which enables the stable charge/discharge reactions as a matrix of nano crystals of Li–Si alloys. Namely, the electrode acts as a mixture of irreversible Li₄SiO₄ and reversible Li–Si alloys.



According to the previous reports [28,29,51], the alloy formation instead of the composition of Li₂₂Si₅ proceeds as a reversible reaction.



On the other hand, the thermodynamic calculations suggest that the reversible reaction occurs between Si and $\text{Li}_{13}\text{Si}_4$ with the Li_4SiO_4 matrix. When alloying reaction is utilized for $\text{Li}_{22}\text{Si}_5$ composition, the decomposition of Li_4SiO_4 and formation of Li_2O are inevitable.

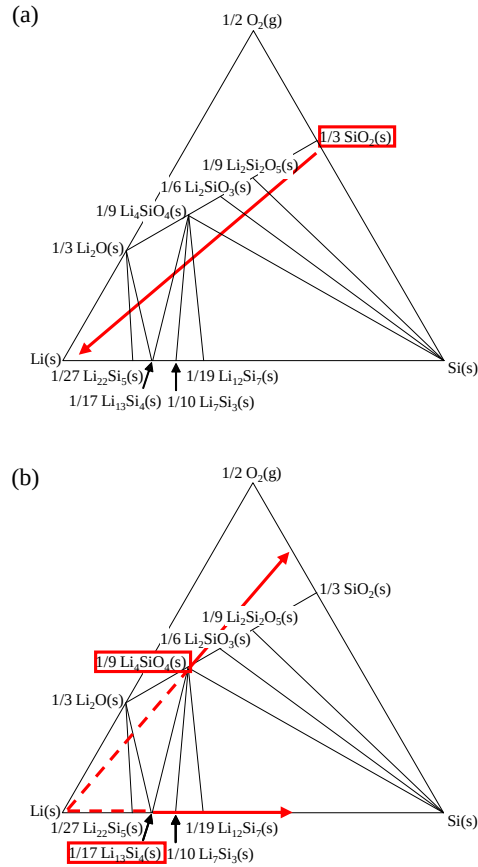


Fig. 2 Reaction pathway during (a) the Li insertion for a SiO_2 negative electrode and (b) the Li desorption for a Li_4SiO_4 electrode at 298 K shown in the ternary phase diagram for Li-Si-O system.

According to the calculated potentials in Table 3, the theoretical potential shift during the Li insertion reaction for a SiO_2 electrode (with equilibrium maintained) is shown in Fig. 3(a). In practice, because the reaction does not proceed at equilibrium states, a similar shift can be obtained at an extremely slow charge rate. As explained

1
2
3 above, the electrode potential remains fixed at the three-phase equilibrium, which is
4 represented by the inside of the triangles according to the Gibbs phase rule. By way of
5 contrast, the potential changes at the two-phase equilibrium, which is represented by the
6 sides of the triangles. In the Li insertion reaction, the potential plateaus corresponding to
7 the formation of lithium silicates are initially observed around 1.4 V (point ②–④) and
8
9
10
11
12
13
14
15
16
17 1.0 V (⑥) vs. Li/Li⁺ with a capacity of 608 mA h g⁻¹. At this stage, the formation of Li–
18
19
20
21 Si alloys starts at 0.37 V (⑧) and continues until 0.22 V (⑫) with a capacity of 1482 mA
22
23 h g⁻¹. At state ⑭, the Li₄SiO₄ phase is decomposed into Li₂O and Li₁₃Si₄. Then, the Li–Si
24
25 alloy formation is finalized with the composition of Li₂₂Si₅ (point ⑰).

26
27
28
29 The relationship among the amount of inserted Li, the charge capacity, and the
30
31 reaction equation is theoretically summarized in Table 4. In the practical electrode, SEI
32
33 (solid-electrolyte interface) formation can also occur, especially at negative potentials. In
34
35 Ref. [23], the potential plateau at 0.8 V in the initial charge was ascribed to SEI
36
37 formation. The calculated potential shift in Fig. 3 strongly suggests that the plateau
38
39 corresponds to the formation of lithium silicates, as well as the deviation due to the
40
41 overvoltage for the reaction and the ohmic drop. Electrode behaviors reported by other
42
43 researchers, such as the differential capacity peaks [27,31], can be also explained by the
44
45 theoretical potential of as lithium silicate formation at 1.4 V and 1.0 V.
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

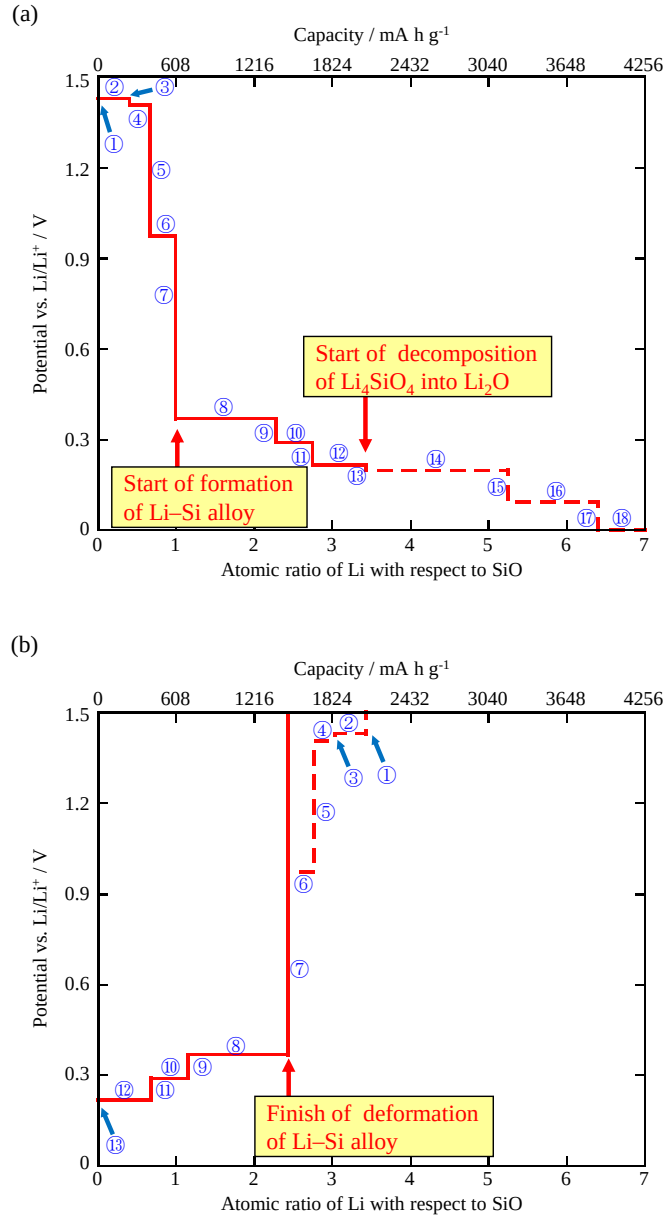


Fig. 3 Transition of equilibrium electrode potential during the Li (a) insertion and (b) desertion after the formation of $\text{Li}_{13}\text{Si}_4$ for a SiO negative electrode at 298 K shown in the ternary phase diagram for Li-Si-O system.

Figure 3(b) shows the equilibrium potential during the Li extraction reaction for a SiO electrode, which occurs after Li insertion and continues until the completion of the $\text{Li}_{13}\text{Si}_4$ formation (point 13). A reversible capacity of 1482 mA h g^{-1} with 70.9% coulombic efficiency from the Li-Si alloys appears until the reaction reaches the

formation of Si and Li_4SiO_4 (point ⑦). Further Li insertion indicated by the broken line does not occur because Li_4SiO_4 is inactive, as reported in Ref. [28]. When Li insertion further proceeds to form Li_2O , the discharge capacity and coulombic efficiency increase in spite of the decomposition of Li_4SiO_4 (until points ⑬ and ⑰). The amount of extracted Li, the discharge capacity, and the coulombic efficiency corresponding to each reaction are listed in Table 5.

Table 4 The calculated reactions for the Li insertion of a SiO negative electrode at 298 K.

	Reaction	Atomic ratio of Li with respect to SiO	Charge capacity, C_d / mA h g^{-1}
③	$5\text{SiO} + 2\text{Li}^+ + 2\text{e}^- \rightarrow 3\text{Si} + \text{Li}_3\text{Si}_2\text{O}_5$	0.40	243
⑤	$3\text{SiO} + 2\text{Li}^+ + 2\text{e}^- \rightarrow 2\text{Si} + \text{Li}_2\text{SiO}_3$	0.67	405
⑦	$4\text{SiO} + 4\text{Li}^+ + 4\text{e}^- \rightarrow 3\text{Si} + \text{Li}_4\text{SiO}_4$	1.00	608
⑨	$28\text{SiO} + 64\text{Li}^+ + 64\text{e}^- \rightarrow 3\text{Li}_{12}\text{Si}_7 + 7\text{Li}_4\text{SiO}_4$	2.29	1390
⑪	$12\text{SiO} + 33\text{Li}^+ + 33\text{e}^- \rightarrow 3\text{Li}_7\text{Si}_3 + 3\text{Li}_4\text{SiO}_4$	2.75	1672
⑬	$16\text{SiO} + 55\text{Li}^+ + 55\text{e}^- \rightarrow 3\text{Li}_{13}\text{Si}_4 + 4\text{Li}_4\text{SiO}_4$	3.44	2090
⑮	$4\text{SiO} + 21\text{Li}^+ + 21\text{e}^- \rightarrow \text{Li}_{13}\text{Si}_4 + 4\text{Li}_2\text{O}$	5.25	3192
⑰	$5\text{SiO} + 32\text{Li}^+ + 32\text{e}^- \rightarrow \text{Li}_{22}\text{Si}_5 + 5\text{Li}_2\text{O}$	6.40	3891

Table 5 The calculated reactions for the Li extraction of a SiO negative electrode at 298 K.

Charged state	Dis-charged state	Reaction	Atomic ratio of Li with respect to SiO	Discharge capacity, C_d / mA h g^{-1}	Coulombic efficiency (%)
⑬	⑪	$3\text{Li}_{13}\text{Si}_4 + 4\text{Li}_4\text{SiO}_4 \rightarrow 4\text{Li}_7\text{Si}_3 + 4\text{Li}_4\text{SiO}_4 + 11\text{Li}^+ + 11\text{e}^-$	0.69	418	20.0
	⑨	$21\text{Li}_{13}\text{Si}_4 + 28\text{Li}_4\text{SiO}_4 \rightarrow 12\text{Li}_{12}\text{Si}_7 + 28\text{Li}_4\text{SiO}_4 + 129\text{Li}^+ + 129\text{e}^-$	1.15	700	33.5
		$3\text{Li}_{13}\text{Si}_4 + 4\text{Li}_4\text{SiO}_4 \rightarrow 12\text{Si} + 4\text{Li}_4\text{SiO}_4 + 39\text{Li}^+ + 39\text{e}^-$	2.44	1482	70.9
⑮	⑦	$\text{Li}_{13}\text{Si}_4 + 4\text{Li}_2\text{O} \rightarrow 3\text{Si} + \text{Li}_4\text{SiO}_4 + 17\text{Li}^+ + 17\text{e}^-$	4.25	2584	81.0
⑰		$4\text{Li}_{13}\text{Si}_4 + 20\text{Li}_2\text{O} \rightarrow 15\text{Si} + 5\text{Li}_4\text{SiO}_4 + 108\text{Li}^+ + 108\text{e}^-$	5.40	3283	84.4

2-3. Relationship between the charge/discharge conditions and performances for SiO electrodes

On the basis of the ternary phase diagram for the Li–Si–O system at 298 K (Fig. 1) and the theoretical potential shift during the Li insertion/extraction reaction for a SiO electrode (Fig. 3), the optimum conditions and the key factors for high capacity and impressive cycle performance herein discussed.

The analysis of the previous reports listed in Table 1 indicates that the initial discharge capacity is not necessarily dependent on the initial charge capacity. For example, a discharge capacity of around 1300 mA h g⁻¹ is obtained even at charge capacities of 1750 mA h g⁻¹ [30] and 2200–2500 mA h g⁻¹ [19,22,27,32]. Furthermore, a discharge capacity of 1450 mA h g⁻¹ is obtained at charge capacities of 1950 mA h g⁻¹ [31] and 2700 mA h g⁻¹ [23]. Naturally, the initial coulombic efficiency is different between the reports. Table 1 also clarifies that Li₂O is formed as the intermediate phase in the reports of the higher charge capacity in addition to the lithium silicates [22,23,27,32].

The fact that the initial discharge capacity is not necessarily dependent on the initial charge capacity also explains the effects of Li₂O formation on discharge capacity. Whereas different initial discharge capacities are obtained as 1300 [22,27,32] and 1800 mA h g⁻¹ [28] even at the initial capacity around 2500 mA h g⁻¹, the discharge capacity remains low in case of Li₂O formation. However, according to Table 4, the atomic ratio of Li/SiO corresponding to Li₁₃Si₄ alloy formation is higher for Li₂O (i.e., 5.25) than for Li₄SiO₄ (i.e., 3.44). These values suggest that the discharge capacity after the charge and until Li₂O formation has a theoretically higher value, and indicates the degraded kinetics for Li₂O formation and/or lithium silicate decomposition while some research on Li conduction for Li₂O has been investigated [81]. The matrix roles of lithium silicates for Li conduction, expansion, relaxation, and electric contact are the key factors for high performance.

Consequently, the combination of the performance reported in the literature and the calculated ternary phase diagram indicates that the crucial charge/discharge condition consists of avoiding or minimizing the formation of Li_2O , which induces two negative effects concerning the low utilization of the inserted Li and the poor reaction kinetics.

3. Experimental

Amorphous SiO powder (Osaka Titanium technologies) with a mean diameter of $D_{50} = 4.8 \mu\text{m}$ was used. The preparation of disproportionated SiO powder was carried out by the thermal treatment of amorphous SiO powder. Amorphous SiO powder contained in an alumina crucible was placed in an Ar atmosphere in an electric furnace maintained at 1273 K or 1473 K for 5 h. As shown in the transmission electron microscope (TEM) images (JEOL, JEM-ARM200F) and X-ray diffraction (XRD) patterns (PANalytical, X'Pert Powder) in Fig. 4, Si nano clusters with a diameter smaller than 10 nm were formed in the SiO_2 matrix by the disproportionation of amorphous SiO.

For the preparation of SiO working electrodes, SiO powder (80 wt%) and Ketjen black (KB) as a conductive additive (5 wt%) were thoroughly mixed with polyimide (PI) as a binder (15 wt%). A slurry was prepared by adding N-methylpyrrolidinone as a solvent to the mixture. For comparison, a slurry consisted of 25wt%-KB and 75wt%-PI was also prepared. The obtained slurry was cast onto a sheet of copper foil, and predried at 393 K in air to remove the solvent. The electrodes were obtained after a final dry at 623 K under a vacuum for 1 h in an electric furnace. The loading mass density fell in the range of $3.5\text{--}4.5 \text{ mg cm}^{-2}$. The SiO electrode was prepared by stamping the copper foil into a circle with an area of 1 cm^2 . Two-electrode 2032-type coin cells – with the SiO and lithium metal as working and counter electrodes, respectively – were assembled in an Ar

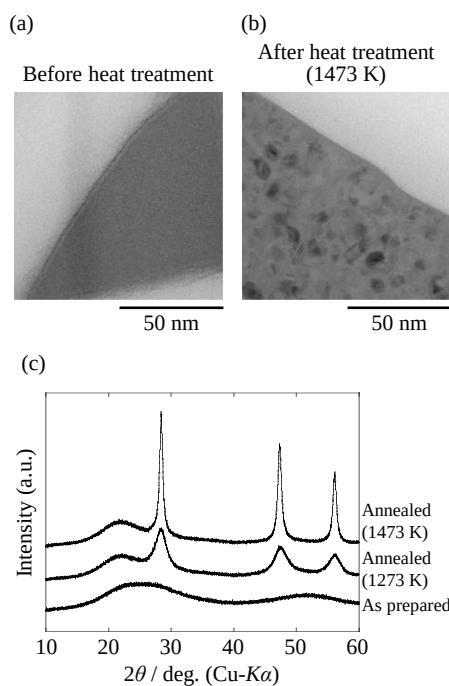


Fig. 4 (a, b) TEM images and (c) XRD patterns for the silicon monoxide particles before and after the heat treatment in an Ar atmosphere at 1273 K and 1473 K.

glovebox. Ethylene carbonate (EC)/diethyl carbonate (DEC) (1:1 by volume) with the addition of $1 \text{ mol L}^{-1} \text{ LiPF}_6$ was used as an electrolyte. The separator was made of polypropylene (PP). The SiO/EC:DEC(1:1) + $1 \text{ mol L}^{-1} \text{ LiPF}_6/\text{Li}$ cells were operated for charge/discharge reactions.

The formation potentials of the related species were evaluated at a slow rate reaction under the constant current (CC) mode at 15 mA g^{-1} until a voltage of 0 V (charge), and at 15 mA g^{-1} until a voltage of 1.5 V (discharge). The cell performance was evaluated under the constant-current/constant-voltage (CC-CV) mode in the voltage range of 0.005–1.5 V at 298 K. The constant-current/constant-voltage mode was used in order to investigate the lifetime of SiO material under the minimization of the overpotential and ormic drop. During the 1st cycle, the charge conditions were a CC of 150 mA g^{-1} until a voltage of 0.005 V, and a CV of 0.005 V until a current of 15 mA g^{-1} ; discharge conditions were a

1
2
3 CC of 150 mA g⁻¹ until a voltage of 1.5 V. During the 2nd cycle, the charge conditions
4
5 were a CC of 450 mA g⁻¹ until a voltage of 0.005 V, and a CV of 0.005 V until a current
6
7 of 15 mA g⁻¹; discharge conditions were a CC of 450 mA g⁻¹ until a voltage of 1.5 V.
8
9 After the 3rd cycle, the charge conditions were a CC of 750 mA g⁻¹ until a voltage of
10
11 0.005 V, and a CV of 0.005 V until a current of 15 mA g⁻¹; discharge conditions were a
12
13 CC of 750 mA g⁻¹ until a voltage of 1.5 V.
14
15
16
17
18
19
20
21


22 **4. Results and discussion**

23 **4-1. Confirmation of formation potentials**

24
25
26 The analysis of the electrochemical reaction can be carried out by separating it into
27
28 equilibrium and kinetic factors. As the first component of the experimental, the electrode
29
30 behavior was examined at a low charge rate in order to minimize the kinetic factor.
31
32

33
34 Figure 5(a) shows the equilibrium potential shift until the end of the Li-Si alloy
35
36 formation with the charge/discharge curves of (SiO + KB + PI) anode recorded at a rate
37
38 of 15 mA g⁻¹, which is slower than a 0.01 C rate. For comparison, the curves of (25wt%
39
40 KB + 75wt% PI) are shown in Fig. 5(b). The rate was 10 mA g⁻¹, which was also as large
41
42 as a 0.01 C rate. Clearly, a potential plateau is observed until 600 mA h g⁻¹ at 0.35–0.5 V
43
44 for the curve of amorphous SiO (Fig. 5(a)). Almost the same capacity of 600 mA h g⁻¹
45
46 with the theoretical value indicates that the plateau corresponds to the formation of
47
48 lithium silicate. It should be noted that the potentials are identical between the
49
50 amorphousSiO and the equilibrium at the end of the plateau. This behavior indicates that
51
52 the potential difference observed by the overpotential for the Li insertion is negligibly
53
54 small, thus suggesting the high Li conduction of lithium silicate phases. Later, the
55
56 potential gradually shifts to the negative range of 0.05–0.35 V. These potentials
57
58
59
60
61
62
63
64
65

(a) SiO + KB + PI

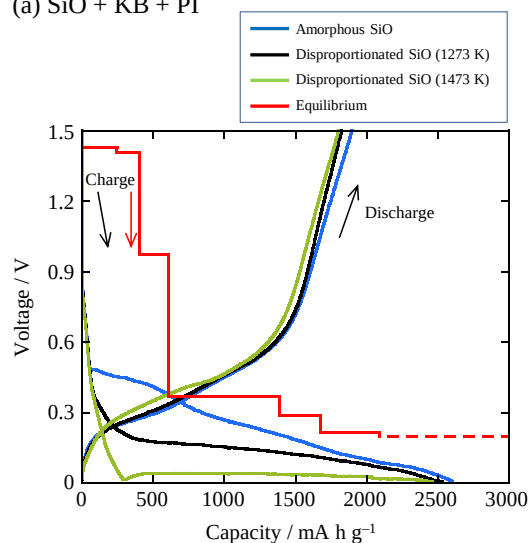

(b) KB + PI

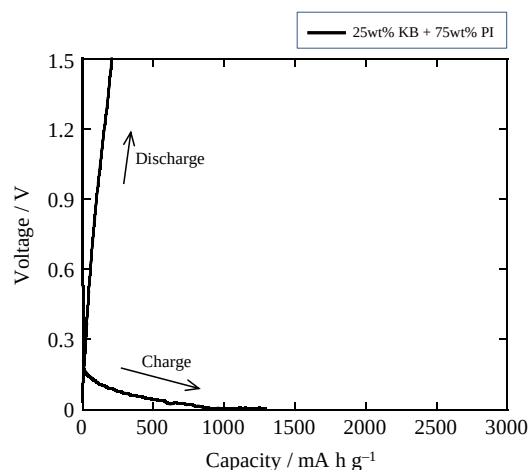


Fig. 5 (a) Charge and discharge curves for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0–1.5 V at 298 K. Charge conditions: a constant current of 15 mA g⁻¹ until a voltage of 0 V. Discharge conditions: a constant current of 15 mA g⁻¹ until a voltage of 1.5 V. (b) Charge and discharge curves for the 1st cycle of KB+PI/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0–1.5 V at 298 K. Charge conditions: a constant current of 10 mA g⁻¹ until a voltage of 0 V. Discharge conditions: a constant current of 10 mA g⁻¹ until a voltage of 1.5 V.

correspond to the formation of Li–Si alloys including the capacity of KB and PI. Also, the capacity should partially contain an irreversible one owing to the SEI formation at negative potentials. Even considering the charge capacity of KB conductive additive and

PI binder of 1292 mA h g^{-1} (Fig. 5(b)), which corresponds to $323 \text{ mA h (g·SiO)}^{-1}$, the capacity of 2610 mA h g^{-1} is larger than the theoretical value at the start of the decomposition of Li_4SiO_4 (2090 mA h g^{-1}), suggesting the partial decomposition of lithium silicates to Li_2O . The relatively rapid potential shift after 2090 mA h g^{-1} might result from the large overpotential owing to the formed Li_2O . In contrast, the plateau that corresponds to the formation of lithium silicate is not observed for the disproportionated SiO . Especially, the charge curve for the disproportionated SiO at 1473 K shows an immediate shift to 0.02 V before 350 mA h g^{-1} . Then, the potential remains around 0.05 V , and the charge reaction finishes at 2463 mA h g^{-1} . This capacity suggests the partial decomposition of lithium silicates in addition to the formation of Li-Si alloys.

To summarize these charge behaviors, the following two points for the equilibrium and kinetics are found out. First, the equilibrium potential curve calculated from the thermodynamic data in this study is valid to discuss the reaction. Second, the overpotential for the Li insertion for lithium silicate formation, which is observed as the deviation from the equilibrium potential, is larger for the disproportionated SiO negative electrode.

4-2. Cell performance

The electrochemical behaviors of the SiO electrodes were compared at a high charge rate. The charge and discharge capacities and coulombic efficiency are summarized in Table 6. Based on the capacities shown in Tables 4 and 5, the charge reaction is expected to proceed between states B and C .

Figure 6(a) shows the equilibrium potential shift until the end of the Li-Si alloy formation, with the charge curves in the initial cycle being recorded in the CC-CV mode. Here, the graphs are standardized by the capacity in each charge run. Furthermore, only

the disproportionated SiO at 1473 K shows the curve in the 2nd cycle. At a high reaction rate, the potential plateau for the formation of lithium silicate above 0.6 V is not observed. However, the charge curve shows more positive potentials for the amorphous SiO than

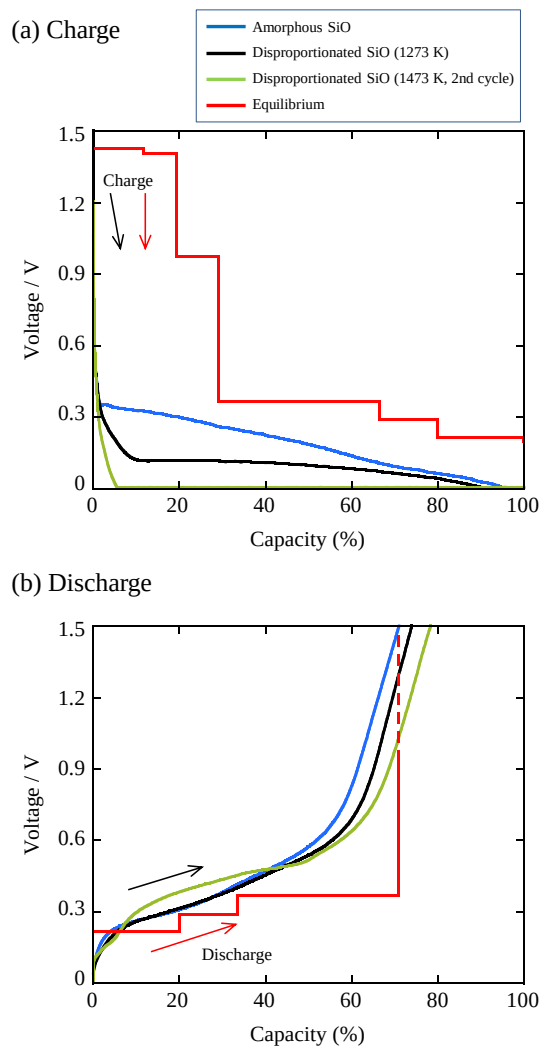


Fig. 6 (a) Charge and (b) discharge curves for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K. Charge conditions: a constant current of 150 mA g⁻¹ until a voltage of 0.005 V and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Discharge conditions: a constant current of 150 mA g⁻¹ until a voltage of 1.5 V.

for the disproportionated SiO electrodes. The disproportionated SiO shows such a large overpotential in the Li insertion that the 1st cycle charge reaction ends at a small capacity of 337 mA h g⁻¹, as shown in Table 6. The cause of the different overpotential is the formed phases in the 1st cycle. Only the Li₂Si₂O₅/Si phases are formed in the initial reaction for the amorphous SiO electrode (Fig. 7(a)). On the other hand, the reaction state starts from the mixture of Si and SiO₂ for the disproportionated SiO, and the Li₂Si₂O₅/Si/SiO₂ phases are formed, as shown in Fig. 7(b). The high resistivity of SiO₂ would result in the large overpotential.

In the discharge reaction for all SiO electrodes, a high discharge capacity above 1898 mA h g⁻¹ and a coulombic efficiency of 71.0% were obtained. The values higher than 1482 mA h g⁻¹ and 70.9% suggest that the deterioration of a SiO electrode does not occur upon decomposition of a small amount of Li₄SiO₄ in the initial cycle. The curves for the electrodes exhibit almost the same behavior with the equilibrium potentials as shown in Fig. 6(b). In spite of the slightly larger discharge capacity, the curve for the disproportionated SiO at 1473 K shows a more positive potential than the other electrodes and the equilibrium curve. This behavior is also explained by the high resistivity and large overpotential of the electrodes.

Table 6 Charge and discharge capacities and coulombic efficiency for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K.

	Charge Capacity, C _c mAh g ⁻¹	Discharge Capacity, C _d mAh g ⁻¹	Coulombic efficiency (%)
Amorphous SiO	2753	1955	71.0
1273 K heat treatment	2623	1898	72.4
1473 K heat treatment	337 (2554)	132 (2001)	39.1 (78.4)


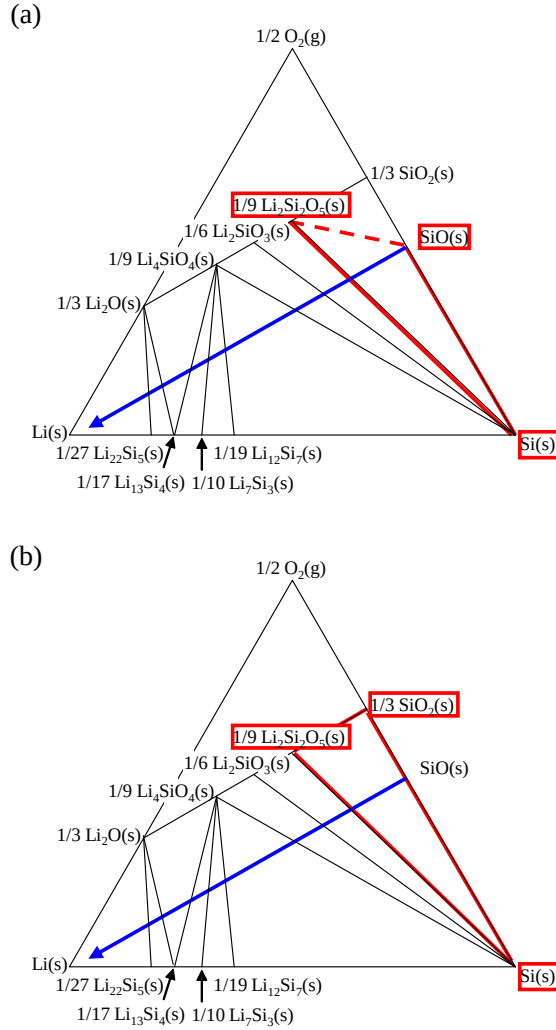


Fig. 7 Comparison of transition of formed phases during the Li insertion for (a) amorphous and (b) disproportionated SiO negative electrodes at 298 K.

The charge/discharge curves for the 2nd and 10th cycles are compared in Figs. 8(a) and (b), respectively. Also in these graphs, the curves for the 3rd and 11th cycle are shown for the disproportionated SiO at 1473 K. Compared to the behaviors in the 1st cycle in Fig. 6, all the SiO electrodes indicate almost the same potential curves in the charge reaction, which are similar with the 1st cycle behavior for the amorphous SiO. As a result of lithium silicate formation during the 1st cycle, the overpotential for Li

(a) 2nd cycle

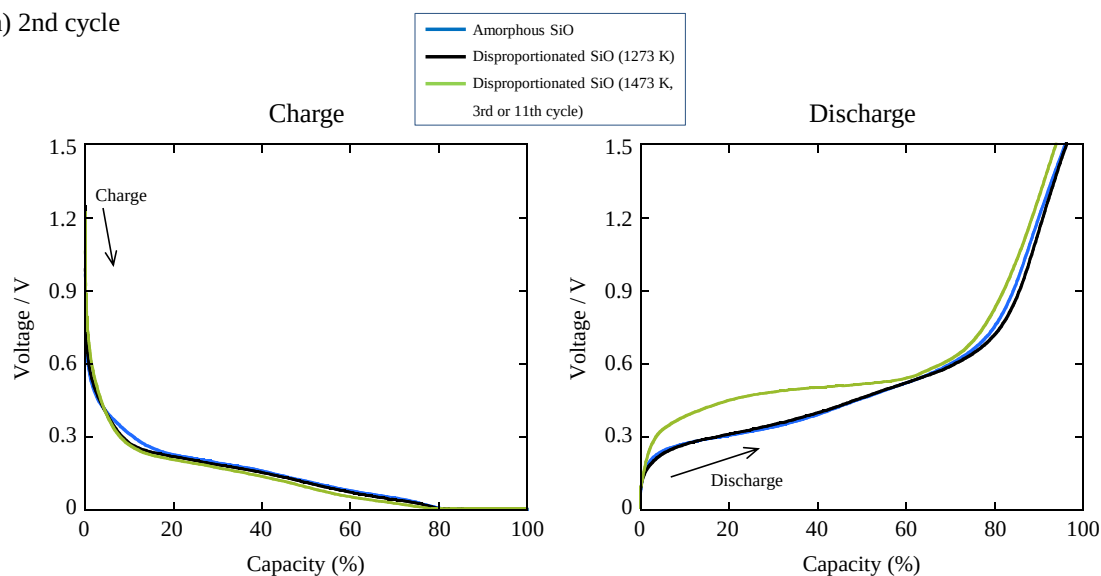

(b) 10th cycle

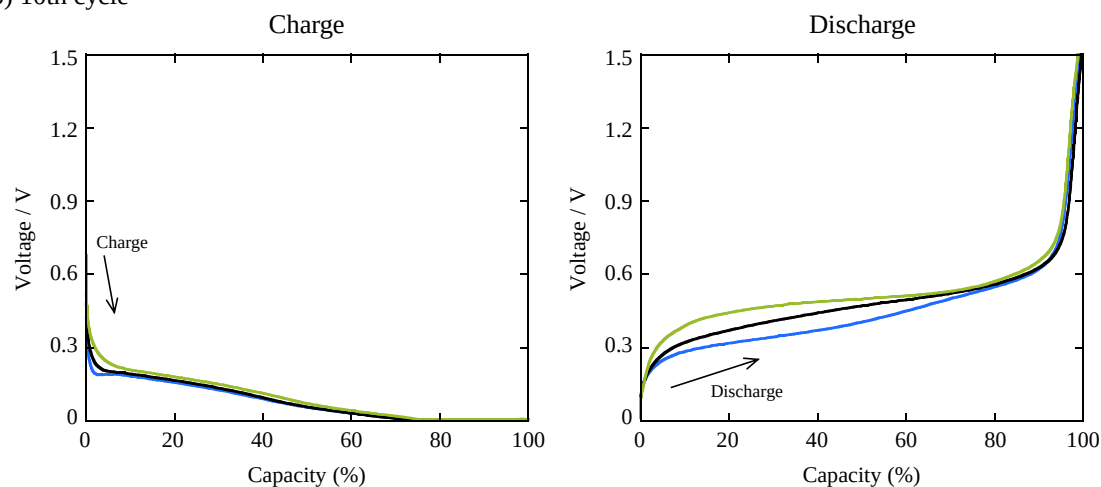


Fig. 8 Charge and discharge curves for the (a) 2nd and (b) 10th cycles of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K. Charge conditions (2nd cycle): a constant current of 450 mA g⁻¹ until a voltage of 0.005 V and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Charge conditions (after 3rd cycle): a constant current of 750 mA g⁻¹ until a voltage of 0.005 V and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Discharge conditions (2nd cycle): a constant current of 450 mA g⁻¹ until a voltage of 1.5 V. Discharge conditions (after 3rd cycle): a constant current of 750 mA g⁻¹ until a voltage of 1.5 V.

insertion became small even for the disproportionated SiO. However, the overpotential for the discharge reaction remains larger for the disproportionated SiO electrodes. With the repetition of cycles, the disproportionated SiO experiences a potential shift to the

positive direction – i.e., a smaller power density. One possible explanation for this behavior concerns the slow kinetics for the discharge reaction; that is because the inhomogeneous formation of $\text{Li}_2\text{Si}_2\text{O}_5/\text{Si}/\text{SiO}_2$ phases disturbs a Li extraction owing to the SiO_2 phase. The homogeneous formation of Li–Si alloys and lithium silicates in a nano scale for the amorphous SiO electrode would enable a faster Li diffusion in the discharge reaction compared to the disproportionated SiO producing large-sized SiO_2 and Li_2O .

Conclusion

The electrochemical behavior of a SiO negative electrode was investigated based on the calculated equilibrium curves. The ternary phase diagram for the Li–Si–O system at 298 K was calculated, and the equilibrium potentials for Li insertion/extraction reactions were diagrammatically indicated. The formation of lithium silicates is the initial reaction of the SiO electrodes, and occurs above 0.36 V vs. Li/Li^+ ; furthermore, the decomposition of lithium silicates starts after the formation of the $\text{Li}_{13}\text{Si}_4$ alloy. The kinetics was discussed from the experimental curves of the SiO electrodes with reference to the equilibria. It was suggested that the Li_4SiO_4 phase formed as an irreversible component had high Li conduction. The disproportionated SiO electrode demonstrated a larger overvoltage than the amorphous SiO owing to the formation of SiO_2 . While the overvoltage became identical in the charge reaction between the amorphous and disproportionated SiO electrodes, a large overpotential (thus resulting in a smaller power density) was observed for the disproportionated SiO in the discharge reaction.

Acknowledgments

The authors would like to thank Assistant Professor Naoyuki Hatada at Kyoto University for the use of Chesta ver. 2.22, and Editage (www.editage.jp) for English language editing.

References

- 1 J. Cabana, L. Monconduit, D. Larcher, M. R. Palacín, *Adv. Mater.* 22 (2010) E170–E192.
- 2 C.-M. Park, J.-H. Kim, H. Kim, H.-J. Sohn, *Chem. Soc. Rev.* 39 (2010) 3115–3141.
- 3 M. V. Reddy, G. V. Subba Rao, B. V. R. Chowdari, *Chem. Rev.* 113 (2013) 5364–5457.
- 4 T. B. Massalski, H. Okamoto, P. R. Subramanian, L. Kacprzak, eds., *Binary Alloy Phase Diagrams*, 2nd ed., ASM International, Metals Park, Ohio, 1990.
- 5 R. J. Temkin, *J. Non-Cryst. Solids* 17 (1975) 215–230.
- 6 A. Hohl, T. Wieder, P. A. van Aken, T. E. Weirich, G. Denninger, M. Vidal, S. Oswald, C. Deneke, J. Mayer, H. Fuess, *J. Non-Cryst. Solids* 320 (2003) 255–280.
- 7 H. R. Philipp, *J. Non-Cryst. Solids* 8–10 (1972) 627–632.
- 8 H. R. Philipp, *J. Phys. Chem. Solids* 32 (1971) 1935–1945.
- 9 K. Schulmeister, W. Mader, *J. Non-Cryst. Solids* 320 (2003) 143–150.
- 10 J. Wang, X. F. Wang, Q. Li, A. Hryciw, A. Meldrum, *Philos. Mag.* 87 (2007) 11–27.
- 11 B. Hallstedt, *Calphad* 16 (1992) 53–61.
- 12 F. T. Ferguson, J. A. Nuth, III, *J. Chem. Eng. Data* 57 (2012) 721–728.
- 13 S. M. Schnurre, J. Gröbner, R. Schmid-Fetzer, *J. Non-Cryst. Solids* 336 (2004) 1–25.
- 14 M. Mamiya, H. Takei, M. Kikuchi, C. Uyeda, *J. Cryst. Growth* 229 (2001) 457–461.
- 15 M. Mamiya, M. Kikuchi, H. Takei, *J. Cryst. Growth* 237–239 (2002) 1909–1914.
- 16 A. Barranco, F. Yubero, J. P. Espinos, J. P. Holgado, A. Caballero, A. R. Gonzalez-Elipe, J. A. Mejias, *Vacuum* 67 (2002) 491–499.
- 17 R. Alfonsetti, L. Lozzi, M. Passacantando, P. Picozzi, S. Santucci, *Appl. Surf. Sci.* 70–71 (1993) 222–225.

- 1
2
3 18 A. Hirata, S. Kohara, T. Asada, M. Arao, C. Yogi, H. Imai, Y. Tan, T. Fujita, M.
4
5 Chen, Nat. Commun. 7 (2016) 11591.
6
7
8 19 J. Yang, Y. Takeda, N. Imanishi, C. Capiglia, J. Y. Xie, O. Yamamoto, Solid State
9 Ionics 152–153 (2002) 125–129.
10
11
12 20 Y. Nagao, H. Sakaguchi, H. Honda, T. Fukunaga, T. Esaka, J. Electrochem. Soc.,
13 151 (2004) A1572–A1575.
14
15
16 21 M. Miyachi, H. Yamamoto, H. Kawai, T. Ohta, M. Shirakata, J. Electrochem. Soc.
17 152 (2005) A2089–A2091.
18
19
20 22 M. Miyachi, H. Yamamoto, H. Kawai, J. Electrochem. Soc. 154 (2007) A376–A380.
21
22
23 23 T. Kim, S. Park, S. M. Oh, J. Electrochem. Soc. 154 (2007) A1112–A1117.
24
25
26 24 Y. Yamada, Y. Iriyama, T. Abe, Z. Ogumi, J. Electrochem. Soc. 157 (2010) A26–
27 A30.
28
29
30 25 C.-M. Park, W. Choi, Y. Hwa, J.-H. Kim, G. Jeong, H.-J. Sohn, J. Mater. Chem. 20
31 (2010) 4854–4860.
32
33
34 26 S. Komaba, K. Shimomura, N. Yabuuchi, T. Ozeki, H. Yui, K. Konno, J. Phys.
35 Chem. C 115 (2011) 13487–13495.
36
37
38 27 J.-H. Kim, C.-M. Park, H. Kim, Y.-J. Kim, H.-J. Sohn, J. Electroanal. Chem. 661
39 (2011) 245–249.
40
41
42 28 H. Yamamura, K. Nobuhara, S. Nakanishi, H. Iba, S. Okada, J. Ceram. Soc. Jpn. 119
43 (2011) 855–860.
44
45
46 29 T. Miyuki, Y. Okuyama, T. Sakamoto, Y. Eda, T. Kojima, T. Sakai,
47 Electrochemistry 80 (2012) 401–404.
48
49
50 30 G. Jeong, J.-H. Kim, Y.-U. Kim, Y.-J. Kim, J. Mater. Chem. 22 (2012) 7999–8004.
51
52
53 31 K. W. Kim, H. Park, J. G. Lee, J. Kim, Y.-U. Kim, J. H. Ryu, J. J. Kim, S. M. Oh,
54 Electrochim. Acta 103 (2013) 226–230.
55
56
57
58
59
60
61
62
63
64
65

- 1
2
3 32 H. Takezawa, K. Iwamoto, S. Ito, H. Yoshizawa, J. Power Sources 244 (2013) 149–
4
5 157.
6
7
8 33 T. Morita, N. Takami, J. Electrochem. Soc. 153 (2006) A425–A430.
9
10 34 J.-H. Kim, H.-J. Sohn, H. Kim, G. Jeong, W. Choi, J. Power Sources 170 (2007)
11
12 456–459.
13
14
15 35 Y. Kobayashi, S. Seki, Y. Mita, Y. Ohno, H. Miyashiro, P. Charest, A. Guerfi, K.
16
17 Zaghib, J. Power Sources 185 (2008) 542–548.
18
19
20 36 A. Velucharmy, C.-H. Doh, D.-H. Kim, J.-H. Lee, D.-J. Lee, K.-H. Ha, H.-M. Shin,
21
22 B.-S. Jin, H.-S. Kim, S.-I. Moon, C.-W. Park, J. Power Sources 188 (2009) 574–577.
23
24
25 37 M. Yamada, A. Ueda, K. Matsumoto, T. Ohzuki, J. Electrochem. Soc. 158 (2011)
26
27 A417–A421.
28
29
30 38 J. Wang, H. Zhao, J. He, C. Wang, J. Wang, J. Power Sources 196 (2011) 4811–4815.
31
32
33 39 A. Guerfi, P. Charest, M. Dontigny, J. Trottier, M. Lagacé, P. Hovington, A. Vijh, K.
34
35 Zaghib, J. Power Sources 196 (2011) 5667–5673.
36
37
38 40 Q. Si, K. Hanai, T. Ichikawa, M. B. Phillipps, A. Hirano, N. Imanishi, O. Yamamoto,
39
40 Y. Takeda, J. Power Sources 196 (2011) 9774–9779.
41
42 41 Y. Ren, J. Ding, N. Yuan, S. Jia, M. Qu, Z. Yu, J. Solid State Electrochem. 16 (2012)
43
44 1453–1460.
45
46
47 42 C. Guo, D. Wang, Q. Wang, B. Wang, T. Liu, Int. J. Electrochem. Sci. 7 (2012)
48
49 8745–8752 .
50
51
52 43 H. Sepehri-Amin, T. Ohkubo, M. Kodzuka, H. Yamamura, T. Saito, H. Iba, K. Hono,
53
54 Scripta Materialia 69 (2013) 92–95.
55
56
57 44 Q. Yuan, F. Zhao, Y. Zhao, Z. Liang, D. Yan, Electrochim. Acta 115 (2014) 16–21.
58
59
60 45 Y. Yang, W. Peng, H. Guo, Z. Wang, X. Li, Y. Zhou, Y. Liu, Trans. Nonferrous Met.
61
62 Soc. China 17 (2007) 1339–1342.
63
64
65

- 1
2
3 46 B. Guo, J. Shu, Z. Wang, H. Yang, L. Shi, Y. Liu, L. Chen, *Electrochem. Commun.*
4
5 10 (2008) 1876–1878.
6
7
8 47 Q. Sun, B. Zhang, Z.-W. Fu, *Appl. Sur. Sci.* 254 (2008) 3774–3779.
9
10 48 Y. Yao, J. Zhang, L. Xue, T. Huang, A. Yu, *J. Power Sources* 196 (2011) 10240–
11 10243.
12
13
14 49 C. Ban, B. B. Kappes, Q. Xu, C. Engtrakul, C. V. Ciobanu, A. C. Dillon, Y. Zhao,
15 *Appl. Phys. Lett.* 100 (2012) 243905.
16
17
18
19 50 Y. Zhang, Y. Li, Z. Wang, K. Zhao, *Nano Lett.* 14 (2014) 7161–7170.
20
21
22 51 M. Yamada, A. Inaba, S. Nagayama, K. Matsumoto, A. Ueda, T. Ohzuku, Meeting
23 Abstract of The 50th Battery Symposium in Japan, Nov. 30–Dec. 2, Kyoto, Japan,
24 2009, p. 191.
25
26
27
28 52 Y. Hwa, C.-M. Park, H.-J. Sohn, *J. Power Sources* 222 (2013) 129–134.
29
30
31 53 X. Yang, Z. Wen, L. Zhang, M. You, *J. Alloy Compd.* 464 (2008) 265–269.
32
33
34 54 H. Migge, *J. Nucl. Mater.* 151 (1988) 101–107.
35
36
37 55 O. Götzmann, *J. Nucl. Mater.* 167 (1989) 213–224.
38
39 56 J. Sangster, A.D. Pelton, *J. Phase Equilibria* 13 (1992) 296–299.
40
41
42 57 H. A. Wriedt, *Bulletin of Alloy Phase Diagrams* 11 (1990) 43–61.
43
44 58 H. Okamoto, *J. Phase Equilibria Diffusion* 28 (2007) 309–310.
45
46
47 59 R. S. Roth, ed., *Phase Equilibria Diagrams: Phase Diagrams for Ceramists*, American
48 Ceramic Society, Waterville, Ohio, 1995.
49
50
51 60 S. S. Kim, T. H. Sanders, Jr., *J. Am. Ceram. Soc.* 74 (1991) 1833–1840.
52
53
54 61 A. Skokan, H. Wedemeyer, D. Vollath, E. Günther, *Proc. 14th Symp. on Fusion*
55 *Technology*, Avignon, p. 1255 (1986).
56
57
58 62 H. Okamoto, *Bull. Alloy Phase Diagrams* 11 (1990) 306–312.
59
60
61 63 HSC Chemistry[®] ver. 5.1, Outokumpu Research Oy, Poly, Finland, 2002.
62
63
64
65

- 1
2
3 64 I. Barin, Thermochemical Data of Pure Substances, VCH Verlags Gesellschaft,
4
5 Weinheim, 1993.
6
7
8 65 A. J. Bard, R. Parsons, J. Jordan, Standard potentials in aqueous solution, Marcel
9 Dekker Inc., New York, 1985.
10
11
12 66 Landolt-Börnstein: Thermodynamic Properties of Inorganic Material, Scientific
13 Group Thermodata Europe (SGTE), Springer-Verlag, Berlin-Heidelberg, Part 1,
14 1999.
15
16
17
18
19 67 O. Knacke, O. Kubaschewski, K. Hesselman: Thermochemical Properties of
20 Inorganic Substances, 2nd ed., Springer-Verlag, Berlin, 1991.
21
22
23
24 68 B. J. McBride, S. Gordon, M. A. Reno, eds., Thermodynamic Data for Fifty
25 Reference Elements, NASA-TP-3287, N93-19977, 1993.
26
27
28
29 69 Glushko Thermocenter of the Russian Academy of Sciences, IVTAN Association,
30 Izhorskaya 13/19, 127412 Moscow, Russia, 1994.
31
32
33
34 70 Landolt-Börnstein: Thermodynamic Properties of Inorganic Material, Scientific
35 Group Thermodata Europe (SGTE), Springer-Verlag, Berlin-Heidelberg, Part 4,
36 2001.
37
38
39
40
41 71 I. Barin, Thermochemical Data of Pure Substances, VCH Verlags Gesellschaft,
42 Weinheim, 1989.
43
44
45
46 72 I. Barin, O. Knacke, O. Kubaschewski: Thermochemical Properties of Inorganic
47 Substances, Supplement, Springer-Verlag, Berlin, 1977, p. 861.
48
49
50
51 73 S. C. Lai, J. Electrochem. Soc. 123 (1976) 1196–1197.
52
53
54 74 R. A. Sharma, R. N. Seefurth, J. Electrochem. Soc. 123 (1976) 1763–1768.
55
56 75 V. P. Nikolaiev, A. G. Morachevskii, A. I. Demidov, E. V. Bairachnyi, Zh. Prikl.
57 Khim. 53 (1980) 2088–2090.
58
59
60
61 76 C. J. Wen, R. A. Huggins, J. Solid State Chem. 37 (1981) 271–278.
62
63
64
65

- 1
2
3 77 K. Amezawa, N. Yamamoto, Y. Tomii, Y. Ito, J. Electrochem. Soc. 145 (1998)
4
5 1986–1993.
6
7
8 78 A. I. Demidov, A. G. Morachevskii, V. P. Nikolaev, N. V. Berenda, Russ. J. Appl.
9
10 Chem. 61 (1988) 1373–1375.
11
12 79 M. H. Braga, L. F. Malheiros, I. Ansara, J. Phase Equilib. 16 (1995) 324–330.
13
14
15 80 N. Hatada, Chesta ver. 2.22, Department of Materials Science and Engineering,
16
17 Kyoto University, Japan. <http://www.aqua.mtl.kyoto-u.ac.jp/chestaEng.html>.
18
19
20 81 S. C. Jung, H.-J. Kim, J.-H. Kim, Y.-K. Han, J. Phys. Chem. C 120 (2016) 886–892.
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Table 1 Representative reports on battery and electrode characteristics of the SiO negative electrode.

Author, Ref.	Year	SiO phase	Intermediate phase	Initial charge capacity (mAh g ⁻¹)	Initial discharge capacity (mAh g ⁻¹)	Initial coulombic efficiency (%)	Note
Yang et al. [19]	2002	Amor.	-	ca. 2250	ca. 1300	ca. 57.8	-
Nagao et al. [20]	2004	Amor.	SiO ₂	1594	-	-	Neutron elastic scattering
Miyachi et al. [21]	2005	Amor.	Li-Si-O, Li ₂ O	2404	598	24.9	XPS
Miyachi et al. [22]	2007	-	Li-Si-O, Li ₂ O	2520	1260	50.0	Metal-doped SiO, XPS
Kim et al. [23]	2007	-	Li-Si-O, Li ₂ O	2680	1470	54.9	NMR, HR-TEM, electrochemical dilatometry. Plateau at 0.8 V vs. Li ⁺ /Li in 1st discharge
Yamada et al. [24]	2007	-	-	-	-	-	Kinetics evaluation by AC impedance spectroscopy
Park et al [25]	2010	Amor./dispro.	SiO _x	2216/185	1104/94	49.8/50.8	TEM, Disproportionated at 800, 1000, and 1200 °C.
Komaba et al [26]	2011	-	-	ca. 1800	826	45.9	-
Kim et al., [27]	2011	Amor./dispro.	Li-Si-O, Li ₂ O	2410	1300	53.9	NMR, HR-TEM, Differential capacity peaks at 0.08 and 0.24 V vs. Li ⁺ /Li
Yamamura et al. [28]	2011	Dispro.	Li-Si-O	2548	1791	70.3	Plateau at 0.2 and 0.5 V vs. Li ⁺ /Li in 1st discharge. First principles calculation. SiO ₂ was also reacted.
Miyuki et al. [29]	2011	Amor./dispro.	-	-	-	-	LiFePO ₄ /SiO full cell.
Jeong et al. [30]	2012	Dispro.	-	1757	1265	72.0	TiO ₂ coated SiO
Kim et al. [31]	2013	Dispro.	-	1958	1413	72.2	Carbon coated SiO. Differential capacity peaks at 0.06, 0.21, 0.31 and 0.48 V vs. Li ⁺ /Li after 5th cycle
Takezawa et al. [32]	2013	Amor.	Li-Si-O, Li ₂ O	2418	1306	54.0	SiO _x (0.17 < x < 1.34) was used. XPS

-: Not given

Table 2 Thermodynamic data for Li–Si–O system at 298 K used for the calculation.

Compound				Standard Gibbs energy, $G^\circ / \text{kJ mol}^{-1}$	Standard Gibbs energy of formation, $\Delta G_f^\circ / \text{kJ mol}^{-1}$	Ref
Formula	Component					
	Li	Si	O			
Li	1	0	0	−8.7	0	[64–66]
Si	0	1	0	−5.6	0	[67]
O ₂	0	0	2	−61.1	0	[66,68]
Li ₁₂ Si ₇	12	7	0	−570.5	−426.9	Calculated from [79]
Li ₇ Si ₃	7	3	0	−312.7	−235.0	
Li ₁₃ Si ₄	13	4	0	−525.6	−390.1	
Li ₂₂ Si ₅	22	5	0	−758.8	−539.4	
Li ₂ O	2	0	1	−609.1	−561.2	[64,69 ,70]
SiO ₂	0	1	2	−923.2	−856.5	[71]
Li ₂ Si ₂ O ₅	2	2	5	−2598.3	−2416.9	[64]
Li ₂ SiO ₃	2	1	3	−1673.4	−1558.8	[67]
Li ₄ SiO ₄	4	1	4	−2366.2	−2203.6	[72]

Table 3 Equilibrium phases and electrode potentials during the Li insertion for a SiO negative electrode at 298 K.

Equilibrium phases				Activity or pressure				Equilibrium potential, E , / V (vs. Li^+/Li)
				$\log p_{\text{O}_2}$	$\log a_{\text{Si}}$	$\log a_{\text{Li}}$	a_{Li}	
①	Si	SiO_2						
②	Si	SiO_2	$\text{Li}_2\text{Si}_2\text{O}_5$	-150.1	0	-24.2	6.9×10^{-25}	1.428
③	Si	$\text{Li}_2\text{Si}_2\text{O}_5$						↓
④	Si	$\text{Li}_2\text{Si}_2\text{O}_5$	Li_2SiO_3	-150.4	0	-23.8	1.6×10^{-24}	1.406
⑤	Si	Li_2SiO_3						↓
⑥	Si	Li_2SiO_3	Li_4SiO_4	-160.2	0	-16.5	3.4×10^{-17}	0.973
⑦	Si	Li_4SiO_4						↓
⑧	Si	$\text{Li}_{12}\text{Si}_7$	Li_4SiO_4	-180.6	0	-6.24	5.8×10^{-17}	0.368
⑨	$\text{Li}_{12}\text{Si}_7$	Li_4SiO_4						↓
⑩	$\text{Li}_{12}\text{Si}_7$	Li_7Si_3	Li_4SiO_4	-182.1	-2.27	-4.91	1.2×10^{-5}	0.290
⑪	Li_7Si_3	Li_4SiO_4						↓
⑫	Li_7Si_3	$\text{Li}_{13}\text{Si}_4$	Li_4SiO_4	-183.2	-5.17	-3.67	2.1×10^{-4}	0.217
⑬	$\text{Li}_{13}\text{Si}_4$	Li_4SiO_4						↓
⑭	$\text{Li}_{13}\text{Si}_4$	Li_4SiO_4	Li_2O	-183.3	-6.21	-3.35	4.5×10^{-4}	0.198
⑮	$\text{Li}_{13}\text{Si}_4$	Li_2O						↓
⑯	$\text{Li}_{13}\text{Si}_4$	$\text{Li}_{22}\text{Si}_5$	Li_2O	-190.4	-12.0	-1.58	2.7×10^{-2}	0.093
⑰	$\text{Li}_{22}\text{Si}_5$	Li_2O						↓
⑱	$\text{Li}_{22}\text{Si}_5$	Li_2O	Li	-196.7	-18.9	0	1	0

Table 4 The calculated reactions for the Li insertion of a SiO negative electrode at 298 K.

	Reaction	Atomic ratio of Li with respect to SiO	Charge capacity, C_c / mA h g ⁻¹
③	$5\text{SiO} + 2\text{Li}^+ + 2\text{e}^- \rightarrow 3\text{Si} + \text{Li}_2\text{Si}_2\text{O}_5$	0.40	243
⑤	$3\text{SiO} + 2\text{Li}^+ + 2\text{e}^- \rightarrow 2\text{Si} + \text{Li}_2\text{SiO}_3$	0.67	405
⑦	$4\text{SiO} + 4\text{Li}^+ + 4\text{e}^- \rightarrow 3\text{Si} + \text{Li}_4\text{SiO}_4$	1.00	608
⑨	$28\text{SiO} + 64\text{Li}^+ + 64\text{e}^- \rightarrow 3\text{Li}_{12}\text{Si}_7 + 7\text{Li}_4\text{SiO}_4$	2.29	1390
⑪	$12\text{SiO} + 33\text{Li}^+ + 33\text{e}^- \rightarrow 3\text{Li}_7\text{Si}_3 + 3\text{Li}_4\text{SiO}_4$	2.75	1672
⑬	$16\text{SiO} + 55\text{Li}^+ + 55\text{e}^- \rightarrow 3\text{Li}_{13}\text{Si}_4 + 4\text{Li}_4\text{SiO}_4$	3.44	2090
⑮	$4\text{SiO} + 21\text{Li}^+ + 21\text{e}^- \rightarrow \text{Li}_{13}\text{Si}_4 + 4\text{Li}_2\text{O}$	5.25	3192
⑰	$5\text{SiO} + 32\text{Li}^+ + 32\text{e}^- \rightarrow \text{Li}_{22}\text{Si}_5 + 5\text{Li}_2\text{O}$	6.40	3891

Table 5 The calculated reactions for the Li extraction of a SiO negative electrode at 298 K.

Charged state	Dis-charged state	Reaction	Atomic ratio of Li with respect to SiO	Discharge capacity, C_d / mA h g ⁻¹	Coulombic efficiency (%)
⑬	⑪	$3\text{Li}_{13}\text{Si}_4 + 4\text{Li}_4\text{SiO}_4 \rightarrow 4\text{Li}_7\text{Si}_3 + 4\text{Li}_4\text{SiO}_4 + 11\text{Li}^+ + 11\text{e}^-$	0.69	418	20.0
	⑨	$21\text{Li}_{13}\text{Si}_4 + 28\text{Li}_4\text{SiO}_4 \rightarrow 12\text{Li}_{12}\text{Si}_7 + 28\text{Li}_4\text{SiO}_4 + 129\text{Li}^+ + 129\text{e}^-$	1.15	700	33.5
		$3\text{Li}_{13}\text{Si}_4 + 4\text{Li}_4\text{SiO}_4 \rightarrow 12\text{Si} + 4\text{Li}_4\text{SiO}_4 + 39\text{Li}^+ + 39\text{e}^-$	2.44	1482	70.9
⑮	⑦	$\text{Li}_{13}\text{Si}_4 + 4\text{Li}_2\text{O} \rightarrow 3\text{Si} + \text{Li}_4\text{SiO}_4 + 17\text{Li}^+ + 17\text{e}^-$	4.25	2584	81.0
⑰		$4\text{Li}_{22}\text{Si}_5 + 20\text{Li}_2\text{O} \rightarrow 15\text{Si} + 5\text{Li}_4\text{SiO}_4 + 108\text{Li}^+ + 108\text{e}^-$	5.40	3283	84.4

Table 6 Charge and discharge capacities and coulombic efficiency for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K.

	Charge Capacity, C_c mAh g ⁻¹	Discharge Capacity, C_d mAh g ⁻¹	Coulombic efficiency (%)
Amorphous SiO	2753	1955	71.0
1273 K heat treatment	2623	1898	72.4
1473 K heat treatment	337 (2554)	132 (2001)	39.1 (78.4)

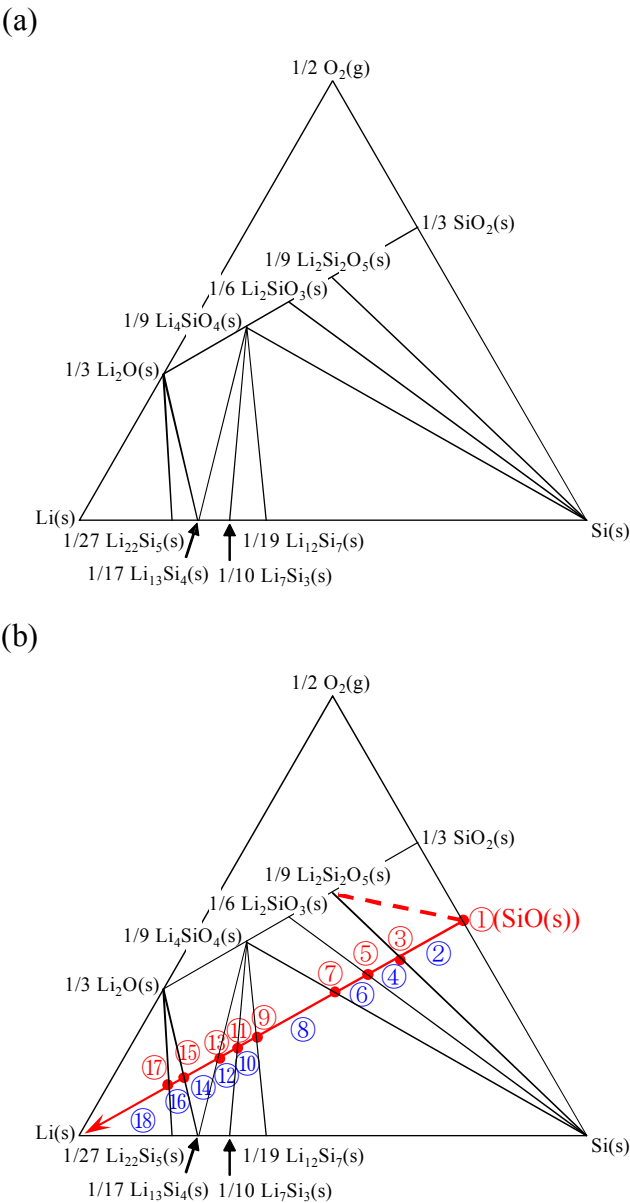


Fig. 1 (a) Calculated ternary phase diagram for the Li–Si–O system at 298 K.
(b) Transition of formed phases during the Li insertion for a SiO negative electrode at 298 K shown in the ternary phase diagram for Li–Si–O system.

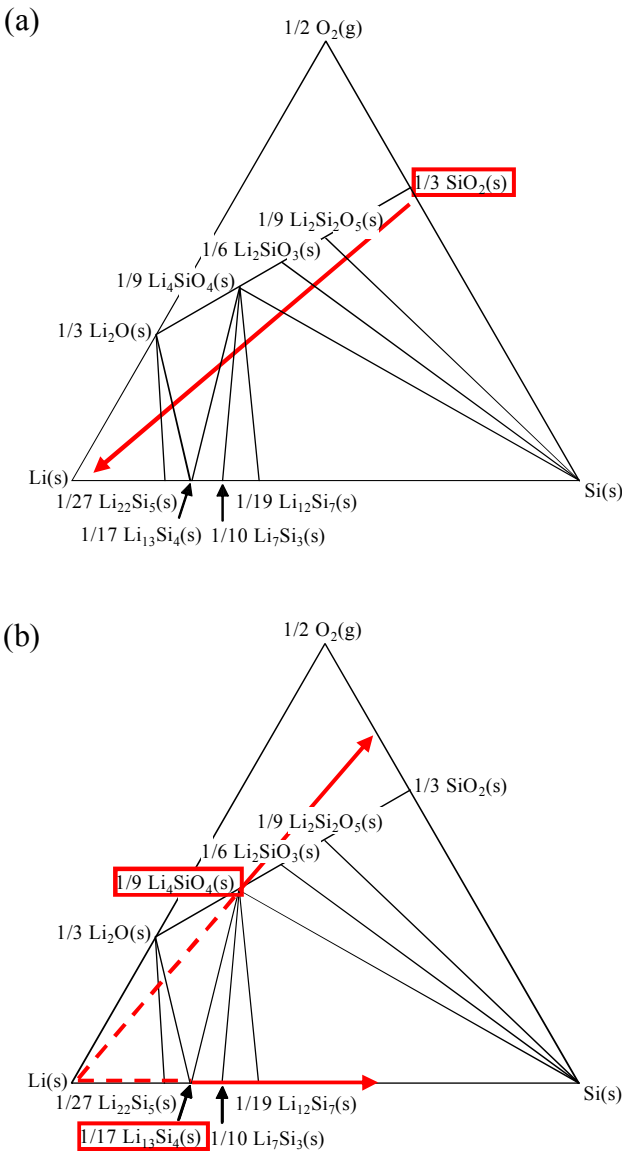


Fig. 2 Reaction pathway during (a) the Li insertion for a SiO₂ negative electrode and (b) the Li desertion for a Li₄SiO₄ electrode at 298 K shown in the ternary phase diagram for Li-Si-O system.

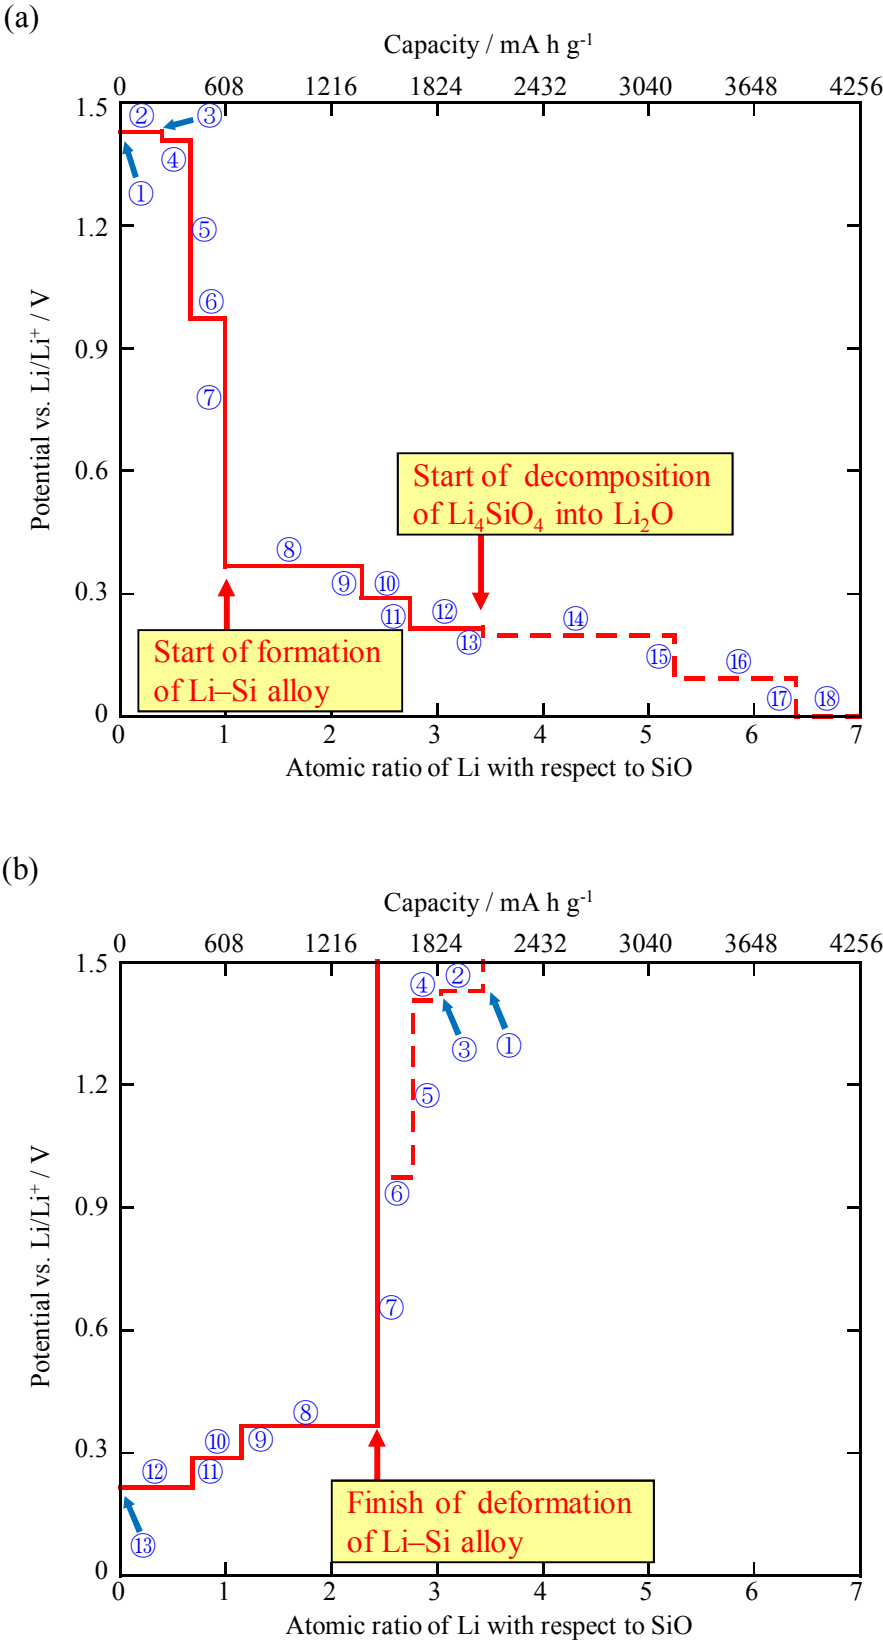


Fig. 3 Transition of equilibrium electrode potential during the Li (a) insertion and (b) desertion after the formation of Li₁₃Si₄ for a SiO negative electrode at 298 K shown in the ternary phase diagram for Li-Si-O system.

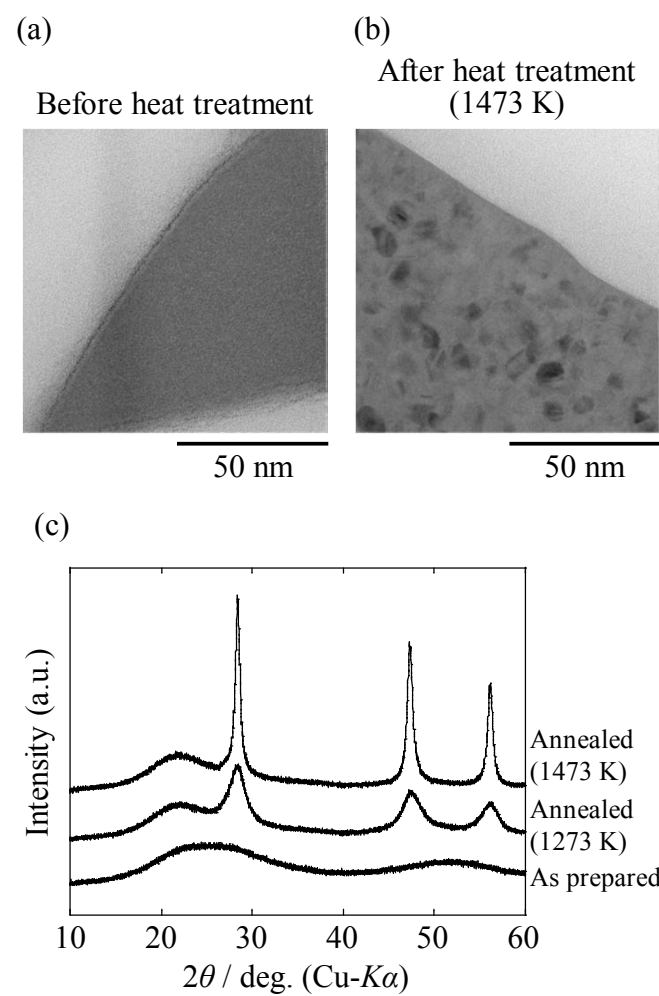


Fig. 4 (a, b) TEM images and (c) XRD patterns for the silicon monoxide particles before and after the heat treatment in an Ar atmosphere at 1273 K and 1473 K.

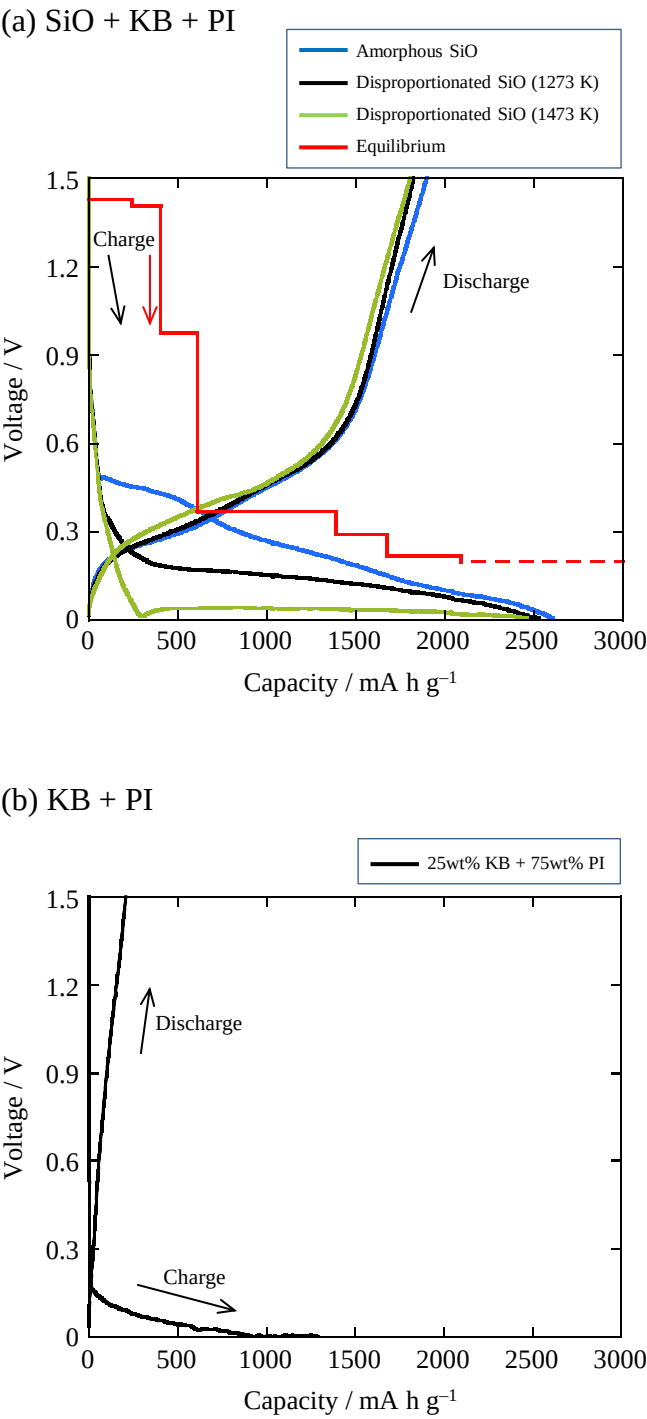


Fig. 5 (a) Charge and discharge curves for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0–1.5 V at 298 K. Charge conditions: a constant current of 15 mA g⁻¹ until a voltage of 0 V. Discharge conditions: a constant current of 15 mA g⁻¹ until a voltage of 1.5 V. (b) Charge and discharge curves for the 1st cycle of KB+PI/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0–1.5 V at 298 K. Charge conditions: a constant current of 10 mA g⁻¹ until a voltage of 0 V. Discharge conditions: a constant current of 10 mA g⁻¹ until a voltage of 1.5 V.

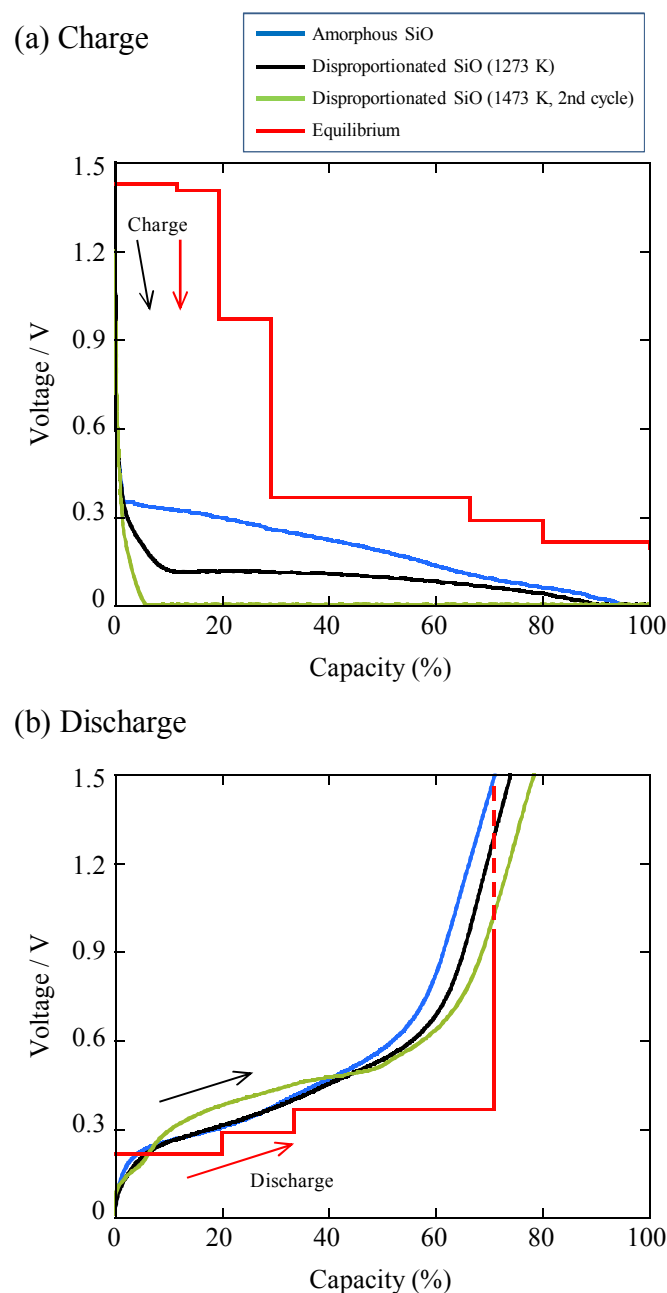


Fig. 6 (a) Charge and (b) discharge curves for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K. Charge conditions: a constant current of 150 mA g⁻¹ until a voltage of 0.005 V and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Discharge conditions: a constant current of 150 mA g⁻¹ until a voltage of 1.5 V.


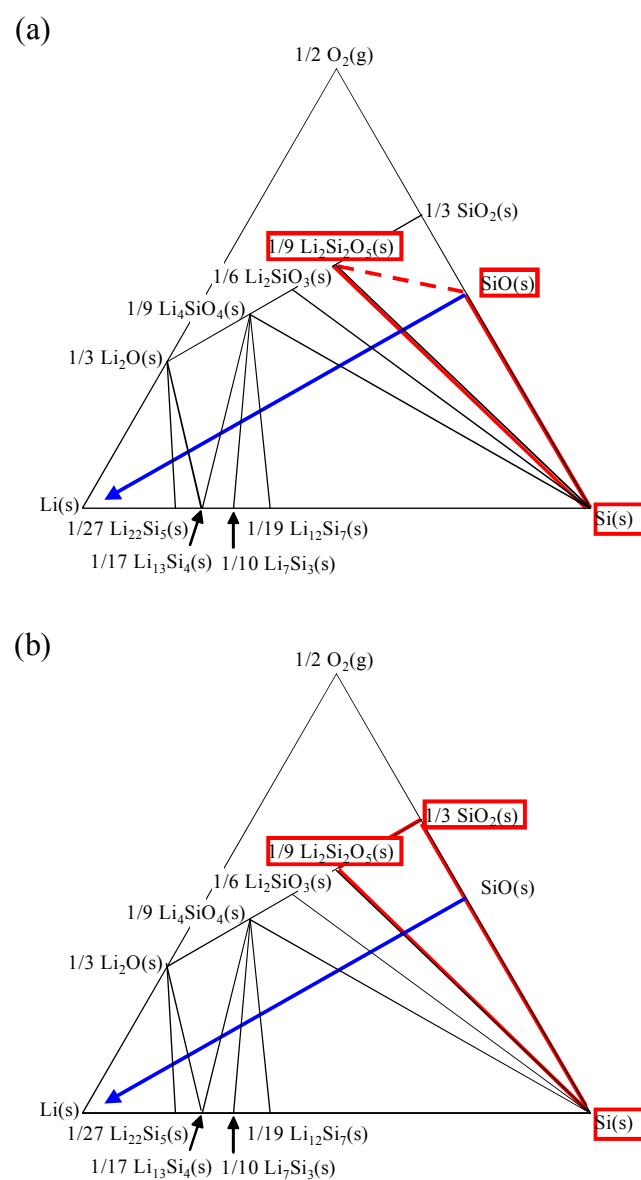


Fig. 7 Comparison of transition of formed phases during the Li insertion for (a) amorphous and (b) disproportionated SiO negative electrodes at 298 K.

(a) 2nd cycle

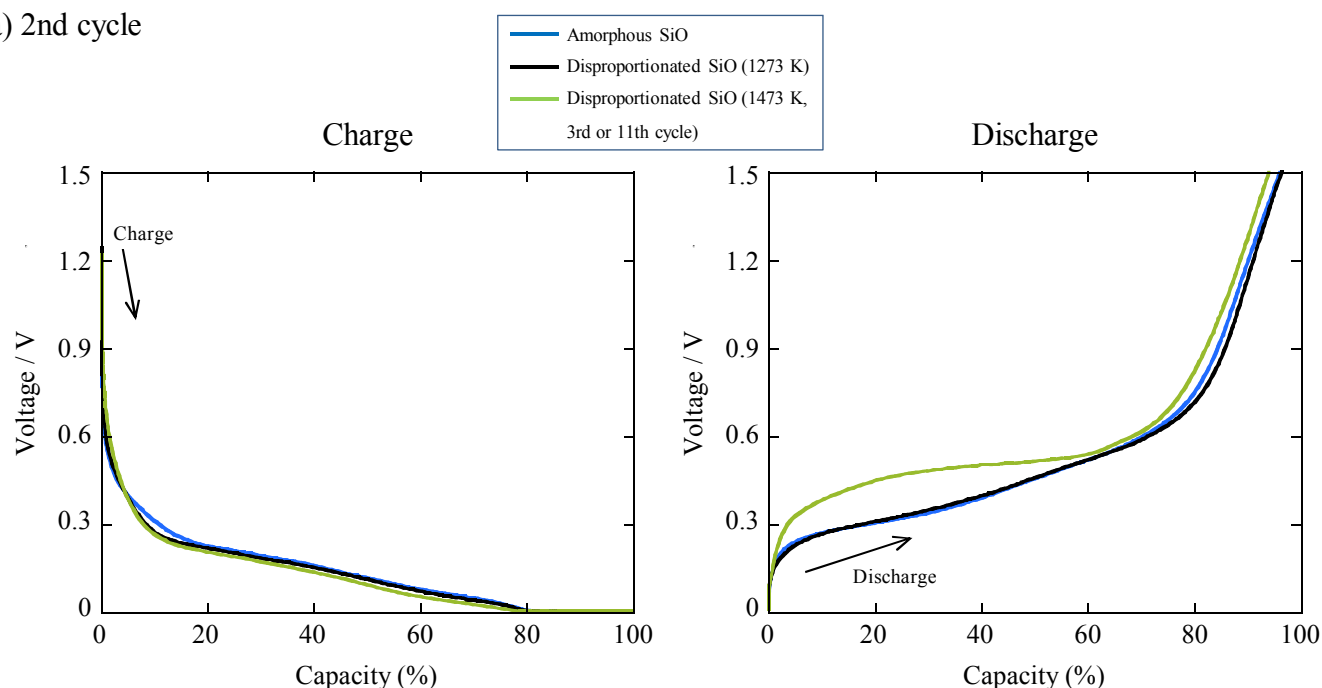

(b) 10th cycle

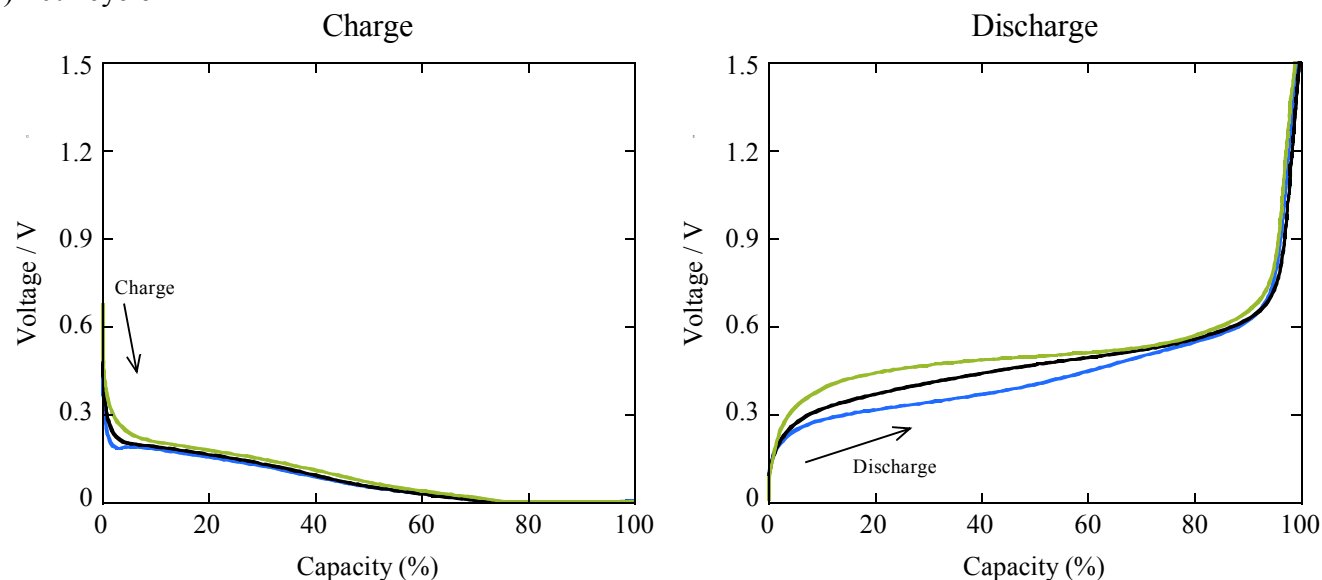


Fig. 8 Charge and discharge curves for the (a) 2nd and (b) 10th cycles of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K. Charge conditions (2nd cycle): a constant current of 450 mA g⁻¹ until a voltage of 0.005 V and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Charge conditions (after 3rd cycle): a constant current of 750 mA g⁻¹ until a voltage of 0.005 V and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Discharge conditions (2nd cycle): a constant current of 450 mA g⁻¹ until a voltage of 1.5 V. Discharge conditions (after 3rd cycle): a constant current of 750 mA g⁻¹ until a voltage of 1.5 V.

Table and figure captions

Table 1 Representative reports on battery and electrode characteristics of the SiO negative electrode.

Table 2 Thermodynamic data for the Li–Si–O system at 298 K used for the calculation.

Table 3 Equilibrium phases and electrode potentials during the Li insertion reaction for a SiO negative electrode at 298 K.

Table 4 The calculated reactions for the Li insertion of a SiO negative electrode at 298 K.

Table 5 The calculated reactions for the Li extraction of a SiO negative electrode at 298 K.

Table 6 Charge and discharge capacities and coulombic efficiency for the 1st cycle of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K.

Fig. 1 (a) Calculated ternary phase diagram for the Li–Si–O system at 298 K. (b) Transition of formed phases during the Li insertion for a SiO negative electrode at 298 K shown in the ternary phase diagram for Li–Si–O system.

Fig. 2 Reaction pathway during (a) the Li insertion for a SiO₂ negative electrode and (b) the Li extraction for a Li₄SiO₄ electrode at 298 K shown in the ternary phase diagram for Li–Si–O system.

Fig. 3 Transition of equilibrium electrode potential during the Li (a) insertion and (b) extraction after the formation of $\text{Li}_{13}\text{Si}_4$ for a SiO negative electrode at 298 K shown in the ternary phase diagram for Li–Si–O system.

Fig. 4 (a, b) TEM images and (c) XRD patterns for the silicon monoxide particles before and after the heat treatment in an Ar atmosphere at 1273 K and 1473 K.

Fig. 5 (a) Charge and discharge curves for the 1st cycle of $\text{SiO/EC:DEC(1:1)} + 1 \text{ mol L}^{-1}$ LiPF_6/Li cells in the voltage range of 0–1.5 V at 298 K. Charge conditions: a constant current of 15 mA g^{-1} until a voltage of 0 V. Discharge conditions: a constant current of 15 mA g^{-1} until a voltage of 1.5 V. (b) Charge and discharge curves for the 1st cycle of $\text{KB+PI/EC:DEC(1:1)} + 1 \text{ mol L}^{-1}$ LiPF_6/Li cells in the voltage range of 0–1.5 V at 298 K. Charge conditions: a constant current of 10 mA g^{-1} until a voltage of 0 V. Discharge conditions: a constant current of 10 mA g^{-1} until a voltage of 1.5 V.

Fig. 6 (a) Charge and (b) discharge curves for the 1st cycle of $\text{SiO/EC:DEC(1:1)} + 1 \text{ mol L}^{-1}$ LiPF_6/Li cells in the voltage range of 0.005–1.5 V at 298 K. Charge conditions: a constant current of 150 mA g^{-1} until a voltage of 0.005 V, and a constant voltage of 0.005 V until a current of 15 mA g^{-1} . Discharge conditions: a constant current of 150 mA g^{-1} until a voltage of 1.5 V.

Fig. 7 Comparison of transition of formed phases during the Li insertion for (a) amorphous and (b) disproportionated SiO negative electrodes at 298 K.

Fig. 8 Charge and discharge curves for the (a) 2nd and (b) 10th cycles of SiO/EC:DEC(1:1) + 1 mol L⁻¹ LiPF₆/Li cells in the voltage range of 0.005–1.5 V at 298 K. Charge conditions (2nd cycle): a constant current of 450 mA g⁻¹ until a voltage of 0.005 V, and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Charge conditions (after 3rd cycle): a constant current of 750 mA g⁻¹ until a voltage of 0.005 V, and a constant voltage of 0.005 V until a current of 15 mA g⁻¹. Discharge conditions (2nd cycle): a constant current of 450 mA g⁻¹ until a voltage of 1.5 V. Discharge conditions (after 3rd cycle): a constant current of 750 mA g⁻¹ until a voltage of 1.5 V.